
02063

NCAR-TN-28

# Superpressure Balloons for Horizontal Soundings of the Atmosphere

VINCENT E. LALLY

June 1967



# **NCAR** Technical Notes

NATIONAL CENTER FOR ATMOSPHERIC RESEARCH Boulder, Colorado

NCAR LIBRARY



The National Center for Atmospheric Research (NCAR) is dedicated to the advancement of the atmospheric sciences for the benefit of mankind. It is operated by the University Corporation for Atmospheric Research (UCAR), a private, university-controlled, non-profit organization, and is sponsored and principally funded by the National Science Foundation.

NCAR shares with other atmospheric research groups four interrelated, long-range objectives that provide justification for major expenditures of public and private funds:

- To ascertain the feasibility of controlling weather and climate, to develop the techniques for control, and to bring about the beneficial application of this knowledge;
- To bring about improved description and prediction of astrophysical influences on the atmosphere and the space environment of our planet;
- To bring about improved description and prediction of atmospheric processes and the forecasting of weather and climate;
- To improve our understanding of the sources of air contamination and to bring about the application of better practices of air conservation.

The research and facilities operations of NCAR are conducted in four organizational entities:

The Laboratory of Atmospheric Sciences
The High Altitude Observatory
The Facilities Laboratory
The Advanced Study Program

All visiting scientist programs and joint-use facilities of NCAR are available to scientists from UCAR-member and non-member institutions (including private and government laboratories in the United States and abroad) on an equal basis. The member universities of UCAR are:

University of Alaska
University of Arizona
University of California
University of Chicago
Colorado State University
University of Colorado
Cornell University
University of Denver

Florida State University
University of Hawaii
The Johns Hopkins University
Massachusetts Institute of Technology
University of Michigan
University of Minnesota
New York University

University of Oklahoma

Pennsylvania State University

Saint Louis University

Texas A & M University

University of Texas

University of Utah

University of Washington

University of Wisconsin

NCAR-TN-28 402B


# Superpressure Balloons for Horizontal Soundings of the Atmosphere

VINCENT E. LALLY 201A

June 1967 P167 Dables Figs. 501

Superforesture meteorological meteorological observations

NATIONAL CENTER FOR ATMOSPHERIC RESEARCH MOIA
Boulder, Colorado

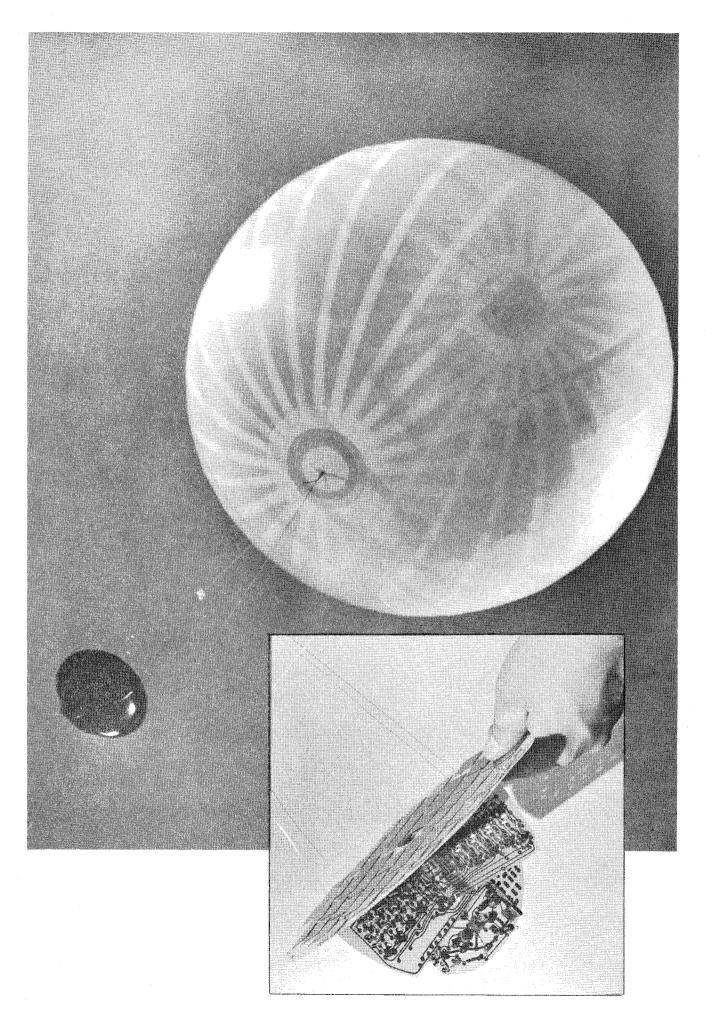

#### FOREWORD

These notes are designed to provide under one cover the status of superpressure balloon technology. For a number of years the promise of long duration flight with superpressure balloons has been taken on faith alone. Between March, 1966, and March, 1967, 85 flights were made in the southern hemisphere under the auspices of the New Zealand Meteorological Service, the Environmental Science Services Administration, and the National Science Foundation. The flight program was conducted by the National Center for Atmospheric Research.

This technical note is a collection of previous reports and articles which have been updated on the basis of the Southern Hemisphere GHOST (Global HOrizontal Sounding Technique) flight program.

The establishment of the GHOST flight program in the southern hemisphere was a major achievement in international cooperation. We are grateful for the assistance of D. A. Davies, Secretary-General of the World Meteorological Organization; Dr. John F. Gabites, Director of the New Zealand Meteorological Service; and Dr. Robert F. White of ESSA for their efforts in obtaining approval and cooperation throughout the southern hemisphere. The cooperation of the volunteer tracking stations has been of inestimable value during the first year of GHOST flights. The assistance of these stations is gratefully asknowledged: Luanda, Angola; McMurdo Station, Antarctica; Buenos Aires, Argentina; Melbourne, Australia; Rio de Janeiro, Brazil; Papeete, French Polynesia; Plaisance, Mauritius; Pretoria, South Africa; and Broken Hill, Zambia.

I am personally indebted to Ernest W. Lichfield and Robert W. Frykman who developed the remarkable electronics systems used on all GHOST flights, to Neil Carlson who designed and fabricated much of the

electronics, to Marcel Verstraete who supervised balloon testing and launching during much of the program, and to Jane Von Letkemann who patiently assembled these notes.

The analysis of trajectory data for the 85 GHOST flights is presently under way under the supervision of Samuel B. Solot. Complete trajectories will be published at a later date.

Vincent E. Lally

June 1967

## CONTENTS

Forewo	rd.	· · · · · · · · · · · · · · · · · · ·	•	•	•	•	ii
List o	f Fi	gures			•		vi:
List o	f Tal	bles		•	•		i
I.	THE	SUPERPRESSURE BALLOON HOW IT FLIES				•	
II.	BAL	LOON SHAPES AND STRESSES					3
	A.B.C.	Prolate Spheroid	•	•	•	٠.	3 2 4 5
III.	FREI	E LIFT AND SUPERTEMPERATURE STRESSES					$\epsilon$
	A. B. C.	Suprepressure Due to Free Lift		_	_		6
IV.	BALI	LOON LIFE					10
	A. B.	Diffusion			•	· .	10 11
v.	THE	RADIATION ENVIRONMENT					20
	A.B.C.	Infrared Radiation		•		•	20 22 22 23
VI.	BALI	OON STABILITY		•			27
	в. С. D.	Diurnal Changes in Altitude Due to Supertempe Change in Altitude Due to Gas Loss	•		•		27 28 28 31
VII.	SENS	ORS FOR USE ON SUPREPRESSURE FLIGHTS					36
	В.	Temperature		•	•	•	36 37 38

	D.	The St	rain	Ga	ug	e/A	ir	Te	mp	er	at	ur	e	Со	mb	in	at	io	n					38
	Ε.	Wind S	hear				•		•	•	•		•	•		•		•	•	•	•	•	•	39 42
	F.	Turbul	ence	•	•	• •	•	•	•	•	•	•	•	•	•	•	•	•	•	•	•	•	•	42
VIII.	MODE	S OF B	ALLO	ON	FA	ILU:	RE				• .	•		•			•				•			43
	Α.	Liquid	Wat	er	Ad	hes	ior	n					•											43
	В.	Superc	oole	d W	at	er,	I	ce	Cr	уs	ta	1s	а	nd	F	ro	st	:						43
	C.	Method	s of	Mi	ni.	miz	ing	3 F	'ai	1u	re		•	•	•	•	•	•	•	•	•	•	•	44
IX.	BALL	OON TE	STIN	G I	EC	HNI	QUE	ES																49
	Α.	Integr	itv	Tes	ts																			49
	В.	Leakag	-																				_	51
	C.	Factor					•																	52
	•		,		0	·	•		•	•	•	•	•		•	•	•	•	•	•	•		•	-
Х.	BALI	LOON MA	TERI	ALS	3		•			•	•		•	•	•	•	•		•	•	•	•	•	54
	Α.	Desire	d Ch	ara	ct	eri	st	ics	3	_											_			54
		Minimu																						54
XI.	LOCA	TION T	EC HN	IQU	JES																			60
	Α.	High F	reau	enc	v :	Dir	eci	tic	n	Fi	nd	lin	g	<b>(</b> H	ΓD	F)								60
	В.	Sun El																						61
	C.	HFDF a																						61
	D.	Loran																						62
	Ε.	OMEGA																						62
	F.	Satell		-													,							63
Append:	ixe <b>s</b>																•							65
	List	of Sy	mbol	S										•									•	67
_			_																					
Α.	Equa	ations	for	Bal	llo	on	De	Si8	gn	ar	ıd	Ва	LL	.00	n	P€	ri	01	cme	inc	e	•	•	69
В.		n <b>ar</b> ies													st	cŀ	ıuı	ccl	1,	Νe	₽W			
	Ze	e <b>ala</b> nd	M	laro	ch	196	6	to	Με	arc	ch	19	67	'	•	•	•	•	•	•	•	•	•	78
Refere	nces											•												L67

# FIGURES

1.	Ascent rate of superpressure balloons for 10 and 20% free lift 7
2.	Diffusion of helium through a Mylar balloon
3.	Creep as a function of stress
4.	Strain and stress variations on a floating balloon

## TABLES

1.	Superpressure due to free lift 8
2.	Permeability ( $\delta$ ) of films to gas at $25^{\circ}C$
3.	Permeability of Mylar to helium
4.	Relative leakage rates of gases for three types of leaks 16
5.	Percentage gas loss per day for typical balloon sizes 17
6.	Estimated leakage rate as a function of hole size
7.	Estimated gas loss per day for typical balloons for various hole sizes
8.	Radiation from a black body as a function of temperature 21
9.	Radiation environment for superpressure balloon
10.	Altitude change with gas loss for typical superpressure balloon designs
11.	Altitude displacement of superpressure balloons as a function of vertical wind
12.	Wind shear on long lines

#### I. THE SUPERPRESSURE BALLOON -- HOW IT FLIES

Three types of balloons are in common use for scientific research or meteorological observations.

The <u>rubber or neoprene balloon</u> is used for vertical soundings either as a pilot balloon or as a radiosonde-carrying balloon. It is inflated with a lifting gas (hydrogen, helium, ammonia, or methane) and stretches as it ascends. When the material has stretched to three to six times the unstressed length (the balloon would then be thirty to two hundred times its original volume) the film ruptures.

The <u>zero-pressure plastic balloon</u> (most commonly polyethylene) is used to carry scientific instruments to a predetermined density level. The plastic balloon is only partially filled with gas on the ground. As the balloon ascends, the expanding gas fills the envelope. This type of balloon has some form of open appendix or duct to release the excess gas which provides the free lift for ascent. When the excess gas is forced out, the balloon floats at its constant-density altitude until there is a change in the radiation environment. At sunset the gas cools, the volume decreases, and the balloon descends to the ground unless ballast is released.

The <u>superpressure balloon</u> is a non-extensible balloon which is sealed to prevent gas release. It has converted the free-lift gas into superpressure by the time floating level is reached. Variations in the radiation environment produce changes in the superpressure, but not in the balloon volume. As long as the balloon is superpressured, it will continue to float at a constant-density level.

The superpressure balloons which have been fabricated to date utilize plastic materials which do stretch as the superpressure changes, producing small changes in balloon volume. In Section VI the variation

in float altitude because of changes in balloon volume is discussed. As gas diffuses through the balloon film or escapes through pin-hole leaks, the mass of the system changes. The effect of these changes on stability is also discussed in Section VI.

Any change in total mass of the balloon system will cause a variation in altitude. The system mass may increase because of the adhesion of liquid water to the balloon film; however, simple surface treatments can reduce the amount of water contained on the balloon to a negligible amount. The accretion of ice in the form of frost, ice crystals or frozen droplets resulting from impact of the balloon with supercooled water is a much more serious problem. No reliable technique has been developed for removing ice from the balloon film. If the balloon accumulates an amount of ice which exceeds the initial free lift of the system, the balloon will descend. A complete description of present knowledge of the modes of balloon failure and methods of minimizing icing is given in Section VIII.

#### II. BALLOON SHAPES AND STRESSES

A balloon can be manufactured in any desired shape. When the balloon is superpressured, the stress distribution will vary over the surface, with the highest stresses in areas of maximum radii of curvature. Only the sphere provides uniform stress distribution over the entire surface. Intuitively, it would appear that the sphere is the most efficient shape for providing the largest enclosed volume at a given maximum stress and a given mass of material. However, constructional difficulties arise which can offset much of the geometric efficiency of the sphere. In addition, the application may be one where factors other than efficiency are of prime importance. For example, the cylinder is a simple structure which is less affected by vertical currents at low altitudes; the tetroon provides a compromise between ease of construction and design efficiency which makes it suitable for low-cost flight programs where maximum performance is not required.

#### A. THE PROLATE SPHEROID

The majority of shapes which are useful in the design of superpressure balloons can be considered as prolate spheroids. The sphere can be considered as a prolate spheroid in which the major and minor radii are equal. The cylinder can be considered as a prolate spheroid for which the major radius is very much larger than the minor radius. The volume of a prolate spheroid is:

$$V = \frac{4}{3} \pi a b^2$$

The surface area of the spheroid is:

$$A = 2\pi \left[b^2 + \frac{ab}{\epsilon} \arcsin \epsilon\right]$$

where a and b are the major and minor radii and  $e^2 = 1 - \left(\frac{b}{a}\right)^2$ . The maximum meridional stress on a prolate spheroid is:

$$S_{m} = \frac{286 \ b \ \Delta P}{t}$$

where

 $S_m$  = meridional stress (psi)

 $\Delta P$  = superpressure (mb)

t = film thickness (mils)

The maximum circumferential stress on a prolate spheroid is:

$$S_c = \frac{572 \text{ b}}{\text{t}} \left(1 - \frac{\text{b}^2}{2\text{a}^2}\right) \Delta P$$

A prolate spheroid with a fineness ratio of  $3\left(\frac{a}{b}=3\right)$  appears to be an ideal vehicle for maintaining vertical stability at low altitudes. In Section VI the stability of such a balloon is compared with that of the sphere.

#### B. THE CYLINDER

The cylinder is an inefficient shape for a superpressure balloon, but it is simple to manufacture and provides a low drag relative to an equivalent sphere. It has application to low-altitude flight with light payloads. The circumferential stress on a long cylinder is:

$$S_c = \frac{572 \text{ r } \Delta P}{t}$$

where r = radius (m), and other symbols are as above. The meridional stress on a long cylinder is:

$$S_{m} = \frac{286 \text{ r } \Delta P}{t}$$

#### C. THE SPHERE

A sphere manufactured of homogeneous film without seals will have a uniform stress distribution over the entire surface which can be expressed as:

$$S = \frac{286 \text{ r } \Delta P}{t}$$

Spherical balloons have always been fabricated from a series of flat gores. Usually 18 to 24 gores are used to approximate a sphere. The tapes which seal the gores provide additional meridional strength. The stress around the balloon equator can be approximated by the formula for homogeneous material. The stress from pole to pole will be approximately two-thirds the equatorial stress.

#### D. THE TETROON

The tetroon, or tetrahedron, is made from a cylinder whose circumference is equal to 2.31 times the cylinder length. The ends are sealed as pillows with the seams orthogonal to each other. A complete description of the tetroon is given in Ref. 1. The basic advantage of the tetroon is manufacturing simplicity. Stresses on the triangular faces are much higher than the stresses on a sphere. The tetroon is not considered further in this report.

#### III. FREE LIFT AND SUPERTEMPERATURE STRESSES

#### A. SUPERPRESSURE DUE TO FREE LIFT

A superpressure balloon is normally launched as a sealed container. It can be lifted to the desired altitude by a tow balloon or it can be inflated with an excess of lifting gas which is valved upon reaching altitude. This second alternate is undesirable for long duration flights since it adds a complicated device which may cause leakage. Fortunately, the free lift used to carry superpressure balloons aloft without assistance (10 to 20%) provides a satisfactory ascent rate. Figure 1 illustrates the variation of ascent rate with free lift for spherical balloons. This free lift becomes the superpressure at floating altitude (the "bank" of excess gas which is drawn upon to sustain flight for extended periods).

Equations 1 through 10 (Appendix A) provide the derivation of superpressure due to free lift. The superpressure due to free lift equals the percentage free lift times the atmospheric pressure at float altitude, if we define percentage free lift as the ratio of free lift to the gross system mass including the mass of the lifting gas. Table 1 relates percentage superpressure to percentage free lift for the most common definition in which the mass of the gas is not included in the system mass.

#### B. SUPERPRESSURE DUE TO SUPERTEMPERATURE

Equations 11 through 14 derive the relationship of superpressure to supertemperature. We can made a very good approximation that a 5% supertemperature produces a superpressure of 5%. It should be clearly noted that changes in air temperature do not directly affect the superpressure. The balloon floats along a constant-density surface. If the

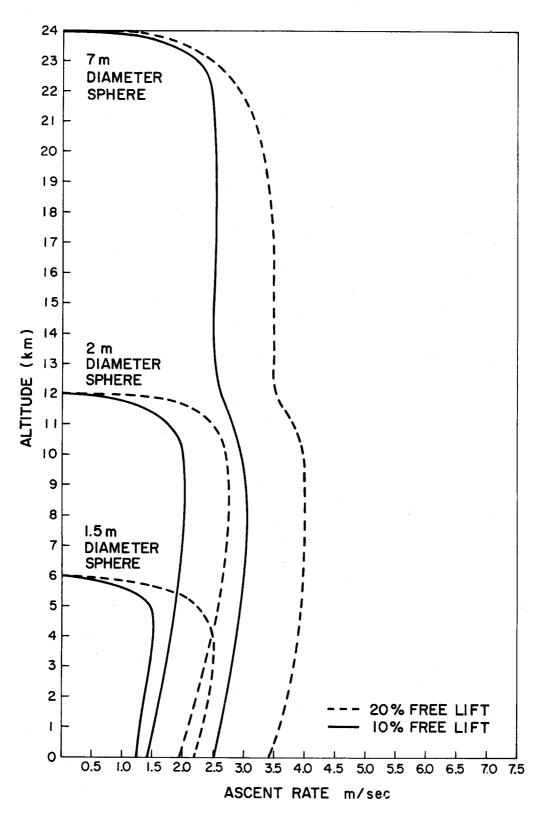


Fig. 1 Ascent rate of superpressure balloons for 10 and 20% free lift

Table 1
SUPERPRESSURE DUE TO FREE LIFT a

Free lift ÷ Balloon mass +	Superpressure = Atmospheric pressure	Free lift Balloon mass + payload mass + gas mass
payload mass	Helium	Hydrogen
0.02	0.018	0.019
0.04	0.035	0.038
0.06	0.052	0.056
0.08	0.070	0.075
0.10	0.087	0.093
0.12	0.104	0.111
0.14	0.123	0.130
0.16	0.138	0.148
0.18	0.154	0.167
0.20	0.172	0.185
0.25	0.214	0.230
0.30	0.251	0.276
0.40	0.336	0.366
0.50	0.414	0.455
0.60	0.493	0.540
0.70	0.569	0.627
0.80	0.642	0.715
0.90	0.714	0.798
1.00	0.784	0.876
1.15	0.885	1.000
1.32	1.000	

<sup>&</sup>lt;sup>a</sup> If free lift is defined as the ratio of free lift to <u>total</u> system mass, the free lift superpressure as a fraction of atmospheric pressure is equal to the free lift ratio.

air temperature decreases, the balloon floats at a lower pressure -- but the superpressure does not change.

There are only two factors that produce superpressure -- the initial free lift and the difference between lifting gas temperature and air temperature, which we call supertemperature. Supertemperature is an awkward expression (especially since it is so often negative), but is it used in place of the more common but incorrect expression, superheat.

The supertemperature varies not only from night to day, but also during the day as the radiation environment changes. The extremes for polyester (polyethylene terephthalate) balloons measured in flights to date are over the range -5% (tropics, 500 mb, nighttime) to +10% (polar, 200 mb, daytime). The flight data are limited and actual extremes may be much larger. The sunset effect on these balloons has been measured at 3 to 5%. A more detailed analysis of supertemperature variations is included in Section VI.

#### C. STRESSES PRODUCED BY SUPERPRESSURE

The expression for the stress produced by free-lift superpressure and the supertemperature-produced superpressure is given by Eq. 17. In practical units this can be stated as:

$$S_{\text{sphere}} = \frac{286 \text{ r P}}{t} \left[ f + (1 + f) \frac{\Delta T}{T} \right]$$

where

S = stress (psi)

r = radius (m)

P = atmospheric pressure

t = film thickness (mils)

f = free lift ratio

 $\frac{\Delta T}{T}$  = fractional superheat

#### IV. BALLOON LIFE

#### A. DIFFUSION

For the purpose of this report, we shall distinguish between two methods of gas loss from a superpressure balloon: diffusion and leakage. We define diffusion as the gas loss through the walls of a balloon that is without defect in material or assembly.

We define leakage as gas loss through defects in the balloon, whether these be pinholes, defective seals, or abrasions which permit a larger gas loss than is realized with film areas without imperfection.

When a plastic film contains a gas, the gas dissolves in the film and diffuses to the outside. The rate at which the gas passes through the barrier varies directly as the permeability of the film to the gas,  $\delta$ , and the partial pressure, p, of the gas across the film, and inversely as the film thickness, t:

Rate of loss = 
$$\frac{\delta pA}{t}$$

For a balloon, the percentage loss of gas per day can be obtained by dividing the rate of loss by balloon volume:

Per cent volume loss per day = 
$$\frac{100\delta pA}{tV}$$

For a spherical balloon, the percentage loss of gas per day is:

Sphere per cent volume loss per day = 
$$\frac{300\delta p}{rt}$$

where

$$\delta = \text{film permeability } (m^3/m^2, \text{mil/mb-day})$$

p = partial pressure of contained gas (mb)

r = balloon radius (m)

t = thickness of film (mils)

For a cylindrical balloon, the equation becomes:

Cylinder per cent volume loss per day =  $\frac{200\delta p}{rt}$ 

The permeability of plastic films is a marked function of temperature. Permeability at low atmospheric temperatures ( $200^{\circ}$  K) may be less than 1% of the value at high temperatures ( $300^{\circ}$  K).

Table 2 provides permeability data for a number of gases and films at 25°C. Table 3 gives specific data on the permeability of the polyester Mylar to helium at various temperatures. The values are derived from a number of sources. Since the permeability of Mylar to helium varies with the percent crystalinity of the Mylar film, the data available are not consistent. The data derived by Lally, Mellor, and Verstraete in extensive tests with inflated balloons indicate lower values than given by other sources, with the exception of the General Mills, Inc. tests made in 1960. These values are used in Table 3, since the combination of stressed film, bilamination, and taped areas appears to provide a lower overall diffusion than would be indicated from the other test results.

Figure 2 shows expected life of balloons at several altitudes using permeability values from Table 3 and an assumption of 10% gas loss to failure.

Circled points on the 500-mb and 200-mb curves are the designs which have been used in the initial GHOST test flights in the southern hemisphere. Life expectancies for balloons without defect are 180 days for a 2.5-mil balloon at 500 mb and 3 years for a 1.5-mil balloon at 200 mb.

#### B. LEAKAGE

Diffusion of gas through a plastic film is a function of the partial pressure of the gas contained within the film. Leakage is a function of

Table 2  $\label{eq:permeability} \mbox{PERMEABILITY ($\delta$) OF FILMS TO GASES AT $25^{\circ}$ C}$ 

Film		Gas	a	
	Не	H <sup>S</sup>	O <sup>S</sup>	N <sub>S</sub>
Saran	$7.5 \times 10^{-7}$ (0.03)	2.5 × 10 <sup>-7</sup> (0.01)	1.2 × 10 <sup>-8</sup> (0.0005)	2.5 × 10 <sup>-9</sup> (0.0001)
Mylar	22 × 10 <sup>-7</sup> (0.088)	15 × 10 <sup>-7</sup> (0.06)	7.5 × 10 <sup>-8</sup> (0.003)	1.2 × 10 <sup>-8</sup> (0.0005)
Polyethylene	185 × 10 <sup>-7</sup> (0.74)	220 × 10 <sup>-7</sup> (0.86)	$140 \times 10^{-7}$ (0.55)	50 × 10 <sup>-7</sup> (0.20)

 $<sup>^{\</sup>rm a}$  First-line entries are  $\delta$  in NCAR units; bracketed entries are in "trade" units. To convert from trade units to NCAR units, multiply by 2.5  $\times$  10  $^{-5}$  .

NCAR units:  $\frac{m^3 \text{ mil}}{m^2 \text{ day mb}}$ 

Trade units:  $\frac{\text{std cc cm } 10^{-9}}{\text{sec cm}^2 \text{ cm Hg}}$ 

Table 3
PERMEABILITY OF MYLAR TO HELIUM

Temperature, T	Permeabil	lity, δ
°ĸ	m <sup>3</sup> mil m <sup>2</sup> day mb	std cc cm 10 <sup>-9</sup> sec cm <sup>3</sup> cm Hg
300	22 × 10 <sup>-7</sup>	0.090
295	19	0.076
290	16	0.067
285	14	0.056
280	12	0.047
275	10	0.039
270	8.2	0.033
265	6.8	0.027
260	5.5	0.022
255	4.7	0.019
250	3.8	0.015
245	3.0	0.012
240	2.4	0.0095
235	1.9	0.0076
230	1.5	0.0058
225	1.1	0.0044
220	8.7 × 10 <sup>-8</sup>	0.0035
215	6.5	0.0026
210	5.0	0.0020

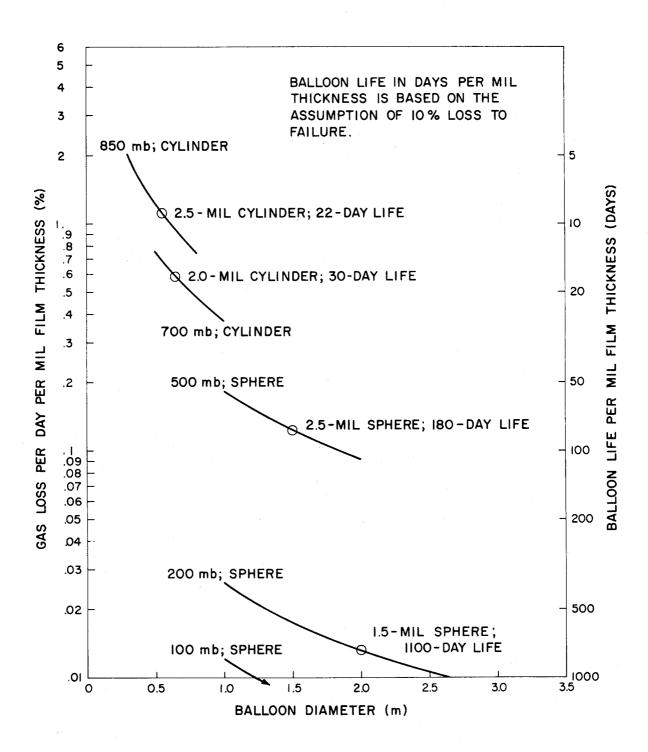


Fig. 2 Diffusion of helium through a Mylar balloon

the differential pressure, which we call either overpressure or superpressure. For "small" leaks, the flow through the orifice is molecular and is directly proportional to overpressure. For "large" leaks, the flow is proportional to the square of the overpressure. For "very large" leaks, the flow is turbulent and flow rate is proportional to the square root of overpressure. Molecular flow occurs when the mean free path of the gas molecules exceeds the largest dimension of the hole. The mean free path for helium in the lower atmosphere is at all times less than 1 micron. A 1-micron hole will not produce a significant gas loss in a superpressure balloon in a period of a year. It is possible to have many hundreds of microholes in a plastic film which could cause serious gas loss, but the technique of laminating two sheets of film in balloon construction should eliminate such imperfections. The bilaminated film can develop holes in handling, manufacture, packing, and testing, but the number of holes that are introduced should be few.

The characteristics of leaks in plastic films have not been investigated. Extensive data have been taken on leaks through vacuum systems. Table 4 is derived in part from a paper by Nerken in Ref. 2. Data are provided on hydrogen, helium, air, and Freon 12, since any of these gases may be used either in testing for leaks or as lifting gases for flight.

Table 5 indicates the per cent gas loss per day for various balloon sizes as a function of leak rate. Table 6 provides estimates of leak rate as a function of hole size and superpressure.

Using Tables 5 and 6, we can combine to estimate the percentage leak rate at several altitudes for various hole sizes (Table 7).

The most common hole size produced in handling, packing, and shipping balloons was approximately  $10^{-4}$  m (4 mils) in diameter. These holes were easily discovered with relatively crude testing techniques. In Section IX a complete description is given of presently used testing techniques and their sensitivity for detecting pinholes.

Table 4

RELATIVE LEAKAGE RATES OF GASES FOR THREE TYPES OF LEAKS

	Viscosity	Molecular	Flow rate re	lative to air		
Gas	at $25^{\circ}$ C (air = 1)	weight (air = 1)	Leak: very large	1arge	small	
	(all - 1)	(all - 1)	Flow: turbulent	viscous	molecular	
Hydrogen	0.48	0.070	3.9	2.7	3.6	
Helium	1.08	0.139	2.7	1.4	2.7	
Air	1.00	1.00	1.00	1.00	1.00	
Freon 12	0.67	4.20	0.49	0.97	0.62	

Table 5

PERCENTAGE GAS LOSS PER DAY FOR TYPICAL BALLOON SIZES (500-mb, 200-mb, and 30-mb balloons)

Gas	flow	Perce	ntage gas loss per	day					
m <sup>3</sup> /day	cc/sec	Balloon Diameter							
		500 mb 1.5 m	200 mb 2 m	30 mb 6.7 m					
10-4	10 <sup>-3</sup>	0.005%	0.0025%	6 × 10 <sup>-5</sup> %					
10 <sup>-3</sup>	10 <sup>-2</sup>	0.05	0.025	6 × 10 <sup>-4</sup>					
10 <sup>-2</sup>	10-1	0.5	0.25	6 × 10 <sup>-3</sup>					
10-1	1	5	2.5	6 × 10 <sup>-2</sup>					
1	10	50	25	0.6					
10	100			6 .					
100	1000		60						

Table 6
ESTIMATED LEAKAGE RATE AS A FUNCTION OF HOLE SIZE

				Gas fl	ow m³/day			
Leak	Hole size	Δρ =	30 mb	Δρ =	10 mb	$\Delta \rho = 5 \text{ mb}$		
	, 1.	Air	Helium	Air	Helium	Air	Helium	
Very small	10 <sup>-5</sup> m (0.4 mil)	3 × 10 <sup>-4</sup>	4 × 10 <sup>-4</sup>	10 <sup>-4</sup>	1.5 × 10 <sup>-4</sup>	5 × 10 <sup>-5</sup>	8 × 10 <sup>-5</sup>	
Pinhole	10 <sup>-4</sup> m (4 mils)	3 × 10 <sup>-2</sup>	4 × 10 <sup>-2</sup>	10 <sup>-2</sup>	1.5 × 10 <sup>-3</sup>	5 × 10 <sup>-3</sup>	8 × 10 <sup>-3</sup>	
Large	10 <sup>-3</sup> m (1 mm)	2	5	1	3	0.7	2	
Enormous	10 <sup>-2</sup> m (1 cm)	175	500	100	270	70	200	

Table 7

ESTIMATED GAS LOSS PER DAY FOR TYPICAL BALLOONS FOR VARIOUS HOLE SIZES

		Gas los	s/day % p	er hole <sup>a</sup>	Expected life for one hole a			
Leak	Hole size	500 mb 1.5 m	200 mb 2 m	30 mb 6.7 m	500 mb 1.5 m	200 mb 2 m	30 mb 6.7 m	
Very small	10 <sup>-5</sup> m (0.4 mil)	0.05%	0.01%	0.00005%	200	1000 days	200,000 days <sup>b</sup>	
Pinhole	10 <sup>-4</sup> m (4 mils)	5	1	0.005	2	10	2,000	
Large	10 <sup>-3</sup> m (1 mm)	<del>-</del> .	120	1.2	-	1	8	
Enormous	10 <sup>-2</sup> m (1 cm)	<del>-</del>	, <b>-</b>	120	-	1	1	

<sup>&</sup>lt;sup>a</sup> Assume 75-mb overpressure for the 500-mb balloon, 30-mb overpressure for the 200-mb balloon, and 5-mb overpressure for the 30-mb balloon.

b Diffusion will limit life to 30,000 days.

#### V. THE RADIATION ENVIRONMENT

#### A. INFRARED RADIATION

We can consider the balloon and its payload in equilibrium with the radiation environment, in order to make a first estimate of temperature of the balloon skin or payload. The actual temperature will lie between the computed radiation temperature and the air temperature. At higher altitudes (above 20 km) and for large objects, the effects of air conduction and convection can be neglected.

We can estimate the radiation environment using the following simplified assumptions:

- 1) Downward radiation
  - a) Clouds above
    - •Downward flux equals blackbody radiation from a source whose temperature is the cloud base temperature (Table 8).
  - b) Clear above
    - ●Balloon above 15 km -- 10 w/m²
    - ●Balloon between 10-15 km -- 20 w/m<sup>2</sup>
    - •Balloon below 10 km -- 40 w/m<sup>2</sup>
- 2) Upward radiation
  - a) Clouds below
    - •Upward flux equals blackbody radiation from a source whose temperature is the cloud top temperature (Table 8).
  - b) Clear below
    - •The upward radiation will vary from 150 w/m² to 450 w/m² depending on altitude and air mass. Table 9 provides estimates of upward flux for several altitudes and air masses.
- 3) Radiation from the sides
  - The radiation from the sides can be estimated as equal to blackbody radiation from a source whose temperature is the air temperature at balloon altitude (Table 8).

Table 8

RADIATION FROM A BLACK BODY AS A FUNCTION OF TEMPERATURE

Temperature (°C)	Radiation flux (w/m²)	Temperature (°C)	Radiation flux (w/m²)
200	2846	50	619
195	2728	45	582
190	2613	40	546
185	2502	35	512
180	2395	30	480
175	2291	25	449
170	2190	20	419
165	2093	15	391
160	1999	10	365
155	1908	5	340
150	1821	0	316
145	1736	-5	294
140	1655	-10	272
135	1576	-15	252
130	1500	-20	233
125	1427	-25	215
120	1357	-30	198
115	1289	<b>-</b> 35	183
110	1224	-40	168
105	1161	<b>-</b> 45	154
100	1101	-50	141
95	1043	-55	129
90	988	-60	117
85	934	-65	107
80	883	<b>-</b> 70	97
75	834	-75	88
70	787	-80	79
65	742	<b>-</b> 85	71
60	700	-90	64
55	658		

#### B. SOLAR RADIATION

Direct solar radiation at very high levels is  $1400 \text{ w/m}^2$ . At 100 mb direct radiation is about  $1200 \text{ w/m}^2$ . At 700 mb a figure of  $1000 \text{ w/m}^2$  may be used. If there are clouds below the balloon, the indirect radiation reflected from the clouds may be as high as  $800 \text{ w/m}^2$  directed upward.

At altitudes of 12 km and above, cirrus clouds rarely produce more than 10% reduction in incoming solar radiation.

#### C. TEMPERATURE CONTROL OF BALLOONS

Nighttime radiation temperature for a spherical balloon may be calculated from the following equation:

$$[\alpha_i + (1 - \alpha_i)\alpha_i](\Phi_D \pi r^2 + \Phi_U \pi r^2 + 2 \Phi_S \pi r^2) = \alpha_i 4\pi r^2 \Phi_r$$

where  $\alpha_i$  is the absorptivity of the film in the infrared,  $\Phi_D$ ,  $\Phi_U$ ,  $\Phi_S$ , and  $\Phi_r$  are the down, up, side, and reradiated flux, respectively.

For films which are highly absorptive in the infrared, this equation simplifies to:

$$(\Phi_{D} + \Phi_{U} + 2\Phi_{S}) = 4\Phi_{r}$$

Film temperature may be computed from the reradiated flux, using Table 8.

It should be noted that the radiation temperature is independent of the absorptivity for materials which are more than 80% absorptive in the infrared.

A balloon with a reflective coating will have the same radiation temperature at night as a "black" balloon. A balloon which is relatively transparent in the infrared will have a higher radiation temperature than the black balloon, since it absorbs radiation which penetrates one side. However, the reflective balloon and the transparent balloon will each take on a temperature which is closer to the air temperature than that

of the "black" balloon, since the total energy absorbed and reradiated is much less than for the "black" balloon. A balloon with a metalized cap will operate 10 to  $15^{\circ}$ C hotter than a balloon of 100% polyester material.

The effect of the sun is to produce an increase in absorbed radiation and an increase in film temperature. The added flux absorbed from sunlight for a "transparent" balloon is:

$$\Phi_{\text{sup}} \alpha_0 2 \pi r^2 = \Delta \Phi_r 4 \pi r^2$$

or

$$\Delta \Phi_{\rm r} = \frac{\alpha_{\rm o}}{2} \Phi_{\rm sun}$$

where  $\Delta\Phi_{\rm r}$  is the added flux reradiated, and  $\alpha_{\rm O}$  is the absorptivity in the visible spectrum.

For a polyester balloon ( $\alpha_0$  = 0.05), the added flux is 0.025 $\Phi_{\rm sun}$ . This added flux varies from a minimum of 25 w/m² for a low-altitude balloon above a water surface, to 45 w/m² for a high-altitude balloon above a continuous cloud deck. For a polyester balloon ( $\alpha_1$  = 0.85), the temperature increase required to radiate 1 w/m² of flux at -50°C is 0.4°C; the temperature increase required to radiate 1 w/m² at 0°C is 0.25°C. Maximum solar heating on a high-altitude balloon (30 mb) will be 20°C, and a typical increase will be 12°C. At the lower altitudes, an average temperature increase due to solar radiation will be 8 to  $10^{\circ}$ C.

Table 9 indicates the radiation environment for several altitudes and seasons.

### D. TEMPERATURE CONTROL OF ELECTRONIC SYSTEMS

Control of small electronic packages during daytime hours is a simple matter. The skin temperature of the package can be controlled within narrow limits by use of controlled surface blackness. It can be

Table 9

RADIATION ENVIRONMENT FOR SUPERPRESSURE BALLOON

Altitude	Season	Air	Average nighttime clear sky		Mylar balloon ( $\alpha_0 = 0.05$ )		
		Temperature °C		Metalized top balloon, °C	Temperature in- crease per w/m <sup>2</sup> increment, <sup>O</sup> C	Maximum added solar flux w/m <sup>2</sup>	Maximum daytime temperature increase, °C
3 km (700 mb)	Temperate,	-10	0	+5	0.24	35	8
	Temperate,	5	-3	+2	0.21	35	8
	Tropic	10	-5	0	0.20	35	8
6 km (500 mb)	Temperate, winter	-30	0	+8	0.30	35	10
	Temperate,	-15	-5	+5	0.27	35	9
	Tropic	-5	-10	+2	0.25	35	9
9 km (300 mb)	Temperate, winter	-50	+5	+15	0.36	40	14
	Temperate,	-35	-5	+7	0.34	40	13
	Tropic	-30	-10	+2	0.34	40	13
12 km (200 mb)	Temperate, Winter	-55	+10	+20	0.36	45	16
	Temperate,	-55	+10	+20	0.36	45	16
	Tropic	-50	+5	+15	0.36	45	16
16 km (100 mb)	Temperate,	-60	+5		0.42	45	19
	Temperate,	-65	+10		0.42	45	19
	Tropic	-80	+15		0.47	45	21
24 km (30 mb)	Temperate,	-55	-5		0.45	45	20
	Temperate,	-55	-5		0.45	45	20
	Tropic	-55	-5		0.45	45	20

assumed that the nighttime skin temperature will equal the air temperature, with an error which will seldom exceed  $10^{\circ}$  C. The largest deviation from this assumption occurs in the altitude range from 12 to 18 km where the nighttime temperature of the package will be 5 to  $10^{\circ}$  warmer than the air temperature.

If it is desired to maintain warm temperatures at night, the electronic package must contain the following:

- a) An insulated container which restricts heat loss to a few watts across the temperature gradient to the cold environment.
- b) A thermal mass of sufficient capacity to maintain a reasonable temperature within the container during the entire night. Water provides the best thermal mass if the system is heated sufficiently to melt all ice during daytime hours. One kilogram of water provides 93 w-hr of heating capacity through heat of fusion.
- c) A combination of skin temperature control and external heating, introduced to the package during daytime hours, which is sufficient to balance the heat loss during the night.

It is possible to produce higher skin temperatures than are realized with a black body, by use of a silver sulfide coating on the package. This coating has an absorption of 80% or better in the visible but it emits at less than 30% efficiency in the infrared. A blackbody surface perpendicular to the sun will reach a temperature of  $100^{\circ}$ C. The silver sulfide surface, because of its poor emissivity, will reach a radiation temperature of  $140^{\circ}$ C. The insulation used within the container must be capable of withstanding these temperatures without deterioration. Polyurethane foam, which can withstand temperatures up to  $200^{\circ}$ C without deterioration, is one of the most suitable insulating materials for use in maintaining nighttime temperatures.

It must be emphasized that any means of maintaining warmer temperatures at night requires a thermal mass and, consequently, a substantial amount of material. Such a mass might introduce hazards to aircraft. The ultimate goal in the development of electronic systems and power

sources must be a system which will operate at ambient air temperature at whatever level the balloon flies. With such systems the problem in daytime temperature control will be to minimize the solar effect so that the system will maintain a constant temperature day and night. The use of paints which are reflective in the visible, and black in the infrared, permits such temperature control without any difficulty.

#### VI. BALLOON STABILITY

# A. DIURNAL CHANGES IN ALTITUDE DUE TO SUPERTEMPERATURE

Equations 18 through 27 (Appendix A) derive the relationship of altitude changes to volume changes. For a polyester sphere, 1% change in supertemperature will produce a change of 0.15% in volume. Any change in volume will produce an identical change in density at which the balloon floats. A 1% change in altitude equals approximately 0.3T m in altitude, where T is temperature in  ${}^{\circ}K$ .

The altitude variation due to supertemperature change on a spherical balloon can be approximated as:

$$\Delta Z = 4.5\Delta(\Delta T)$$

As a simple approximation, we can state that  $\underline{a} \ 1^{\circ} \underline{C}$  change in supertemperature will produce a 4.5-m change in altitude for a typical spherical balloon.

Variation in temperature during the day may be as much or greater for a Mylar balloon as the day-night effect. Maximum differences observed have been  $6^{\circ}$  C, but data are too limited to allow us to set realistic limits. For balloon design, a  $10^{\circ}$  C ( $\pm 5^{\circ}$  C) variation is assumed in supertemperature due to changes in the infrared environment.

Diurnal changes in altitude due to supertemperature may be summarized as:

- a) A predictable day-night altitude change of 30 to 40 m.
- b) An "unpredictable" variation in the radiation environment on the order of  $\pm 20~\text{m}$ .

# B. CHANGE IN ALTITUDE DUE TO GAS LOSS

Equations 28 through 31 derive the relationship which permits a balloon to lose gas without any change in altitude. Table 10 shows the change in altitude produced by a 10% loss in gas for balloons designed to fly at several altitudes. For all practical balloon designs, the altitude change due to gas loss can be neglected.

#### C. CREEP

All plastic materials exhibit some degree of creep under stress. Creep is the permanent elongation of the plastic film when stressed. The relationship between stress and strain is defined by the modulus of elasticity, which is a function of temperature. Non-elastic creep is a function of stress and temperature as well, but also depends strongly on the prior history of the material.

Plastics exhibit markedly different characteristics above and below the "glass-transition" temperature: at higher temperatures they have "plastic" characteristics; at lower temperatures they behave more like a glass. Plastics creep under stress much more than glasses. The "glass-transition" temperature for polyesters is about 350°K -- thus, the polyesters are "glassy" substances at all temperatures of importance in ballooning.

Tests have been conducted at room temperature on bilaminated Mylar strips to measure creep. Results are shown in Fig. 3. Creep will be less at the lower temperatures which balloons experience at float altitude.

Tentative results can be summarized as:

- Creep under moderate stress reduces with time, becoming negligible after two weeks. The time constant is about two days at room temperature for stresses between 5,000 and 10,000 psi. Total creep is 3.3% at 10,000 psi and 0.25% at 5,000 psi.
- •A balloon may be prestressed to minimize creep. This procedure will also relieve stresses produced in balloon manufacture.

Table 10

ALTITUDE CHANGE WITH GAS LOSS FOR TYPICAL
SUPERPRESSURE BALLOON DESIGNS

Altitude	Balloon diameter (m)	Film thickness (mils)	Altitude change for 10% gas loss (m)
6 km	1.5	3.0	+ 5
(500 mb)	1.5	2.5	-17
9 km	2.26	3.0	+13
(300 mb)	2.0	2.0	-15
12 km	2.26	2.0	+12
(200 mb)	2.0	1.5	0
16 km	3.0	1.5	+22
(100 mb)	2.5	1.0	+ 4
24 km	5.5	1.5	+15
(30 mb)	3.5	1.0	+19

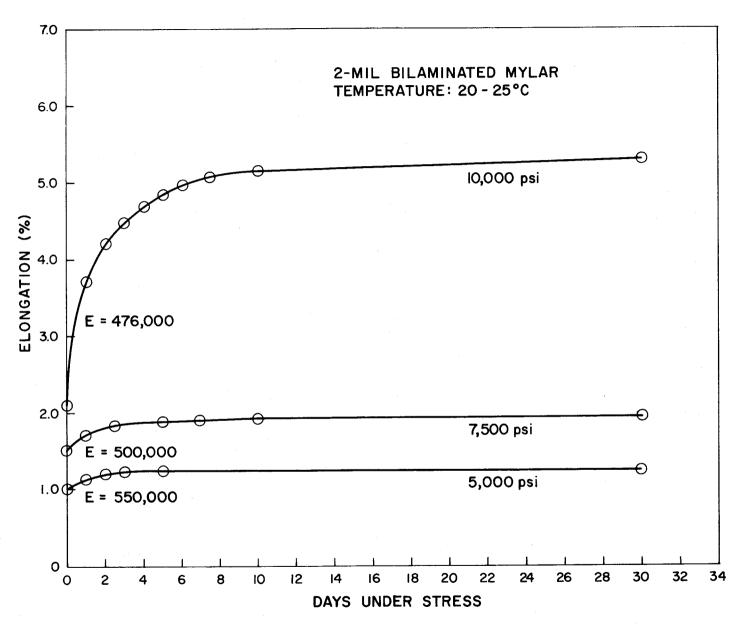


Fig. 3 Creep as a function of stress

•If a balloon is prestressed at 10,000 psi for one week at room temperature and is not stressed at float altitude beyond 7,500 psi, creep will be negligible over a period of one year.

Figure 4 shows variation in strain measured over a period of five days on a balloon floating at 500 mb. This balloon was highly stressed and showed very large creep. The time constant appears to be three days for this balloon rather than the two days observed in room temperature measurements. This apparent increase is due to the reduction of stress at night, so that only 50% of the time was the balloon stressed at the higher and more critical values above 9,000 psi.

# D. ALTITUDE VARIATION DUE TO VERTICAL CURRENTS

The altitude variation for a sphere as derived in Eqs. 32 through 36 is:

$$\Delta Z = \frac{1.15 \text{ C}_{D} \text{ Tv}^{2}}{\text{r}}$$

where

 $\Delta Z$  = incremental change in altitude (m)

 $C_{\rm p}$  = drag coefficient

 $T = temperature at Z (^{\circ}K)$ 

v = vertical wind velocity (m/sec)

r = balloon radius (m)

For a prolate spheroid balloon, the equation is:

$$\Delta Z = \frac{1.15 \text{ C}_{\text{D}} \text{ Tv}^2}{a}$$

where

 $\Delta Z$  = incremental change in altitude (m)

 $C_{D} = drag coefficient$ 

 $T = temperature at Z (^{\circ}K)$ 

v = vertical wind velocity (m/sec)

a = major radius (m)

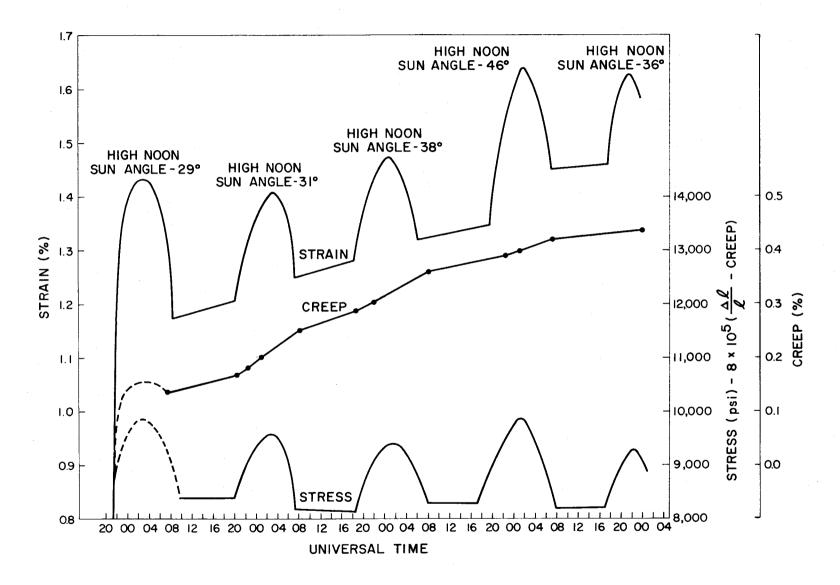


Fig. 4 Strain and stress variations on a floating balloon

Table 11 provides data on the deviation from the buoyant altitude as a function of vertical wind velocity for spheres and for a prolate spheroid with a fineness ratio of 3. The vertical excursion is negligible for vertical winds less than 0.5 m/sec for the spherical balloon, but becomes quite serious for vertical winds in excess of 1 m/sec.

At lower altitudes where convection may be severe, the balloon may move with the updrafts and downdrafts. We can make a streamlined superpressure balloon for which the response will be less than 10% of the response of an equivalent spherical balloon. The streamlined shape is recommended for all altitudes up to 700 mb. Above 700 mb the streamlined shape becomes too large and unwieldy.

# E. NATURAL OSCILLATION PERIOD OF A SUPERPRESSURE BALLOON

If a superpressure balloon is displaced from its buoyant altitude,  $Z_{\!\mbox{\tiny S}}$ , there is a restoring force which is proportional to the balloon volume and the density difference:

$$m \frac{d^{3}Z}{dt^{3}} = -Vg(\rho_{s} - \rho)$$

or

$$\frac{d^{3}Z}{dt^{2}} = -g \frac{(\rho_{s} - \rho)}{\rho}$$

$$\frac{\rho_{s} - \rho}{\rho} = \frac{\left(P \frac{\partial T}{\partial Z} - T \frac{\partial P}{\partial Z}\right) Z}{PT}$$

$$\frac{d^{2}Z}{dt^{2}} = \frac{-g\left(\frac{\partial T}{\partial Z} - \frac{T}{P} \cdot \frac{\partial P}{\partial Z}\right)Z}{T}$$

Table 11

ALTITUDE DISPLACEMENT OF SUPERPRESSURE BALLOONS
AS A FUNCTION OF VERTICAL WIND

		·			
Vertical	ΔZ (m)				
wind speed	700 mb sphere	700 mb prolate spheroid	500 mb sphere	200 mb sphere	
(m/sec)	$C_D = 0.5$ $T = 269^{\circ} K$ r = 0.75  m	$C_D = 0.05$ $T = 269^{\circ} K$ $a = 1.5 \text{ m}$ $b = 0.5 \text{ m}$	$C_D = 0.5$ $T = 252^{\circ} K$ r = 0.75 m	$C_D = 0.5$ $T = 217^{\circ} K$ r = 1.0  m	
0.1 0.5 1.0 2.0 5.0	2 m 51 m 206 m 824 m 5,150 m	0.1 m 2.5 m 10.0 m 42.0 m 260.0 m	2 m 48 m 193 m	1.3 m 31.0 m 125.0 m	

The value for T is taken from the U. S. Standard Atmosphere, 1962.

This is the familiar equation for simple harmonic motion with the period of oscillation,  $\tau$ , equal to:

$$\tau = 2\pi \sqrt{\frac{T}{g\left(\frac{\partial T}{\partial Z} - \frac{T}{P} \cdot \frac{\partial P}{\partial Z}\right)}}$$

or

$$\tau = 2 \sqrt{\frac{T}{\frac{\partial T}{\partial Z} + 3.42 \times 10^{-2}}}$$

since

$$\frac{\partial P}{\partial Z} = -3.48 \times 10^{-3} \frac{P}{T} g$$

For an isothermal region  $\left(\frac{\partial T}{\partial Z}=0\right)$ , the expression for period of oscillation simplifies to:

$$\tau = 11 \sqrt{T}$$

The natural oscillation period for a superpressure balloon in an isothermal atmosphere varies from 150 sec at  $-75^{\circ}$ C to 180 sec at  $0^{\circ}$ C. An adiabatic lapse rate  $\left(\frac{\partial T}{\partial Z} = -10^{-2} \, {}^{\circ}$ C/m $\right)$  will increase the period by approximately 15%.

# VII. SENSORS FOR USE ON SUPERPRESSURE FLIGHTS

#### A. TEMPERATURE

It has been assumed that the lack of ventilation on a superpressure balloon makes it difficult to measure temperature accurately. However, extensive tests by several investigators concerned with measurement of air temperature from rocketsondes have shown that above 40 km convection is not a significant factor in reducing radiation errors. At lower altitudes, errors can be made sufficiently small that the absence of forced convection is not critical. Thermistors developed for rocketsonde applications are directly useful for measurement from floating balloons at all altitudes of interest, with errors not exceeding  $1^{\circ}$  C.

The small metalized-bead thermistor will provide acceptable temperature measurements on a superpressure balloon to altitudes above 10 mb. Difficulties with this sensor are long-term drift effects and self-heating. The delicate lead contacts are the principal cause of long-term drift for the small bead thermistor. The small size of the bead makes it very sensitive to self-heating errors introduced from the measuring circuits. Great care must be exercised in minimizing the current flow through the bead.

We have found a 10-mil aluminized rod thermistor to be entirely satisfactory to altitudes of 30 mb. This thermistor is much less sensitive to self-heating effects and shows superior long-term stability.

The conventional ML-419 radiosonde thermistor which is 30 mils in diameter provides acceptable temperature measurements to altitudes of at least 200 mb. The lead carbonate coating on this element is black in the infrared and as a result the instrument is too sensitive to the infrared radiation environment.

The rod thermistor should be mounted vertically for superpressure balloon flight. This mounting minimizes infrared errors, since the element is "looking" at the surrounding air rather than at ground and space. This mounting is especially important for the ML-419 element. The vertical mount of the rod thermistor permits a correction (if this is considered necessary) for solar heating, since the angle of the sun can be computed at any time. With the vertical mounting a variation in apparent temperature during the day as a function of sun angle provides an accurate measurement of the total solar effect.

The most critical element in measuring temperature of a superpressure balloon is the location of the sensor. It should be located well below the balloon to prevent measurement errors caused by "chimney" currents flowing over the balloon. If the balloon is considerably colder than the atmosphere, the below-balloon mounting will introduce errors; however, this effect is important only at altitudes above 30 km where the balloon at night may be 10 or 20° colder than the air. The element should be mounted on a boom, removed from the electronic package by a distance not less than two to three times the largest package dimension. If the package is black in order to maintain daytime heating, the ML-419 element becomes unacceptable unless it can be removed completely from the influence of the package.

With care, air temperature measurements can be made to an accuracy of  $0.5^{\circ}\text{C}$  or better at all altitudes where superpressure balloons will be flown.

### B. DENSITY

The superpressure balloon floats at a constant density level. Equations 39 and 40 indicate the method of determining volume, using strain gauge measurements. Density is computed from the relationship of mass to volume. Density can be computed to an accuracy of 0.25% absolute (15 m). The variation in density can be computed to 0.1% (6 m) by monitoring the variation in strain on the balloon.

#### C. PRESSURE

$$P = k \rho T^*$$

$$T* = T + f \frac{es}{p} \times 0.38$$

At 500 mb the maximum virtual temperature difference ( $T^*$  - T) is  $0.45^{\circ}$  C. At 300 mb the maximum virtual temperature difference is  $0.06^{\circ}$  C. At higher altitudes the difference is negligible. Assuming at 500 mb or lower that humidity is estimated or measured to within 30%, humidity errors will not contribute to the pressure error. No correction is needed at higher altitudes than 500 mb.

Since density is known to 0.25% and temperature to 0.2%, the pressure is known to 0.3% accuracy (20 m).

Variations in pressure should be measurable to 0.15% (10 m).

# D. THE STRAIN GAUGE/AIR TEMPERATURE COMBINATION

### 1. Balloon Stress

$$S = E \frac{\Delta \ell_s}{\ell_D}$$

where  $\frac{\Delta \ell_{\rm B}}{\ell_{\rm O}}$  is the balloon strain. Note that the measured value,  $\frac{\Delta \ell}{\ell}$ , includes a creep factor which must be estimated.

$$\frac{\Delta l_s}{l_0} = \frac{\Delta l}{l_0} - \frac{\Delta l_c}{l_0}$$

Stress variations can be measured to 0.05% on a balloon which is no longer creeping. (Creep time constant is between two and three days.)

The absolute value of stress will not be known to better than 5% because of uncertainties in the value of E and of the absolute creep from time of original measurements of  $\ell_0$  and  $V_0$ .

# 2. Balloon Superpressure

$$\Delta P = \frac{St}{r}$$

$$\Delta P = E \frac{\Delta \ell_s}{\ell_0} \cdot \frac{t}{r}$$

The value of overpressure should be known to 5% because of uncertainties in the total amount of creep. Overpressure variations can be measured to better than 0.1%.

# 3. Balloon Supertemperature

Superpressure = free lift superpressure + supertemperature superpressure - gas loss

$$\Delta P = \frac{F}{M} P + \left(\frac{T_g - T}{T}\right) P + \frac{\Delta M_g}{M_\sigma} P$$

The absolute value of supertemperature is computed from superpressure, initial free lift and gas loss. Gas loss can be estimated on a long flight within 2%. Supertemperature can be measured to the accuracy of superpressure (5%). Since short-term variations in superpressure are entirely due to supertemperature, supertemperature variations can be measured to 0.1% or better.

This sensitivity should permit accurate estimates of the variation in the radiation environment.

#### E. WIND SHEAR

The superpressure balloon provides an ideal platform for making wind measurements. A long line may be deployed below the balloon and the wind can be measured at any point along the line. At the point which may be considered the drag center of the balloon-line system, the average wind will be zero. The balloon will be exposed to a small relative wind since it will be above this drag center. A line 3500 m long below a 300-mb balloon would permit measurement at 400 and 500 mb using

wind, temperature and pressure sensors deployed along the line. It would take a strong, weighted line, however, to probe deeply. Shorter lines can be used to measure wind shear and data can be extrapolated to lower altitudes without appreciable error, provided the balloon is flying below the tropopause. An assumption of uniform wind shear over an altitude of 3,000 m is appropriate in the altitude range of 5,000 to 10,000 m, especially in temperate latitudes during the winter season.

Table 12 indicates the level of zero wind for line lengths between 100 and 1000 m for a flight level of 400 mb, assuming a balloon with a cross section of 3 m<sup>2</sup> and a 6-1b breaking strength, monofilament nylon line with a diameter of  $2.3 \times 10^{-4}$  m. Relative wind velocity on the balloon and the bottom of the line is also indicated in terms of wind shear.

Maximum line length should not exceed 600 m because of the blow-up in line tilt at the balloon for strong shears when a longer line is used. Wind shear can be measured with a wind sensor at the line bottom or at the balloon. For a 600-m line of 6-lb strength, the shear can be measured using a formula resembling:

$$\sigma = 10^{-2} V_{h}$$

where  $\sigma$  is the shear in  $\sec^{-1}$  and  $V_b$  is the balloon velocity in m/sec. Since wind velocity at the balloon will be  $10^{-1}$  m/sec for a shear of  $10^{-3}\,\mathrm{sec}^{-1}$ , we need a low starting speed anemometer. The simplest solution is to equip the balloon with cups. The balloon will rotate at an angular rate such that the cup speed will be about one-third wind speed. We have an ideal, frictionless anemometer.


The deployment of a 600-m line from a small superpressure balloon appears to be a formidable problem. However, the balloon and its associated electronics can be launched in the normal manner while a slack string is run off a spinning reel. If winds are strong, the line tends to drop to the ground. Judicious placement of 10-gm balloons (fastened with masking tape) along the line keeps it from falling. When the end

	Table 12				
WIND	SHEAR	ON	LONG	LTNES	a

Line length, L (m)	Fractional distance from balloon to zero shear point, x	Distance from balloon to zero wind (m)	Wind on balloon (S)	Wind on bottom of line (S)
100	0.14	14	14 b	86
200	0.15	30	30	170
400	0.16	64	64	336
600	0.18	108	108	492
800	0.19	152	152	648
1000	0.20	200	200	800

 $<sup>^{\</sup>rm a}$  For a balloon of 3 m² cross section. Nylon monofilament (6-1b breaking strength) line diameter = 2.3  $\times$  10  $^{\rm -4}$  m.

 $<sup>^{</sup>b}$  S wind shear (sec<sup>-1</sup>) (S<sub>max</sub> = 2 × 10<sup>-2</sup> sec<sup>-1</sup>)

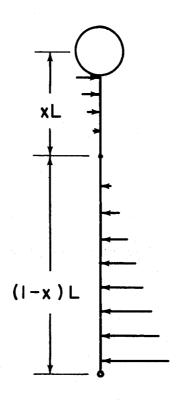

of the line with its payload is reached, the payload is released on a 30-gm balloon which has a slow leak. The payload and line move off with no danger of striking the ground. As the system ascends, the 30-gm balloon loses its lift and transfers the payload to the main balloon. The 10-gm balloons shatter during ascent.

Five long-train balloon launches have been made without difficulty from a parking lot in Boulder, Colorado, in light to moderate winds using this deployment technique. Two of the launches were with balloons equipped with cup anemometers. The longest train launched was 2500 m.

### F. TURBULENCE

The superpressure balloon does not provide, per se, a suitable platform for turbulence measurements. The balloon is moving in the air stream and does not undergo measurable accelerations for turbulence of long wavelengths. Small-scale turbulence can be measured using suitable sensors on the vehicle. For example, a black disk which was used to measure sun angle on a number of flights from Japan reached temperatures from 50 to  $100^{\circ}$ C above ambient. Small-scale turbulence produced cooling of the black disk. It was possible to correlate turbulence with the frequency and amplitude of temperature variations, but only in a qualitative manner.

The best means of measuring turbulence from the balloon platform would appear to be through measurement of wind shear over an appropriate distance, since the turbulence cells will produce a vertical wind shear which can be correlated with the vertical winds. The device can be a very sensitive indicator of turbulence for cell dimensions of the same order as the line length. The line length can be adjusted to permit measurements of clear air turbulence over the dimension range significant for aircraft operations.

# VIII. MODES OF BALLOON FAILURE

### A. LIQUID WATER ADHESION

Balloons flying below the freezing level can accumulate enough water on the balloon surface to overcome the free lift if the balloon is small and the surface untreated. An untreated balloon can retain as much as 50 gm of liquid water for each meter squared of surface area. However, balloons with a surface treatment such as Carnauba wax will retain no more than 5 gm/m $^2$  of surface. Wax treatments will undoubtedly deteriorate with time, but a chemical treatment now available will maintain the water-repelling characteristics of the balloon film surface for periods in excess of six months. With the use of surface treatments, adhesion of liquid water should not produce balloon failure.

The pressure of a continuing heavy downpour of rain can drive a spherical balloon down to the ground. A cylinder balloon is much less susceptible to this type of damage. A balloon caught in strong convection can be forced up to an altitude where it is overstressed and destroyed, or it can be forced down to the surface by a strong downdraft. The best procedure for minimizing this effect at the low altitudes is to use a shaped balloon. The improvement factor using a prolate spheroid with a fineness ratio of 3 is illustrated in Section VI, D.

# B. SUPERCOOLED WATER, ICE CRYSTALS AND FROST

Reliable superpressure balloon flight has not yet been achieved in the region from the freezing level to an altitude of approximately  $10~\rm km$ . The freezing level can vary from ground level to an altitude of  $5~\rm km$ . Below the freezing level the major hazards are violent storms and mountains. Above the freezing level and below  $10~\rm km$  clouds contain supercooled water droplets. If a supercooled droplet touches the balloon,

it freezes instantly and adheres strongly. No methods have yet been developed which will release the ice accumulations formed by the freezing of supercooled water. Mechanical motions and chemical treatments can remove layers of ice from the balloon when the ice film has integrity, but by that time the ice load is heavier than the balloon can carry. Supercooled water exists at temperatures down to  $-40^{\circ}$ . A number of investigators cite evidence of supercooled water at lower temperatures than  $-40^{\circ}$ , but their findings have not been generally accepted. Above 10 km temperatures are usually below  $-40^{\circ}$  and it appears a reasonable assumption that supercooled water does not pose a hazard.

At altitudes above 10 km it is possible for ice crystals to be attracted to the balloon film because of charge differences. A settling of sufficient ice crystals on the surface of the balloon could cause the balloon to descend and fail. The French have some evidence that this was the mode of failure for two balloons flying in the tropics at the altitude of 10 km.

At night the superpressure balloon is warmer than the air temperature at all altitudes between 10 and 20 km. Between 5 and 10 km the superpressure balloon is usually colder at night than the atmospheric temperature. On one flight in the tropics at an altitude of 5.5 km, the balloon was  $10^{\circ}$  colder at night than air temperature. This effect was so pronounced that the balloon temperature remained 1 to  $2^{\circ}$  colder than air temperature during daylight hours. It is apparent that a balloon in this environment can accumulate a frost coating at night even in the absence of clouds, provided the dew point is higher than the film temperature.

We do not yet know which of the three mechanisms (supercooled water, ice crystals, or frost) is the principal factor in reduction of balloon life between 5 and 10 km.

# C. METHODS OF MINIMIZING FAILURE

The methods to be used in reducing flight failures between 5 and 10 km should be based on understanding of the mechanism of failure.

Lacking such knowledge, we can attempt a number of solutions: if one solution succeeds, it will help to determine the failure mode.

There are three approaches to overcome the ice problem. We can fly the balloon above the icing level with a long line permitting measurement in the areas which are not safe for balloon operation. We can permit the balloon to descend to the surface or to a lower level where it may shed the ice and return to its flight level. Or we can allow rapid ascent of the balloon above the level of icing once the danger is detected, and return to flight level at a later time. The first of these solutions is described in Section VII, F. With this technique wind shear is measured over a vertical distance of several thousand feet, permitting extrapolation to even lower levels. The other two methods are described below.

# 1. The Pontoon or Yoyo Balloon

The French, in preliminary project EOLE experiments, have successfully demonstrated the pontoon technique, which consists of carrying a float 100 m or more below the balloon. When the balloon ices up, it descends to the ocean surface. The pontoon has sufficient mass so that its buoyancy as it skims the water overcomes the icing load. When the ice breaks loose or melts from the balloon surface, the balloon and its pontoon will ascend again to the design float altitude.

There are two disadvantages to this scheme. It is usable only over ocean areas (in the southern hemisphere this is scarcely a disadvantage), and the balloon will probably ascend again into the same critical environment and be forced down again. A successful pontoon system must be very rugged to overcome the stresses of these repeated returns to the ocean surface. A modification of this method which will be tested on future EOLE experiments is the replacement of the pontoon with a small superpressure balloon which becomes overpressured at a very low altitude. It is hoped this system will permit the descent of the balloon to an altitude below the freezing level where it will regain its lift after shedding ice and return to design altitude. If this method performs successfully it will permit recovery over land areas and will minimize stressing of the balloon system.

# 2. The Cannibal-loon

An alternative to attempting to recover at lower altitude is a balloon system which will rapidly ascend above the icing level whenever icing danger is sensed. Release of ballast from a superpressure balloon will not permit the balloon to ascend unless lift gas is valved from the Such a solution could be used only once and there would be no way of returning the balloon to its design altitude. However, it is possible to fly a two-balloon system in which the helium-filled balloon is zero-pressure and always has an excess of volume, and the control balloon is a superpressure balloon filled with air. This air balloon can be considered an "anchor" which holds the helium balloon to a fixed altitude. If air is vented from the anchor balloon, the balloon system rises and the superpressure remains constant. If air is forced into the anchor balloon the overpressure does not increase but the balloon descends to a lower altitude. It is thus possible to control such an anchor balloon system to float at any altitude, to ascend rapidly, and to return to its design altitude, provided there is some means of pumping air back into the anchor balloon.

There are two disadvantages to this balloon system. The total surface area is larger than for a single balloon, thus increasing the area on which ice may form; and the balloon system when uncontrolled floats at a higher altitude during daytime hours than at night, since the supertemperature of the helium balloon during daytime provides additional lift which can only be overcome by moving the anchor balloon to a higher altitude where its apparent weight increases.

Both defects can be overcome by swallowing the helium balloon within the superpressure anchor balloon -- thus the name "cannibal-loon."

Since the system volume is constant, the cannibal-loon will float at a constant density altitude at all times in the absence of venting or pumping. This system has a number of other advantages:

•The balloon can be launched fully inflated, permitting test prior to launch in inflated condition. Launch can be made in high winds without balloon damage. Brittle materials such as metals and glass can be used.

- The helium membrane is not overpressured and pinholes will not cause gas loss. The membrane can be made of material with low permeability for helium regardless of material strength.
- The outer film may have leaks without affecting performance.
  (A leak causes the balloon to go up.)
- With the use of an air pump the balloon can be lowered to any desired altitude. When pumping stops, it will fly at a constant density surface.
- With the use of a valve the balloon can be raised quickly to any desired altitude. When icing is sensed, the balloon can quickly rise to a higher altitude out of the icing environment. It can be pumped down during daylight hours to its assigned altitude after it has moved out of the icing area.

The manner of operation of the cannibal-loon is as follows:

- a) The balloon is launched fully inflated with a valve open, permitting air to be exhausted as the balloon ascends.
- b) The valve is closed by a pressure switch when the balloon reaches its design altitude.
- c) When danger is indicated by a 100% humidity detection, the valve is reopened and the balloon ascends until it is out of the danger area.
- d) During daylight hours a simple air pump is operated, forcing the balloon back to its design altitude. This air pump is operated at all times when the ice sensor indicates "no danger," as long as the balloon remains above its design altitude.

A simple air pump has been designed, consisting of a rigid rotating chamber with half its surface black. One-way valves bring air into the chamber and force air into the balloon. Rotation is most easily obtained by slowly turning the entire balloon system. Tests are underway on designs which will not be a hazard to aircraft. The pump will take up to two days to return the balloon to a 400-mb level if it has escaped to 200 mb. This delay is not a disadvantage, since it is better to delay return until the balloon has moved far from the danger area. This procedure will permit a much more rapid and efficient deployment

of balloons around the hemisphere from a single launch site than can be achieved if balloons are always flying at the design level where wind speeds may be lower.

This technique can provide a programmed radiosonde-type reading during ascent and an accumulation of long-term average data over the entire altitude range during the slow descent, provided that communications and location are controlled from a geostationary satellite.

A metalized cap on a polyester balloon will increase the nighttime temperature by 10 to  $15^{\circ}$  K if skies are clear above. If a principal failure mechanism is the collection of frost when the film temperature drops below the dew point on a clear night, the metalized cap covering one-third of the film area may provide the necessary margin of safety to prevent frost accumulation.

#### IX. BALLOON TESTING TECHNIQUES

There are two basic kinds of tests for balloons: integrity tests which determine whether the balloon is a tight vehicle or not, and leak detection tests in which the objective is to determine the specific location of leaks so that they may be repaired.

#### A. INTEGRITY TESTS

Integrity tests can only be justified if a majority of the balloons which are tested successfully pass the test. If most balloons fail the test, it is essential that leakage tests be made to determine the specific location of leaks. If most of the balloons do have leaks, it would appear appropriate to run a leak detection test prior to an integrity test. A major advantage of the integrity test is the assurance, if a balloon passes, that no leaks above a threshold level exist in the balloon. There is always the chance in a leak detection test that a leak may be overlooked.

Three types of integrity tests have been used to date:

#### 1. Helium Lift Tests

This test procedure is useful only for small balloons and requires one to two days. The balloon is inflated with helium in a cold room so that it is slightly underpressure. The lift of the balloon is then measured. Measurements are repeatable to an accuracy of 0.1 gm for 2000 gm lift, if there is no air motion in the room and if the wall temperature and air temperature are in equilibrium. The balloon is then moved to a warm room where it overpressures. The balloon loses gas through diffusion and through pinhole leaks. After not less than one day, the balloon is returned to the cold room and the lift measured again. During this period gas diffusion can be as high as 0.25% but

this diffusion should be known within 0.02%. If a number of identical balloons are tested, diffusion corrections can be made to as close as 0.01%. The loss of gas in excess of diffusion is assigned to leakage. With proper procedures leakage can be measured to 0.02%, provided the cold room is a stable environment.

The advantage of this test method is that the balloon can be flown without deflation and reinflation, simply by removing the excess helium. The disadvantages are that full helium inflation is difficult with balloons larger than 2 m diameter, and that it is expensive to provide a stable, cold-room environment for large balloons.

### 2. Overpressure Test

This test procedure requires at least one week to provide leakage measurements better than 0.1%, because of balloon creep and the difficulty of making exact measurement of volume change. The procedure is to measure atmospheric pressure, air temperature, balloon overpressure and balloon volume. Fractional loss of gas due to leakage can be computed by adding fractional loss of pressure, fractional loss of overpressure, fractional loss in volume and fractional gain in temperature. The advantage of this test procedure is that monitoring is simple (a single measurement each day suffices) and, if air is used as the inflation gas, diffusion can be neglected. The disadvantage is the marginal accuracy of the technique which requires a long time period and a high space utilization. To minimize large changes in overpressure the test should be made in a room in which temperature is well controlled, since the balloon exhibits hysteresis effects in change of volume with change of stress.

### 3. Tent Test

The tent test consists of inflating a balloon with air and Freon to a large overpressure. The balloon is placed for not less than twenty-four hours under a plastic tent. If the balloon has leaks, Freon will accumulate in the tent and can be readily detected by a halogen detector. If properly conducted, the tent test is probably more sensitive than the other two integrity tests. However, the test

is not quantitative and it is difficult to use the results to compare relative integrity of balloons.

### B. LEAKAGE TESTS

Leakage tests are much more burdensome than integrity tests but they may be conducted more quickly.

# 1. Visual, Hand and Ear Inspection

If overpressure in the balloon exceeds 10 mb, leaks from holes 1 mm (40 mils) in diameter or larger are easily detected visually or by the sound of escaping gas. If the hole cannot be seen, its exact location can usually be discovered by running the wrist across the suspected area.

# 2. Ammonia-Wet Cloth Method

With this technique ammonia is introduced into the balloon together with air, and the balloon is overpressured. A cloth which has been soaked in phenolphthalein solution is placed over the balloon. Leaks produce reddish spots on the cloth where the ammonia reacts with the phenolphthalein solution. The sensitivity of this technique is not known.

#### 3. Freon Detection

Freon is introduced into the balloon together with air, and the balloon is overpressured. A standard halogen detector is used, with a funnel over the detector to increase the inspection area. Holes 0.1 mm (4 mils) in diameter are readily detected. With careful technique in a clean room, 1-mil holes can be detected. The major disadvantage with this technique is the time required -- about ten minutes inspection time per square meter of surface.

#### 4. Helium Detection

The balloon can be completely filled with helium or, if it is a large balloon, filled with a helium-air mixture and leaks detected with a device sensitive to helium. The mass spectrometer is not suitable

for this application since it is too sensitive and will respond to diffusion of helium through the walls of the balloon. Also, a major leak will saturate this system and requires extensive purging before work can be continued.

A helium detector now on the market operates on the principle of thermal conductivity. This device balances background air against sample air and can be used in an atmosphere which has a high helium concentration. It appears a most promising method, with about the same sensitivity as the halogen detector; however, the concentration of helium in the balloon can be raised to at least ten times the level that is economical for Freon concentration. This technique should permit the conductivity device to out-perform the halogen detector.

#### 5. Bubble Detection

This technique has been used very successfully on the French EOLE project. A plastic wading pool is filled with water and detergent is added. The balloon is floated in the pool and visual inspection detects bubbles in the area which is underwater. This technique detects larger holes very quickly -- only one or two minutes are required for careful inspection per square meter of area. It should be capable of detecting holes of 0.1 mm (4 mils) diameter when some care is used.

### C. FACTORY TESTING

At present it is essential that balloons be tested in the field prior to launch because of damage which may occur in packing and shipping, or because of the inability of the manufacturer to make valid integrity tests in an economical fashion. Larger balloons pose very difficult problems for field testing, because of the difficulty of handling, and because large enough facilities for conducting tests are seldom available.

There appears to be no inherent reason that balloons can not be packed, shipped and handled without damage. For any large-scale operational program, field testing is impossible. It is essential that techniques be developed at the factory to insure that the balloon as

delivered to the launch site is free of defects. A major development program is required to attain this capability. What is required is a development effort in which the manufacturer will fabricate, test, pack, ship, unpack, and retest balloons and repeat this cycle until he can give assurance that balloons as delivered are without defect. This closed cycle is necessary because of the very long delay in determining balloon integrity through flight tests. As the closed cycle continues, the manufacturer will learn to improve his testing techniques and handling and packing procedures. After the balloon is tested it may be necessary to treat it with special preservative coatings which are removed just prior to flight, or it may be necessary to develop new laminates containing one or more layers of soft plastic which will not be subject to handling damage.

# X. BALLOON MATERIALS

# A. DESIRED CHARACTERISTICS FOR BALLOON MATERIALS

The ideal balloon film would have a very large modulus of elasticity (10 million psi), and would be transparent to the entire spectrum of radiation from infrared to ultraviolet. Such a material would not need high ultimate strength since it would never be highly stressed. The material, in addition, should be easily formed so that a balloon could be manufactured out of few spherical sections. It should be readily sealed with seal strengths as high as the strength of the basic material. The material should be impermeable to helium, oxygen, nitrogen, and water vapour. In addition, it should be plastic at room temperature so that it could be readily packed without damage. At floating altitude, the material could well be glassy so that it would shatter if struck by an aircraft.

No existing material comes close to meeting these ideal specifications. However, at least one material does come sufficiently close to providing an acceptable film for fabricating superpressure balloons. This is the polyester, polyethylene terephthalate.

# B. MINIMUM SPECIFICATIONS FOR BALLOON MATERIALS

Most plastic materials fall short of the minimum specifications in one characteristic or another, so that they cannot provide a long-lived, stable vehicle. The minimum specifications to permit flight are interrelated; for example, a material that has great strength, but at the same time is highly absorbent of solar radiation, will be overstressed by the pressure buildup caused by supertemperature. A weaker film may survive if it is sufficiently transparent. The minimum specifications for a balloon material are indicated in the following sections.

### 1. Modulus of Elasticity

A balloon with an insufficient modulus of elasticity will stretch as it superpressures, if the volume increase due to stretch is sufficient to move the balloon to a higher altitude so that the stress is maintained. The balloon will continue to ascend until it bursts in the same fashion as neoprene and rubber balloons. The minimum modulus of elasticity for an acceptable balloon depends on the free lift introduced in the balloon and on the supertemperature which the balloon will realize at floating altitude. All materials with a modulus of elasticity less than 300,000 psi are unacceptable for superpressure use. This minimum modulus applies at the temperature at floating altitude. A number of film materials have too low a modulus at room temperature or at lower floating altitudes, but are acceptable at higher altitudes where the film temperature is  $-30^{\circ}\,\mathrm{C}$  or lower. A realistic minimum modulus of elasticity for a plastic film with average transparency is 500,000 psi. The higher the modulus, the more stably the balloon will fly and the less the variation in altitude will be between night and day. A balloon with a modulus of 800,000 psi will have an altitude change of 30 to 40 m between day and night. A modulus of 10 million psi would reduce the altitude change between night and day to an insignificant amount.

# 2. Strength of the Balloon Material

Modulus of elasticity is a much more important characteristic of balloon film than ultimate film strength, provided the balloon is never stressed beyond its elastic limit. A lighter material may have a lower ultimate strength than a more dense material, since a thicker film may be used. For example, a polypropylene, which is 40% less dense than polyester, can provide a stronger material for balloon design than polyester, even though its strength is somewhat lower. An acceptable film strength for superpressure design depends on flight altitude, payload weight, and density of the film. As a general rule, the film material should be capable of stresses to 10,000 psi in its elastic range, while maintaining an acceptable modulus of elasticity.

### 3. Transparency

Balloon films vary markedly in their transparency to solar and infrared radiation. The ideal material should be transparent to the entire spectrum of solar and earth radiation. Of the several plastic materials which approach this ideal, polyethylene comes closest, absorbing less than 6% of the radiation through the solar infrared band. Polyester film approaches polyethylene transparencies at solar wavelengths, but is almost black in the infrared. As a result, for a balloon made of polyester variations in internal heating due to variations in the atmospheric radiation environment are larger than those due to night and day differences.

It may be assumed that a metalized balloon would have ideal characteristics. However, the best values of reflectivity achieved with metalized balloons have been about 94% for solar radiation and 99% for infrared radiation. The infrared emmissivity of the metalized film is 1%, and so the balloon film becomes very hot when solar input is maximum. The metalized balloon, in general, is inferior in radiation characteristics to a clear balloon at higher altitudes. For lower altitude flights, a metalized balloon will provide improved characteristics over a thick-walled semitransparent balloon. Conduction then becomes the basic mechanism removing excess heat acquired by the balloon's inefficiency as an infrared emitter.

No complete theory has been worked out which will permit computation of the amount of supertemperature experienced by a balloon in flight. The effectiveness of conduction and convection in removing heat from a balloon at float altitude can only be estimated at present. The simplest procedure for obtaining these data is to conduct flight tests of instrumented balloons with measurements of air temperature and lifting gas temperature.

#### 4. Formability

The ideal film material should be readily formed into a hemisphere, or at least a large sector of a sphere, by heat or pressure in a die or mold. Most plastics can be so formed. However, the more readily they

can be formed in this fashion the poorer they usually are as a balloon material. Polyethylene terephthalate film, a polyester, which is the best of the available balloon materials, is cast in sheet form and is drawn into other forms with great difficulty. As a result, the balloons used presently for superpressure flight are made from a large number of flat gores to simulate a sphere. The sealing tapes add considerable weight and increase the chances of leaks.

The optimum characteristic for formability would be a material which can be blown into a spherical shape in the same manner as rubber balloons or glass bulbs. However, attempts to blow large glass forms have failed because of the brittleness of the material. All the plastics which have been successfully formed by blowing have been completely inadequate in strength and modulus. It is conceivable that thin-walled glass balls may be blown using helium instead of air to provide a lighter-than-air sphere. We would need then only to enclose thousands of these balls in a netting to provide our superpressure balloon system.

#### 5. Brittleness

Since superpressure balloons will be flown in the air lanes, it is essential that the balloon material either shatter or tear easily. A number of plastic materials have a sufficiently high "glass transition temperature" that they become glass-like at flight temperatures. Polyethylene terephthalate is one of these materials, with a glass transition temperature above 70°C. Although this polyester has ten times the strength of polyethylene, it has only about one-tenth the tear resistance. Since the balloon is never shocked during testing, inflation, launch, or flight there is no need for high tear resistance.

However, the glassy materials present a major problem in manufacture, packing, and unpacking. Creases in the material can cause holes. A double fold, one transverse to the other, in a glassy material provides a sharp point which can tear another section of the film or cause a pinhole at the point of intersection. To prevent such defects the balloon could be assembled at the launch site, but this is not usually feasible. Perhaps the problem will be solved by making sure that the

balloon is handled, packed, unpacked, and inflated, at high room temperatures so that the material has more plastic characteristics.

### 6. Sealability

Many plastics, such a polyethylene, can be heat-sealed using simple techniques. The seals have over 90% of the strength of the plastic material. Polyesters and polypropylene are not easily sealed to themselves and require tape seals with a thermal-setting adhesive. Tape seals are more difficult and costly, but they do provide additional strength to the balloon.

Any seal should be gas-tight and provide at least equivalent strength to the basic material.

# 7. Permeability

Most plastics serve as quite adequate gas barriers for a one-day flight. However, few existing plastic materials have low enough permeability to permit extended flight using either helium or hydrogen. It is not sufficient that the balloon film have low permeability just for helium and hydrogen. Its permeability for nitrogen, oxygen, and water vapour must also be sufficiently low that there is no appreciable transfer of air into the balloon during flight. All the materials under consideration do have much lower permeability to nitrogen and oxygen than to hydrogen and helium.

For extended flights of superpressure balloons, helium is the only acceptable filling gas. Ammonia exacts too great a weight penalty in balloon design. Hydrogen is unacceptable because of explosion hazard, both during testing and also after the balloon returns to earth at the end of its flight, when the possibility of air mixing with hydrogen, makes an even greater hazard.

The best existing plastic for helium retention is cellophane.

Saran ranks second, and polyester (polyethylene terephthalate) ranks third. Few other plastics have acceptable helium permeability characteristics at warmer temperatures. However, among plastics diffusion depends greatly upon temperature, and polyethylene and polypropylene

become acceptable at temperatures below  $-30^{\circ}$  C. As a rule of thumb, for long-duration flights the rate of diffusion through a plastic material should be less than  $10^{-6}$  m<sup>3</sup> mil/m<sup>2</sup> per day per millibar (4 ×  $10^{-11}$  std cc cm per sec per cm<sup>2</sup> per cm Hg pressure).

### XI. LOCATION TECHNIQUES

GHOST balloons and their payloads must be non-hazardous to aircraft. In addition, the need for both light weight and low cost (in a system involving thousands of balloons) indicates that the balloon payload must consist of the simplest possible electronic system. The systems flown successfully so far weigh 100 gm and cost \$100. However, the location accuracy has been an order of magnitude less than the accuracy required for an operational system.

Interrogation by satellite provides the opportunity of enhancing location accuracy without a substantial increase in balloon electronic complexity. To date, unfortunately, the emphasis in development of balloon-satellite electronics has been on reliability rather than simplicity, and all the systems under present development are too heavy, too complex, and too costly.

# A. HIGH FREQUENCY DIRECTION FINDING (HFDF)

The classical method of locating balloons has been high frequency direction finding at 3 to 15 Mc. The more sophisticated balloon systems have used two frequencies to provide optimum transmission day and night. Fixes are obtained by combining several simultaneous bearings from widely separated stations. The Federal Communications Commission has a direction-finding network which locates transmitters to an accuracy of 20 to 50 km from the middle Pacific to the eastern Atlantic. Adcock antennas provide bearings of 1° or better. However, long baselines limit accuracy with high-frequency direction finding and even a network operated by experts such as maintained by the FCC is saturated if more than ten targets are to be tracked.

#### B. SUN ELEVATION ANGLE

If the sun elevation angle is telemetered from a balloon, the balloon can be located as lying on a circle, the center point of which lies directly below the sun. If a second elevation angle is measured at a later time, a new circle can be determined. The intersection of these two circles provides a location, provided that the balloon has not moved. However, if the velocity of the balloon is not known, there is no unique position fix and position can only be estimated. If the elevation angle of the sun is monitored continuously through the day, a series of lines of position can be determined and a reasonably accurate fix obtained. The position determination is unique only if some assumption is made as to the balloon's velocity, such as constant velocity or constant acceleration. Experience obtained in more than 80 flights in the southern hemisphere indicates that position can be estimated to an accuracy between 50 and 100 km if data have been obtained on sun angle for several hours. The technique is, of course, only usable during daylight and at times when there are no clouds above the balloon. Thin cirrus clouds affect angle determination at low sun angles but do not cause serious errors in sun angle measurements at high sun elevation angles. Reference 3 provides a complete description of the technique for measuring and telemetering sun angle information.

#### C. HFDF AND SUN ELEVATION ANGLE

In a combined location system employing sun elevation angle and high-frequency direction finding, simultaneous lines of position are obtained and there is no need for a balloon velocity correction. Since the circle of position lines of the sun elevation angle is moving and changing in size, at some time during the day it is possible to get a good intersection between the high-frequency bearing and the sun elevation circle. The problem of having enough HFDF stations over a large area to provide good intersects is avoided and it is only necessary to have sufficient stations so that at least one station can obtain a bearing during the day. The advantage of this technique over the sun elevation angle alone has been demonstrated many times by cooperating

radio operators equipped with Adcock antennas who have tracked test flights of the GHOST system. The accuracy of this combined system will not exceed the accuracy of sun elevation angle alone, except where gross errors are made in the assumptions about balloon velocity. This combined technique requires much more complex equipment and a much larger number of installations to cover a hemisphere.

#### D. LORAN C

It is possible to provide a 100-kc receiver on the superpressure balloon and retransmit on a high-frequency link the Loran C signals received aboard the balloon, to provide accurate position location. The technique has been demonstrated by the U. S. Weather Bureau with radiosondes. Unfortunately, the Loran C networks cover only areas of heavy aircraft traffic and there is presently no Loran C coverage in the southern hemisphere.

#### E. OMEGA

The OMEGA very low frequency location system is, like Loran, a hyperbolic system; however, it operates in the 10 to 14 kHz range and eight stations will provide global coverage. It is theoretically possible to receive OMEGA signals on a balloon and retransmit the signals back to a ground station to obtain location of the balloon. However, since each of the stations is multiplexed, any variation in the transmission time back to the ground station will introduce serious errors. Consequently, OMEGA signals can be used with high frequency retransmission only if phase comparisons are performed at the balloon platform prior to retransmission. The signal-to-noise ratio of the received OMEGA signals is such that this appears most difficult at this time.

We do not yet know whether OMEGA will be implemented on a global basis. There are presently only four substandard stations -- Norway, Trinidad, New York, and Hawaii. They provide an adequate area for testing but the utilization of OMEGA remains in doubt until a national decision is made to implement.

#### F. SATELLITE TECHNIQUES

Satellites can be used in three ways to locate GHOST balloons. First is the use of a geostationary satellite as a simple command and communications relay, with other techniques being used to provide the balloon location. For example, the OPLE (OMEGA Position Location Equipment) now under limited development at Goddard Space Flight Center locates the balloon by transmitting the OMEGA signals back through a geostationary satellite to a ground computer which determines the balloon location. There are a number of major problems in providing absolute position for balloons using the OMEGA stations because of possible confusion in identity of the correct lane. The system does provide extremely precise relative position over short periods of time. We can conceive a system in which the balloon's absolute position is determined once a day within 50 km, using simple sun elevation angle sensors. velocity would be determined every two hours by transmitting OMEGA information back through the synchronous satellite, and absolute position could be obtained by dead reckoning until the next sun elevation angle position was obtained. The requirement for meteorology is to ascribe an accurate velocity to a rather large area, i.e., a block 300 km on a side. If this velocity is obtained by sequential absolute positions, then these positions must be known with great accuracy. However, if the velocity can be obtained in some manner independent of the absolute position, the 300 km location accuracy is sufficient for all meteorological needs concerned with the general circulation.

A second means of obtaining location via satellite is to use a low-orbiting satellite which locates the balloon by successive measurements, each of which provides a line of position. Since the satellite is moving rapidly, lines obtained one or two minutes apart will have good intersects and need only small corrections for balloon motion. The IRLS system under development at the National Aeronautics and Space Administration determines position by two successive range measurements. The EOLE system under development in France provides position by two successive measurements of doppler shift which give information on the angle between satellite and balloon. The system proposed in the National

Academy of Sciences report (Ref. 4) is similar in concept to the IRLS location method. These systems are capable of determining balloon position to an accuracy of 1 to 2 km. Velocity is determined by positions obtained on successive orbits of the satellite (every two hours).

Almost one-third of the globe is under continuous view of the geostationary satellite, giving it an inherent advantage over the loworbiting satellite. Data can be obtained from balloons in the observed area whenever desired. This coverage permits more frequent interrogation in areas of major interest; it permits verification by a second interrogation when data may be questionable; and it permits the monitoring of data which are required in a continuous fashion, such as from a balloon which is making a vertical radiosonde ascent. The difficulty with the geostationary satellite is that it is so far away that position location from the satellite is much more difficult than from a loworbiting satellite. However, there are two feasible means of obtaining direct position data from the geostationary satellite. The first is the use of an interferometer to provide accurate angle of transmission from an interrogated balloon. The angle must be resolved to 15" of arc to permit location within 2 km, which would be a tour de force at the fringes of the state of the art. Such a system would place, of course, the minimum requirement on the balloon. It would merely interrogate and telemeter its information plus a pure tone for angle determination.

The third means, which could be used with the geostationary satellite, would be determination of range between balloon and satellite. Since range determination provides a circle of position, it would be necessary to utilize two synchronous satellites within line of sight for each balloon. Five satellites would be needed to provide global coverage. The rate of range change is very low directly below the satellite. However, this region of coarse data consists of a circle of only 100 mi diameter directly below the satellite -- a negligible portion of the globe.

## APPENDIXES

List	of Symbol	ls .	• • •		• • • •		• • • •	• •	•	67
Α.	Equations	for	Balloon	n De <b>s</b> ign	and Bal	lloon P	erforma	nce	•	69
В.	Summaries Zealand			_			,			78

## SYMBOLS

A	balloon surface area, m <sup>2</sup>
A'	balloon cross section, m <sup>2</sup>
а	radius of major axis of a spheroid
b	radius of minor axís of a spheroid
C <sub>D</sub>	coefficient of drag
E	modulus of elasticity, psi
$e_s$	saturation water vapor pressure, mb
F	free lift, kg
f	free lift ratio (F/M)
f	relative humidity
g	acceleration of gravity (9.8 m/sec <sup>2</sup> )
<b>l</b>	cylinder length, m
$\ell_{0}$	original length of strain gauge
$\frac{\Delta \mathcal{L}}{\mathcal{L}}$	fractional change in length due to strain
$\frac{\Delta \ell_{\rm s}}{\ell}$	fractional change in length due to stress
∆l <sub>c</sub>	fractional change in length due to creep
M	mass of balloon, payload and lifting gas, kg
$M_{\mathbf{f}}$	mass of gas which provides free lift, kg
m	molecular weight of lifting gas
n	number of moles of gas at $Z_{\rm g}$
P	atmospheric pressure, mb
$P_{g}$	gas pressure, mb
$P_{gs}$	gas pressure at $Z_{\rm s}$ , $mb$
$P_{O}$	atmospheric pressure at $Z_0$ , mb
$P_s$	atmospheric pressure at $Z_{\rm s}$ , ${\rm mb}$
p	partial pressure of gas, mb
ΔΡ	superpressure, mb
$\Delta \mathtt{P}_{\mathbf{T}}$	superpressure due to supertemperature, mb

```
\Delta P_{\mathbf{f}}
            superpressure due to free lift, mb
 R
            gas constant
 r
            balloon radius, m
            stress, psi
 S
            atmospheric temperature, °K
 T
            temperature of enclosed gas, °K
 T_{g}
            temperature at Z_0, {}^{\circ}K
 T_0
            temperature at Z, °K
 T_s
 T^*
            virtual temperature
            thickness of balloon envelope, mils
 t
            supertemperature, OK
\Delta T
            balloon volume, m<sup>3</sup>
 V
            vertical wind velocity, m/sec
 v
\Delta V
            change in balloon volume
            altitude at which balloon becomes fully inflated, m
 Z_0
            altitude at which balloon is in static equilibrium,
 Z_{s}
            i.e., floating altitude, m
\Delta Z
            incremental change in altitude, m
            factor relating strain to volume change (\alpha = 3 for
 \alpha
            uniform sphere)
            permeability constant, (m<sup>3</sup> mil)/(m<sup>2</sup> mb day)
 δ
 \epsilon_{s}
            1 - (b/a)^2
            air density at Z_0, kg/m^3
 \rho_{\mathcal{O}}
            air density at Z_s, kg/m<sup>3</sup>
 \rho_s
            air density at \Delta Z \pm Z_s, kg/m<sup>3</sup>
            wind shear, sec-1
 σ
```

#### Conversions to MKS Units

```
1 mb = 10^3 dyne/cm<sup>2</sup> = 10^2 kg/(m/sec<sup>2</sup>)
1 psi = 69 mb
1 mi1 = 25 \times 10^{-6} m
```

#### Appendix A

#### EQUATIONS FOR BALLOON DESIGN AND BALLOON PERFORMANCE

## SUPERPRESSURE DUE TO FREE LIFT

At a density level of  $\rho_0$ , the superpressure balloon becomes completely inflated. The balloon still retains its free lift. Neglecting supertemperature and film expansion, the expression for equilbrium at this point is:

$$V\rho_{O} = M + F \tag{1}$$

At float altitude,  $\rho_{\text{s}}\,,$  where the balloon is neutrally buoyant, we have:

$$V\rho_s = M$$
 (2)

dividing Eq. (1) by Eq. (2):

$$\frac{\rho_0}{\rho_s} = 1 + \frac{F}{M} \tag{3}$$

$$f \equiv \frac{F}{M} \tag{4}$$

combining Eqs. (3) and (4):

$$\frac{\rho_0}{\rho_s} = 1 + f \tag{5}$$

Using the equation of state,  $\rho = kP/T$ , Eq. (5) can be expressed as:

$$\frac{P_0 T_s}{P_s T_0} = 1 + f \tag{6}$$

The lifting gas pressure,  $P_{\text{gs}}$ , equals the pressure at  $Z_0$  where the balloon becomes full, corrected for temperature change.

$$P_{gs} = P_0 \frac{T_s}{T_0} \tag{7}$$

substituting in Eq. (6)

$$\frac{P_{gs}}{P_s} = 1 + f \tag{8}$$

or:

$$f = \frac{P_{gs} - P_s}{P_s} = \frac{\Delta P_f}{P_s}$$
 (9)

or:

superpressure due to free lift = 
$$\Delta P_f = fP_s$$
 (10)

#### SUPERPRESSURE DUE TO SUPERTEMPERATURE

The equation of state for the enclosed gas of a constant-volume balloon floating at altitude may be expressed as:

$$P_{g}V = n R T_{g}$$
 (11)

Since there is no change in volume or mass, we can simplify:

$$P_{g} = k T_{g}$$
 (12)

and for small pressure changes due to temperature changes:

$$\frac{\Delta P_{T}}{P_{g}} = \frac{\Delta T}{T_{g}} \tag{13}$$

or:

$$\frac{\Delta P_{T}}{P_{s} + \Delta P_{f}} = \frac{\Delta T}{T_{g}}$$
 (14)

#### STRESSES ON A SPHERE PRODUCED BY SUPERPRESSURE

For a sphere the stress expressed in consistent units is:

$$S = \frac{r \Delta P}{2t}$$

If stress is expressed in psi, radius in meters, pressure in millibars, and balloon film thickness in mils, the equation becomes:

$$S = \frac{286 \text{ r } \Delta P}{t} \tag{15}$$

$$\Delta P = \Delta P_{f} + \Delta P_{T}$$
 (16)

Combining Eqs. (10) and (16):

$$S = \frac{286 \text{ r P}}{\text{t}} \left[ f + (1 + f) \frac{\Delta T}{T} \right]$$
 (17)

#### DIURNAL CHANGES IN ALTITUDE DUE TO SUPERTEMPERATURE

The volume of a superpressure balloon does not remain constant. As the internal pressure increases, the stress on the film increases; consequently, volume increases. The expression relating stress, S, to strain,  $\Delta \ell/\ell$ , is the modulus of elasticity, E:

$$E = \frac{S}{\Delta \ell / \ell}$$
 (18)

For a spherical balloon, the volume change for small changes is three times the linear change in dimension:

$$\frac{\Delta V}{V} = \frac{3\Delta \ell}{\ell} \tag{19}$$

(For a cylinder balloon, the volume change is twice the linear change.) The volume change for a spherical balloon can be expressed by combining Eqs. (18) and (19):

$$\frac{\Delta V}{V} = \frac{3 \text{ S}}{E} \tag{20}$$

Since we are concerned with changes in volume due to changes in stress rather than the total volume change from no stress, the equation can be written as:

$$\frac{\Delta(\Delta V)}{V} = \frac{3\Delta S}{E}$$
 (20a)

Using Eqs. (14) and (15) and combining them with Eq. (20a), we can derive an expression for the volume change due to change in supertemperature:

$$\frac{\Delta(\Delta V)}{V} = \frac{3}{E} \times \frac{286 \text{ r}}{t} \times \frac{\Delta(\Delta T) (P_s + \Delta P_f)}{T}$$
 (21)

If we assume a spherical balloon design which produces 10,000 psi stress at 25% superpressure, we can obtain a "ball-park" figure for the variation of volume with supertemperature changes. From Eq. (14) we learned that a 1% increase in supertemperature produces a 1% increase in superpressure. For the typical design we consider here, an increase of 1% in the superpressure produces a 400 psi increase in stress. We can express this as:

$$\Delta S \approx 400 \times 100 \frac{\Delta(\Delta P)}{P} \approx 400 \times 100 \frac{\Delta(\Delta T)}{T}$$
 (22)

substituting in Eq. (20a):

$$\frac{\Delta(\Delta V)}{V} \approx \frac{3 \times 4 \times 10^4}{E} \cdot \frac{\Delta(\Delta T)}{T}$$
 (23)

Using the value of  $8.0 \times 10^5$  psi for the modulus of elasticity of Mylar, we have:

$$\frac{\Delta(\Delta V)}{V} \approx \frac{1.2 \times 10^{5}}{8.0 \times 10^{5}} \cdot \frac{\Delta(\Delta T)}{T}$$

$$\approx 0.15 \cdot \frac{\Delta(\Delta T)}{T}$$
(24)

A change in volume will produce an identical change in the density at which the balloon floats. A 1% change in density equals approximately 0.3T m in altitude, where T is the air temperature in  ${}^{\circ}K$ .

The altitude variation due to supertemperature change on a spherical balloon can be roughly written as:

$$\Delta Z \approx 0.3T \frac{\Delta \rho}{\rho} 100 \approx 0.3T \frac{\Delta(\Delta V)}{V} 100$$

$$\approx 30T \frac{\Delta(\Delta V)}{V}$$
(25)

Using the value derived in Eq. (24):

$$\Delta Z \approx 30T \times 0.15 \frac{\Delta(\Delta T)}{T}$$
 (26)

Thus:

$$\Delta Z \approx 4.5 \ \Delta(\Delta T) \tag{27}$$

## CHANGE IN ALTITUDE DUE TO GAS LOSS

At launch a superpressure balloon is filled with sufficient gas to provide a free lift, f, in excess of the gas required for buoyant flight. The mass of this gas is:

$$M_{f} = f V \rho_{s} \frac{m}{28.9}$$
 (28)

During the life of the balloon, this excess gas diffuses. If we assume the balloon descends at the time that all free-lift gas has been lost, the change in balloon system mass is:

$$\Delta M = M_{f} \tag{29}$$

The percentage mass loss is:

$$\frac{100 \Delta M}{M} = \frac{100 \text{ f V } \rho_s \frac{m}{28.9}}{V \rho_s} = 100 \text{ f } \frac{m}{28.9}$$
(30)

For a helium-filled balloon having 10% free lift, the percentage mass loss is:

Percentage mass loss = 100 f 
$$\frac{m}{28.9}$$
 = 100 × 0.1 ×  $\frac{4}{28.9}$  = 1.4%

This 1.4% mass loss would cause the balloon to float (near the end of its useful life) at a level 1.4% lower in density than its original float level. However, the overpressure due to free lift decreases as the free-lift gas is lost. This decrease in overpressure causes a reduction in volume which tends to balance out the mass loss.

We can design the balloon so that the mass loss exactly balances the loss in free-lift superpressure. Basically, the technique requires that the volume loss caused by a percentage reduction in overpressure equals the mass loss produced by the same percentage loss in free lift. Combining Eq. (20) with Eq. (15), we get:

$$\frac{\Delta V}{V} = \frac{3S}{E} = \frac{3}{E} \cdot \frac{286 \text{ r}}{t} \Delta P = \frac{3}{S} \cdot \frac{286 \text{ r}}{t} \text{ f } P_s$$

Equation (30) established:

$$\frac{\Delta M}{M} = f \frac{m}{28.9}$$

As discussed above, we want:

$$\frac{\Delta V}{V} = \frac{\Delta M}{M}$$

Thus:

$$\frac{858 \text{ r f } P_s}{E \text{ t}} = \frac{f \text{ m}}{28.9}$$
 (31)

For a helium-filled sphere:

$$\frac{r}{t} = \frac{4 E}{28.9 \times 858 \times P_g}$$
 (31a)

Assuming  $E = 8 \times 10^5$ , then:

$$\frac{r}{t} = \frac{162}{P_s} \tag{31b}$$

Thus if the ratio of r/t is equal approximately to  $162/P_s$  for a Mylar balloon filled with helium, the gas loss during the life of the balloon will not change the altitude.

#### ALTITUDE VARIATION DUE TO VERTICAL CURRENTS

The drag of a balloon in a vertical current is:

$$Drag = \frac{1}{2} C_D A' \rho_s v^2$$
 (32)

The restoring force can be expressed as:

Restoring force = 
$$V (\rho_s - \rho_{\Lambda Z})$$
 g (33)

We can use the excellent approximation from Eq. (25), that the density-difference height,  $\Delta Z$ , above or below the buoyant density,  $\rho_s$ , is:

$$\Delta Z \approx 30 \frac{\Delta \rho}{\rho_s} T$$
 (25)

$$(\rho_s - \rho_{\Lambda Z}) \equiv \Delta \rho$$

or

$$(\rho_s - \rho_{\Delta Z}) = \frac{\Delta Z \rho_s}{30T}$$
 (34)

Substituting Eq. (34) in Eq. (33) and equating restoring force to drag, we have:

$$\frac{C_D A' \rho_s v^2}{2} = \frac{V \Delta Z \rho_s g}{30T}$$
 (35)

Solving for  $\Delta Z$ :

$$\Delta Z = \frac{15 \text{ C}_{D} \text{ T } \text{v}^{2}}{\text{g}} \cdot \frac{\text{A'}}{\text{V}}$$
 (35a)

For a sphere, this equation reduces to:

$$\Delta Z = \frac{1.15 \text{ C}_{\text{D}} \text{ T v}^2}{\text{r}}$$
 (36)

For a prolate spheroid balloon, Eq. (35a) becomes:

$$\Delta Z = \frac{1.15 \text{ C}_{\text{D}} \text{ T v}^2}{\text{a}}$$
 (37)

#### DENSITY COMPUTATIONS USING A STRAIN GAUGE

$$\rho = \frac{M}{V} \tag{38}$$

$$V \equiv V_0 + \Delta V \tag{39}$$

$$\Delta V = \alpha - \frac{\Delta \ell}{\ell_0} V_0 \tag{40}$$

 $\frac{\Delta \ell}{\ell_0}$  is the strain measurement as telemetered from the balloon. The

factor relating strain to volume change is  $\alpha$ . (For a homogeneous sphere,  $\alpha$ = 3.)

Combining Eqs. (38) and (40):

$$\rho = \frac{M}{V_0 + \alpha \frac{\Delta \ell}{\ell_0} V_0} \tag{41}$$

Since M is known to 0.1%,  $V_0$  is known to 0.1%, and  $\alpha$   $\frac{\Delta \ell}{\ell_0}$  is measured to 0.2% absolute and 0.1% relative, the density,  $\rho$ , can therefore be computed to 0.25% absolute (15 m).

The variation in density can be computed to 0.1% (6 m) since there is no change in  $V_0$ , and M (even for a leaky balloon) will not change by more than 0.03% per day.

## Appendix B

## SUMMARIES FOR BALLOON FLIGHTS

from

### CHRISTCHURCH, NEW ZEALAND

March 1966 -- March 1967

The data for 85 balloons flown from Christchurch, New Zealand, and McMurdo Station, Antarctica, during the period March 1966 -- March 1967 are summarized on the following pages. Seven of these balloons are presumed still flying on 10 June 1967.

## CODE FOR

# GHOST BALLOON FLIGHT SUMMARY SHEETS

Balloon #	nnPPt		Surface winds m/sec
Frequency	15.02f	MHz	
			Climb-out winds UT
Method of le	ak test <u>Referenced</u>		0 - 5,000 m From Cossar radarsonde
Test results	test techniques are		5,000 - 10,000  m flight closest to
	discussed in	··	10,000 m - altitude launch time.
	Section IX.		Altitude
Mfr. balloon	#		Flight duration * days
Balloon mass		gm	Flight duration ** balloon days
Balloon volu	me	m <sup>3</sup>	Number of orbits
Balloon diame	eter	m	Position last heard QLLLLL
Film thicknes	ssm	<u>ils</u>	Balloon days tracked
Electronics i In Ballast <u>ta</u>	mass Includes sensor cludes radar reflect pes and strings.	or,	Remarks:
Gross weight	less helium_	gm	* To last time of signal pick-up.
Free lift		gm	** Balloon gains one day for each
			west to east orbit.
Launch site_	172° 32'E, 43° 29	<u>9's</u>	
Launch time_		UT	nn number of flight. Flights
Ascent rate			01-02, 03-04, 09-10, 16-17,
0 - 5,000 r	mm/s	sec	19-20 were single flights
5,000 - 10	,000 m m/s	sec	with 2 transmitters.
Float altitud	de	m	PP pressure altitude in tens of
Radar_(when	n tracked by Christo	hurc	h millibars
Computed	Cossar radar)		f last digit of frequency in kHz.
Calibration o	lata		Q quadrant of globe, southern hemisphe
Sun angle	-Code period $(10^{-1} \text{ se})$	ec)	5 0 to 90° West longitude
(GHOST cali	bration chart follow	s; i	t $6 90$ to $180^{\circ}$ West longitude $7 180$ to $90^{\circ}$ East longitude
can be used	by drawing straight		$8 90 \text{ to } 0^{\circ}$ East longitude
lines between	en calibration points	s.)	LL latitude in degrees
(Sensor cut	off Occulting ang	<u>le</u>	ll longitude in degrees
from sun by	balloon)		

Balloon # 01505 V	025	03 U
Frequency 15.026	15.0	24 MHz
Method of leak te	st <u>heliu</u>	m lift
Test results less	than .0	3% per
day		
***************************************		
Mfr. balloon # Vi	ron 6	
Balloon mass	984	gm
Balloon volume		
Balloon diameter_		
Film thickness		
Electronics mass_	202	gm
Ballast	154	gm
Gross weight less	helium_	1340 gm
Free lift	134	gm
Launch site	172° 32 'E	<u>43°29's</u>
Launch time 04/03	/66	1650 UT
Ascent rate		
0 - 5,000 m	1.25	m/sec
5,000 - 10,000 m		
Float altitude		
Radar		
Computed xxx		

## Calibration data

Sun angleCode	period	$(10^{-1})$	sec)
10°	36.8		
30°	21.0		
83°	11.3		
83°	0ccu1	ting	angle

Surface windso	calm m/sec
Cloud cover scattered	altostratus
Climb-out winds	1700 UT
0 - 5,000 m 220°	13 m/sec
5,000 - 10,000 m	
10,000 m - altitude_	
Altitude 230°	25 m/sec

Flight duration 4 days

Flight duration 4 balloon days

Number of orbits 0

Position last heard 63072 (08/03/66)

Balloon days tracked 4

Remarks: V transmitter telemetered
sun angle; U the internal temperature
of the electronics package. The
thermal helmet had four 1-cm diameter holes to reduce the temperature.

Maximum electronics temperature during the flight was  $+24^{\circ}\text{C}$ ; minimum temperature was  $-2^{\circ}\text{C}$ ; average temperature was  $+10^{\circ}\text{C}$ .

Probable cause of failure: ice accretion on balloon film.

Balloon # 03505 W 04506 B	Surface winds 030 2 m/sec
Frequency 15.025 15.027 MHz	Cloud cover clear
	Climb-out winds 1900 UT
Method of leak test helium lift	0 - 5,000 m 240° 6 m/sec
Test results less than .02% per	5,000 - 10,000 m
day	10,000 m - altitude
	Altitude 240° 11 m/sec
Mfr. balloon # Viron 5	Flight duration 5+ days
Balloon mass 984 gm	Flight duration 5+ balloon days
Balloon volume 2.26 m <sup>3</sup>	Number of orbits 0
Balloon diameter 1.63 m	Position last heard 65225 (10/03/66)
Film thickness 2.5 mils	Balloon days tracked 5
Electronics mass 208 gm	
Ballast 148 gm	Remarks: Both transmitters tele-
Gross weight less helium $1340~{ m gm}$	metered sun angle. Forty-five-gram
Free lift 134 gm	corner reflector included in ballast
	Since South American stations
Launch site 172° 32'E, 43° 29'S	were not yet in operation, flight
Launch time 05/03/66 1749 UT	duration was probably longer than
Ascent rate	5 days.
0 - 5,000 m 1.25 m/sec	Probable cause of failure: ice
5,000 - 10,000 m m/sec	accretion on balloon film.
Float altitude 5550 m	
Radar	
Computed xxx	
Calibration data 03505 W	04506 В
Sun angleCode period (10 <sup>-1</sup> sec)	0
10° 41.2	10° 35.0
30° 24.6	30° 19.9
83° 13.5	86° 10.7
83 <sup>0</sup> Occulting angle	86 <sup>°</sup>

Balloon #	05507 R	Surface winds Om/sec
Frequency 15.027	MHz	Cloud cover
		Climb-out winds 1900 UT
Method of leak tes	t <u>helium lift</u>	0 - 5,000 m 220° 15 m/sec
Test results less	than .04% per	5,000 - 10,000 m
day		10,000 m - altitude
		Altitude 230° 28 m/sec
Mfr. balloon #	Viron 3	Flight duration 13 days
Balloon mass	984 gm	Flight duration 13 balloon days
Balloon volume	2.26 m <sup>3</sup>	Number of orbits 0
Balloon diameter	1.63 m	Position last heard 62768 (20/03/66)
Film thickness	2.5 mils	Balloon days tracked 13
Electronics mass	105 gm	
Ballast	251 gm	Remarks: Probable cause of failure:
Gross weight less 1	helium <u>1340</u> gm	ice accretion on balloon film.
Free lift	134 gm	
Launch site	172 <sup>0</sup> 32'E, 43 <sup>0</sup> 29'S	
Launch time 07/03/	66 1804 UT	
Ascent rate		
0 - 5,000 m	1.25 m/sec	
5,000 - 10,000 m	m/sec	<u>.</u>
Float altitude	5550 m	<u>.</u>
Radar		
Computed xxx		
Calibration data		
	period $(10^{-1} \text{ sec})$	
10°	37.8	
30°	22.4	•
83°	12.4	
83°	Occulting angle	

Balloon #	06508	K
Frequency	15.028	MHz
Method of leak tes	st <u>heli</u>	um lift
Test results less	than .0	3% per
day		
Mfr. balloon #	Viron	2
Balloon mass	984	gm
Balloon volume		
Balloon diameter_		
Film thickness		
Electronics mass_	105	gm
Ballast	251	gm
Gross weight less		
Free lift	134	gm
Launch site	172° 32 '	E, 43 <sup>0</sup> 29'S
Launch time 07/0	3/66	1808 UT
Ascent rate		
0 - 5,000 m	1.25	m/sec
5,000 - 10,000	m	m/sec
Float altitude	5550	
Radar		
Computed_XXXX		
\		

Surface winds	o m/sec
Cloud cover	
Climb-out winds	1900 UT
0 - 5,000 m 220°	O 15 m/sec
5,000 - 10,000 m	
10,000 m - altitud	de
Altitude 230	O 28 m/sec

Flight duration	19	days
Flight duration 19	balloon	days
Number of orbits	0	
Position last heard	see remark	s
Balloon days tracked	1 <u>8</u>	

Remarks: Balloon last heard 14/03/66 position 63669. On 26/03/66 balloon tracked for 20 min from Pretoria, not possible to set position.

Balloons 05507 R and 06508 K were launched 4 min apart. After 7 days the balloons were separated by 200 km. On the 8th day they moved 600 km apart.

Probable cause of failure: balloon icing.

## Calibration data

Sun angleC	ode period	$(10^{-1} \text{ sec})$
10°	39.3	
30°	23.8	
83°	13.3	
	83° Occu	lting angle

07502 G

Balloon #\_\_\_\_

Frequency	15.022	MHz
Method of leak test	helium	lift
Test results less t	han .03% po	er day
	***	
Mfr. balloon #	Schjeldah	1 3
Balloon mass	881	gm
Balloon volume	1.853	m <sup>3</sup>
Balloon diameter	1.524	<u>m</u>
Film thickness	2.5	mils
Electronics mass	104	gm
Ballast	119	gm
Gross weight less h	nelium <u>110</u> 4	4 gm
Free lift	110	gm
Launch sitel	72 <sup>°</sup> 32 <b>'</b> E, 4	3° 29 'S
Launch time 10/03	/66 000	03 UT
Ascent rate		
0 - 5,000 m	1.25	m/sec
5,000 - 10,000 m		
Float altitude		
Radar		
Computed_xxxx		
Calibration data		
Sun angleCode p	eriod (10	1 sec)
10°	36.2	
30°	20.5	
83°	11.4	
830	Occulting	anole

Surface winds		0	calm	m/	sec
Cloud cover	high	ci	irrus	· ·	
Climb-out winds	<del></del>		2300		UT
0 - 5,000 m	_		20 m/	sec	
5,000 - 10,000					
10,000 m - alt					
Altitude	270°		30 m/	sec	
			<del></del>		

Flight duration	_1	days
Flight duration 1	balloon	days
Number of orbits	0	
Position last heard		
Balloon days tracked	1	

Remarks: Balloon was launched after frontal passage. Winds were 30 m/sec at float altitude; apparently carried balloon into squall line during night.

Probable cause of failure: balloon icing.

Frequency	15.024	MHz C
		С
Method of leak test	helium lif	t
Test results less	than .02% pe	r day,
Leak in end cap s		
	-	·
Mfr. balloon #	Viron 8	F
Balloon mass	984	gm F
Balloon volume	2.26	m <sup>3</sup> N
Balloon diameter	1.63	<u>m</u> P
Film thickness		mils B
Electronics mass		gm
Ballast		gm R
Gross weight less 1		gm f
Free lift		gm a
		1
Launch site	172° 32'E, 43°	29 <b>'</b> S
Launch time 10/03	/66 0020	<u> </u>
Ascent rate		
0 - 5,000 m	1.25 m	/sec
5,000 - 10,000 m	n	/sec
Float altitude	5550	m
Radar		
Computed_xxxx		
Calibration data		
Sun angleCode	period (10 <sup>-1</sup>	sec)
10°	33.8	
30°	18.3	
83°	10.3	
83°	Occulting a	ingle

08504 F

Balloon #\_\_\_\_

Surface winds		0	cal	.m	m/	sec
Cloud cover	high	c	irru	ıs		
Climb-out winds_			2300	)		UT
0 - 5,000 m	270 <sup>0</sup>		20	m/s	ec	
5,000 - 10,000	) m					
10,000 m - ala	titude	· 				
Altitude	270°		30	m/s	ec	

Remarks: Balloon was launched after frontal passage. Winds were 30 m/sec at altitude; apparently carried balloon into squall line during night.

Probable cause of failure: balloon icing.

Balloon # 09505 H 10505 N	Surface winds o calm m/sec
Frequency 15.025 15.025 MHz	Cloud coverclear
	Climb-out winds 1700 UT
Method of leak test helium lift	0 - 5,000 m 210° 10 m/sec
Test results less than .1% per day	5,000 - 10,000 m
	10,000 m - altitude
	Altitude 216° 13.75 m/sec
Mfr. balloon # Schjeldahl 19	Flight duration 13 days
Balloon mass 869 gm	Flight duration 13 balloon days
Balloon volume 1.853 m <sup>3</sup>	Number of orbits 0
Balloon diameter 1.524 m	Position last heard 63055 (25/03/66)
Film thickness 2.5 mils	Balloon days tracked 13
Electronics mass 208 gm	
Ballast 27 gm	Remarks: Both transmitted sun angle
Gross weight less helium $1104~{ m gm}$	data. Accurate radar track at alti-
Free lift 121 gm	tude shows no altitude variation for
	a period of 12 min after reaching
Launch site 172° 32'E, 43° 29'S	altitude.
Launch time 12/03/66 1805 UT	Probable cause of failure: bal-
Ascent rate	loon icing.
0 - 5,000 m 1.35 m/sec	
5,000 - 10,000 m m/sec	
Float altitude 5520 m	
Radar <u>xxxx</u>	
Computed	
Calibration data 09505 H	10505 N
Sun angleCode period $(10^{-1} \text{ sec})$	_
10° 42.2	10° 39.2
30° 25.9	30° 24.6
83° 14.2	86° 13.4
83° Occulting angle	86 <sup>o</sup>

Balloon # 11503 M 12504 A	Surface winds m/sec
Frequency 15.023 15.024 MHz	Cloud cover
	Climb-out winds 1700 UT
Method of leak test helium lift	0
Test results less than .1% per day	5,000 - 10,000 m
	10,000 m - altitude
	Altitude 073° 8.1 m/sec
Mfr. balloon # Schjeldahl 18	Flight duration 7 days
Balloon mass 877 gm	Flight duration 7 balloon days
Balloon volume 1.853 m <sup>3</sup>	Number of orbits 0
Balloon diameter 1.524 m	Position last heard 64831 (22/03/66)
Film thickness 2.5 mils	Balloon days tracked 7
Electronics mass 207 gm	
Ballast 20 gm	Remarks: Both transmitted sun angle
Gross weight less helium 1104 gm	data. Altitude variation for 25 min
Free lift 121 gm	radar track at altitude was less than
	30 m.
Launch site 172° 32'E, 43° 29'S	Probable cause of failure:
Launch time 15/03/66 1805 UT	balloon icing.
Ascent rate	
0 - 5,000 m 1.35 m/sec	
5,000 - 10,000 m m/sec	
Float altitude 5540 m	
Radar xxxx	
Computed	
Calibration data 11503 M	12504 A
Sun angleCode period $(10^{-1} \text{ sec})$	
10° 38.4	10° 41.0
30° 22.3	30° 24.3
83° 12.3	86° 13.1
83° Occulting angle	86 <sup>°</sup>

Balloon #	13518 L		Surface winds	m/sec
Frequency	15.028	MHz	Cloud cover	
			Climb-out winds 1700	UT
Method of leak	test <u>helium lif</u>	t	0 - 5,000 m 240° 3 m/sec	
Test results le	ess than .03% per	day	5,000 - 10,000 m	
			10,000 m - altitude	
		<del></del>	Altitude 070° 2 m/sec	
Mfr. balloon #_	Schjeldahl 12 g	ore	Flight duration 6	days
Balloon mass	1020	gm	Flight duration 6 balloon	days
Balloon volume_	1.853	m <sup>3</sup>	Number of orbits 0	
Balloon diamete	er 1.524	<u>m</u>	Position last heard 64363 (23/	03/66)
Film thickness_	3.0 r	mils	Balloon days tracked 6	
Electronics mas	ss104	gm		
Ballast	5	gm	Remarks: Probable cause of fa	ilure:
Gross weight le	ess helium <u>1129</u>	gm	balloon icing.	
Free lift	135	gm		
Launch site	172° 32 'E, 43° 2	29 <b>'</b> S		
Launch time 17/	<u>/03/66 1819</u>	UT		
Ascent rate				
0 - 5,000 m	1.5 m,	/sec		
5,000 - 10,00	00 mm,	/sec		
Float altitude_	5380	<u>m</u>		
Radar				
$Computed_{XXXX}$				
Calibration dat	а			
-	de period $(10^{-1} \text{ s})$	sec)		
10°	40.3	<del></del>		
30°	24.1			
83°	13.7	<del></del>		
8	3 <sup>0</sup> Occulting ar	ng1e		

Balloon #	14507	KUM
Frequency	15.027	MHz
Method of leak te Test results <u>les</u>		
Mfr. balloon #	Schjel	dah1 20
Balloon mass	876	gm
Balloon volume	1.853	m <sup>3</sup>
Balloon diameter_	1.524	m
Film thickness		
Electronics mass_	128	gm
Ballast	100	gm
Gross weight less		
Free lift	121	gm
Launch site		
Launch time 22/0	03/66	1830 UT
Ascent rate		
0 - 5,000 m	1.4	m/sec
5,000 - 10,000	m	m/sec
Float altitude	5770	m
Radar <u>xxxx</u>		
Computed		

Surface winds	0	n	n/sec
Cloud cover			
Climb-out winds		2300	UT
0 - 5,000 m_	270 <sup>0</sup>	3 m/sec	
5,000 - 10,000	0 m		
10,000 m - al	titude_		
Altitude	280 <sup>0</sup>	7 m/sec	

Remarks: V reference, K sun angle, U helium temperature, M air temperature. Believe feed-through fitting on inflation valve leaked. Ground test of equivalent feed-through subsequently showed leaks.

Maximum supertemperature  $+6^{\circ}C$  at sun angle of  $46^{\circ}$ . Minimum supertemperature  $-5^{\circ}C$  at sun angle of  $10^{\circ}$ . Clouds produced an  $8^{\circ}C$  change in supertemperature near noon, from  $+6^{\circ}C$  to  $-2^{\circ}C$ .

#### Calibration data KKK

Sun angle--Code period  $(10^{-1} \text{ sec})$   $\begin{array}{cccc}
10^{\circ} & 38.8 \\
\hline
30^{\circ} & 23.6 \\
\hline
80^{\circ} & 12.7 \\
\hline
80^{\circ} & 0cculting angle
\end{array}$ 

Balloon # 15253 D	Surface winds 090 ° 3 m/sec
Frequency 15.023 MHz	
	Climb-out winds 1700 UT
Method of leak test	0 - 5,000 m 270° 6 m/sec
Test results Raven: not tested	5,000 - 10,000 m 280° 11 m/sec
Schjeldahl: not tested	10,000 m - altitude
	Altitude 270° 17 m/sec
Raven 128	
Mfr. balloon # Schjeldahl special	Flight duration 4 days
Balloon mass R 965 S 1068 gm	Flight duration 4 balloon days
Balloon volume R 4.19 S 1.86 m <sup>3</sup>	Number of orbits0
Balloon diameter R 2.0 S 1.52 m	Position last heard 64838 (28/03/66)
Film thickness R 1.5 S 3.0 mils	
Electronics mass 105 gm	
Ballast 10 gm	Remarks: Anchor balloon flight with
Gross weight less helium 2148 gm	lower balloon providing a variable
Free lift 129 gm	ballast for the top balloon at all
	altitudes above 340 mb.
Launch site 172° 32'E, 43° 29'S	Untested top balloon probably
Launch time 24/03/66 1826 UT	had a leak since over half of similar
Ascent rate	tested balloons later showed leaks.
0 - 5,000 m 1.25 m/sec	
5,000 - 10,000 m 1.25 m/sec	
Float altitude 10,900 daytime m  Radar 9,600 nighttime	
Radar9,600 nighttime	
Computed xxxx	
Calibration data	
Sun angleCode period (10 <sup>-1</sup> sec)	
10° 38.0	
30° 22.8	
80° 12.5	
80° Occulting angle	

Occulting angle

Balloon # 16202 S 17206 U	Surface winds 020 6 m/sec
Frequency 15.022 15.026 MHz	Cloud cover broken altocumulus
	Climb-out winds UT
Method of leak test air pressure	0 - 5,000 m
Test results less than .1% per day	5,000 - 10,000 m
	10,000 m - altitude
	Altitude
Mfr. balloon # Schjeldahl 6	Flight duration days
Balloon mass 978 gm	
Balloon volume 4.44 m <sup>3</sup>	Number of orbits
Balloon diameter 2.04 m	Position last heard
Film thickness 1.5 mils	Balloon days tracked
Electronics mass 209 gm	
Ballast 42 gm	Remarks: Balloon rose to 5000 m at
Gross weight less helium $1229$ gm	1.5  m/sec, iced up, and descended at
Free lift 111 gm	1.5 m/sec. Temperature at maximum
	altitude was -8°C. S measured elec-
Launch site 172° 32'E, 43° 29'S	tronics temperature; U was sun angle.
Launch time 30/03/66 0023 UT	
Ascent rate	
0 - 5,000 m 1.5 m/sec	
5,000 - 10,000 m m/sec	
Float altitude m	
Radar	
Computed	
Calibration data	
Sun angleCode period $(10^{-1} \text{ sec})$	
Occulting angle	

	15 005	
Frequency	15.025	MHz
Method of leak tes	st_air press	sure
Test results less	s than $.1\%$ $_{ m I}$	per day
The state of the s	· · · · · · · · · · · · · · · · · · ·	
Mfr. balloon #	Schjeldah	1 8
Balloon mass	984	gm
Balloon volume	4.44	m <sup>3</sup>
Balloon diameter_		
Film thickness		
Electronics mass	109	gm
Ballast		
Gross weight less		
Free lift	112	gm
Launch site	172° 32'E, 4	3 <sup>0</sup> 29 'S
Launch time <u>31/</u> 0	03/66 2:	253 UT
Ascent rate		
0 - 5,000 m	1.4	m/sec
5,000 - 10,000 m		
Float altitude		
Radar		
Computed_xxxx		
Calibration data		
Sun angleCode	period (10	1 sec)

18185 L

Balloon #

Surface winds	060 0	7	. 1	m/sec
Cloud cover	broker	n al	tostr	atus
Climb-out winds_		23	00	UT
0 - 5,000 m	280°	12	m/sec	
5,000 - 10,000	) m 330	)°	20 m/	sec
10,000 m - alt	itude_	320	° 25	m/sec
Altitude	_		m/sec	

Flight duration 74 days

Flight duration 80 balloon days

Number of orbits 6

Position last heard 62858 (11/06/66)Balloon days tracked 51

Remarks: This balloon had an intermittent transmitter which failed several times. In one case the transmitter did not operate for a period of 13 days.

Probable cause of failure: transmitter failure.

Sun angle--Code period  $(10^{-1} \text{ sec})$   $\begin{array}{rrr}
10^{\circ} & 45.5 \\
\hline
30^{\circ} & 29.0 \\
\hline
80^{\circ} & 15.9 \\
\hline
80^{\circ} & \text{Occulting angle}
\end{array}$ 

Balloon # 19203 G 20206 V	Surface winds 020 ° 2 m/sec
Frequency 15.023 15.026 MHz	
	Climb-out winds 1700 UT
Method of leak test air pressure	0 - 5,000 m 270° 5 m/sec
Test results less than .1% per day.	5,000 - 10,000 m $250^{\circ}$ 10 m/sec
Leak near equator repaired	• 10,000 m - altitude 230° 35 m/sec
	Altitude 250° 35 m/sec
Mfr. balloon # Schjeldahl 7	Flight duration 39 days
Balloon mass 977 gm	Flight duration 42 balloon days
Balloon volume 4.44 m <sup>3</sup>	Number of orbits 3
Balloon diameter 2.04 m	Position last heard 63129 (14/05/66
Film thickness 1.5 mils	Balloon days tracked 30
Electronics mass 235 gm	
Ballast 17 gm	Remarks: Upper package was 19203 G
Gross weight less helium 1229 gm	electronics temperature.
Free lift 123 gm	
Launch site 172° 32'E, 43° 29'S	
Launch time 05/04/66 1845 UT	
Ascent rate	
0 - 5,000 m 1.5 m/sec	
5,000 - 10,000 m 1.8 m/sec	
Float altitude 11,800 m	
Radar	
Computed_xxxx_	
Calibration data VVV	
Sun angleCode period (10 <sup>-1</sup> sec)	
30° 18.8	
80° 10.4	
80° Occulting angle	

Balloon #	21207 U	Surface winds 250 ° 6 m/sec
Frequency	15.027 MHz	Cloud cover
		Climb-out winds 2300 UT
Method of leak	test <u>air pressure</u>	0 - 5,000 m 250° 18 m/sec
Test results <u>le</u>	ss_than .1%	5,000 - 10,000 m 250° 30 m/sec
		10,000 m - altitude $260^{\circ}$ 30 m/sec
		Altitude 270° 25 m/sec
	Schjeldahl 9	Flight duration 17 days
	988 gm	Flight duration 18 balloon days
Balloon volume_	4.44 m <sup>3</sup>	Number of orbits 1
Balloon diamete	r 2.04 m	Position last heard <u>56977 (24/04/66)</u>
Film thickness_	1.5 mils	Balloon days tracked 17
Electronics mas	s 130 gm	
Ballast	<u>111 gm</u>	Remarks: Sun sensor was open circuited
Gross weight le	ss helium <u>1229 gm</u>	for 2 hr immediately after launch but
Free lift	123gm	operated properly for the duration of
		the flight.
Launch site	172° 32'E, 43° 29'S	Balloon may have been damaged in
Launch time 06	/04/66 2135 UT	a rough launch.
Ascent rate		Balloon moved into the Antarctic
0 - 5,000 m	1.5 m/sec	night on 24/04/66.
5,000 - 10,00	0 m 1.8 m/sec	
Float altitude_	<u>11,800</u> m	
Radar		
${ t Computed}_{{ t XXXX}}$		
Calibration dat		
	de period $(10^{-1} \text{ sec})$	
10°	45.4	
30°	27.5	
80°	14.6	
80°	Occulting angle	

Balloon #	22203 R	<u>.</u>	
Frequency			Ηz
Method of leak tes	st <u>air pr</u>	essure	
Test results less	than .1%	, ,	
·			
Mfr. balloon #	Schjelo	lah1 10	
Balloon mass			
Balloon volume	4.44		m <sup>3</sup>
Balloon diameter_	2.04	- · · - · · · · · · · · · · · · · · · ·	m
Film thickness	1.5	mi	1s
Electronics mass_	132		gm
Ballast	125		gm
Gross weight less			
Free lift	123		gm
Launch site	172° 32 'E	1, 43 <sup>0</sup> 29	)'S
Launch time 06/	04/66	2140	UΊ
Ascent rate			
0 - 5,000 m	1.5	m/s	sec
5,000 - 10,000 :	n <u>1.</u>	8 m/s	sec
Float altitude	11,800		n
Radar			
Computed xxxx			
Calibration data			
Sun angleCode	period	(10 <sup>-1</sup> se	ec)
10°	40.9		
30°	23.6		
80°	12.2		
80°	00011	ing and	·1^

Surface wi	.nds	250	0	6	m	/sec
Cloud cove	r					
Climb-out	winds_		2	300		UT
0 - 5,00	00 m	250°	1	.8 m,	/sec	2
5,000 -	10,000	o m_2	50°	30	m/s	ec
10,000 m						
Altitude		270°				

Flight duration 8 days

Flight duration 6 balloon days

Number of orbits 0

Position last heard 54332 (14/04/66)

Balloon days tracked 6

Remarks: This balloon had an extremely rough launch in gusty winds. The antenna struck a fence after release with no apparent damage.

Probable cause of failure: balloon leak.

Balloon #	23206 F		Surface winds	calm m/sec
Frequency	15.026	MHz	Cloud cover	
			Climb-out winds	
Method of leak te	est		0 - 5,000 m 240°	10 m/sec
Test results			5,000 - 10,000 m 22	0 <sup>0</sup> 28 m/sec
	· · · · · · · · · · · · · · · · · · ·		10,000 m - altitude	210° 25 m/sec
			Altitude 220°	22 m/sec
Mfr. balloon #	Raven 127		Flight duration	51 days
Balloon mass	967	gm	Flight duration 54	balloon days
Balloon volume	4.19	m <sup>3</sup>	Number of orbits	3
Balloon diameter_	2.0	m	Position last heard 6	4048 (31/05/66)
Film thickness	1.5 n	nils	Balloon days tracked_	38
Electronics mass_	133	gm		
Ballast	60	gm	Remarks: Balloon mov	ed into Antarctic
Gross weight less	helium 1160	gm	night on 3 occasions.	
Free lift		gm	Probable cause o	f failure:
			balloon leak.	
Launch site	172° 32'E, 43° 2	<u> 9's</u>		
Launch time 10/0	04/66 1846	UT		
Ascent rate				
0 - 5,000 m	1.5 m/	/sec		
5,000 - 10,000	m <u>1.8</u> m/	sec		
Float altitude	11,800	<u>m</u>		
Radar				
${\tt Computed}_{{\tt XXXX}}$				
Calibration data				
Sun angleCode	period ( $10^{-1}$ s	ec)		
10 <sup>o</sup>	44.5			
30°	26.5			
80°	15.0			
80°	Occulting an	010		

Balloon #	24202 S		Surface winds O calm m/sec
Frequency	15.022	MHz	Cloud coverclear
			Climb-out winds 1700 UT
Method of leak tes	tair pressure		0 - 5,000 m 200° 5 m/sec
Test results less			5,000 - 10,000 m 120° 5 m/sec
			10,000 m - altitude 120° 6 m/sec
			Altitude 100° 5 m/sec
Mfr. balloon #	Schjeldahl 1	2	Flight duration 57 days
Balloon mass	978	gm	Flight duration 61 balloon days
Balloon volume	4.44	m <sup>3</sup>	Number of orbits 4
Balloon diameter_	2.04	m	Position last heard 64245 (08/06/66)
Film thickness	1.5 r	mils	Balloon days tracked 55
Electronics mass	108	gm	
Ballast	143	gm	Remarks: Balloon heard on 09/07/66 by
Gross weight less	helium 1229	gm	Lima station on 89th day, located
Free lift	123	gm	near equator.
			Probable cause of failure:
Launch site	172° 32'E, 43°	29 <b>'</b> S	transmitter failure.
Launch time 12/04	/66 1845	UT	
Ascent rate			
0 - 5,000 m	1.4 m	/sec	
5,000 - 10,000 r	n1.8 m	/sec	
Float altitude	11,800	m	
Radar			
Computed xxxx			
Calibration data			
Sun angleCode	period $(10^{-1})$	sec)	
10°	39.2		
30°	22.0		
80°	12.1		
80°	Occulting a	ng1e	

Balloon #	25209 A		Surface win
Frequency	15.029	MHz	Cloud cover
			Climb-out w
Method of leak	test air press	sure	0 - 5,000
Test results Ba	lloon showed a	gas	5,000 - 1
loss of .25% p	er day in tests	. Leak	10,000 m
discovered & r	epaired, not te	sted	Altitude_
further.			
Mfr. balloon #	Schjeldah1	11	Flight dura
Balloon mass	974	gm	Flight dura
Balloon volume	4.44	m <sup>3</sup>	Number of o
Balloon diamet	er2.04	m	Position la
Film thickness	1.5	mils	Balloon day
Electronics ma	ss129	gm	
Ballast	126	gm	Remarks: Le
Gross weight l	ess helium <u>122</u>	.9 gm	equator pri
Free lift	123	gm	Poor t
			frequency -
Launch site	172° 32'E, 4	3° 29 <b>'</b> S	Probab
Launch time 1	4/04/66 18	52 UT	balloon lea
Ascent rate			
0 - 5,000 m_	1.4	m/sec	
5,000 - 10,00	00 m 1.8	m/sec	
Float altitude	11,800	m	
Radar	_		
Computed xxxx	_		
Calibration dat	ta		

Surface winds	° cal	m m/sec
Cloud cover		
Climb-out winds	170	O UT
0 - 5,000 m 270°	3 m	/sec
5,000 - 10,000 m_	280°	5 m/sec
10,000 m - altitud	<u>a</u> 310°	12 m/sec
Altitude 310°	12	m/sec

Flight duration 30 days

Flight duration 32 balloon days

Number of orbits 2

Position last heard 63353 (14/05/66)

Balloon days tracked 22

Remarks: Leak repaired near balloon equator prior to flight.

Poor tracking due to high frequency -- close to Radio Peking.

Probable cause of failure: balloon leak

Sun angle--Code period  $(10^{-1} \text{ sec})$   $10^{\circ} 37.0$   $30^{\circ} 24.4$   $80^{\circ} 14.2$   $80^{\circ} 0\text{ occulting angle}$ 

Balloon #	26204 K	<del> </del>	Surface winds_	040 °	7	m/sec
Frequency	15.024	MHz	Cloud cover	broken	altostra	atus
			Climb-out wind			UT
Method of leak tes	t air pressu	re	0 - 5,000 m_	270°	12 m/s	sec
Test results less	than .15%		5,000 - 10,0	00 m 25	0 <sup>0</sup> 40 r	n/sec
			10,000 m - a	ltitude	250°	55 m/sec
	· · · · · · · · · · · · · · · · · · ·		Altitude	250°	50 m/s	sec
		_				
Mfr. balloon #						
Balloon mass						
Balloon volume				ts		
Balloon diameter				heard		
Film thickness		mils	Balloon days t	racked_		<del></del>
Electronics mass		gm				
Ballast	147	gm	Remarks: No s	ignals	receive	d at the
Gross weight less	helium 1229	gm	Christchurch s	tation	from the	is bal-
Free lift	123	gm	loon. It is a	ssumed	that it	iced
			up and descend	ed into	the oc	ean.
Launch site	$172^{\circ} 32'E, 43^{\circ}$	29'S				
Launch time 18/0	14/66 18	45 UT				
Ascent rate						
0 - 5,000 m		m/sec				
5,000 - 10,000 m	11	m/sec				
Float altitude		m				
Radar						
Computed						
Calibration data						
Sun angleCode	period (10 <sup>-1</sup>	sec)				
		<del></del>				
		<del></del>				
	Occulting a	ang1e				

Balloon #	27203 В	·	Surface winds 2	210 ° 2	m/sec
Frequency	15.023	MHz	Cloud cover		
			Climb-out winds	2300	UT
Method of lea	k test <u>air press</u>	ure	0 - 5,000 m 2	220° 8 m/sec	
Test results_	lost .4% per day.	Pin-		m 220° 12 m	n/sec
hole leak dis	covered 10° from	equato		tude 230° 12	m/sec
& repaired.	No further test.		Altitude2		
			•		
Mfr. balloon	#Schjeldahl	2	Flight duration_s	ee remarks	days
Balloon mass_	958	gm	Flight duration_	balloon	days
Balloon volum	e4.44		Number of orbits_		
Balloon diame	ter2.04	m	Position last hea	rd	
Film thicknes	s1.5	mils	Balloon days trac	ked3	
Electronics m	ass105	gm			
Ballast	166	gm	Remarks: This bal	loon had a de	fective
Gross weight	less helium <u>1229</u>	gm	transmitter which	made it very	diffi
Free lift	123	gm	cult to read exce	pt when the b	alloon
			was very close.	The balloon w	as
Launch site	172° 32'E, 43	°29'S	heard on 11/06/66	on its 76th	day
Launch time	26/04/66 214	3 UT	in Djakarta.		
Ascent rate					
0 - 5,000 m	1.4	m/sec			
5,000 - 10,0	000 m <u>1.8</u>	m/sec			
Float altitud	11,800	m			
Radar					
Computed <sub>XXX</sub>	<u>x</u>				
Calibration da	ata				
Sun angle	Code period (10 <sup>-1</sup>	sec)			
20°	22.5	<del></del>			
30°	15.0	·			
	80° Occulting	angle			

m/sec

Balloon #	28203 X		Surface winds 0 m/sec
Frequency	15.023	MHz	Cloud cover
			Climb-out winds 2300 UT
Method of leak te	st <u>air pres</u>	sure	0 - 5,000 m 360° 20 m/sec
Test results less	than .05%		5,000 - 10,000 m 340° 25 m/sec
		<del> </del>	10,000 m - altitude 340° 33 m/sec
			Altitude 340° 33 m/sec
Mfr. balloon #	Schjeldah1	3	Flight duration 192 days
Balloon mass	983	gm	Flight duration 208 balloon days
Balloon volume	4.44	m <sup>3</sup>	Number of orbits 16
Balloon diameter_	2.04	m	Position last heard 62344 (04/11/66)
Film thickness	1.5	mils	Balloon days tracked 206
Electronics mass_	108	gm	
Ballast	138	gm	Remarks: Probable cause of failure:
Gross weight less	helium <u>122</u>	9 gm	balloon leak.
Free lift	123	gm	
Launch site	172° 32'E, 4	3° 29 ' S	
Launch time 28/0	)4/66 18	57 UT	
Ascent rate			
0 - 5,000 m_	1.4	m/sec	
5,000 - 10,000	m_ 1.8	m/sec	
Float altitude	11,800	<u>m</u>	
Radar			
Computed xxxx			
Calibration data			
Sun angleCode	period $(10^{-1})$	sec)	
10°	44.6		
30°	27.4		
80°	14.9		
80°	Occulting	angle	

Balloon #	29204 Z		Surfa
Frequency		MHz	Cloud
:			Clim
Method of leak te	st <u>air pr</u>	essure	0 -
Test results less	than .1%	· · · · · · · · · · · · · · · · · · ·	5,0
			10
			A1
Mfr. balloon #			
Balloon mass		gm	Fligh
Balloon volume	4.44	m <sup>3</sup>	Numbe
Balloon diameter_	2.04	<u>m</u>	Posi
Film thickness	1.5	mils	Ballo
Electronics mass_	107	gm	
Ballast	145	gm	Remai
Gross weight less	helium <u>l</u>	229 gm	Proba
Free lift	148	gm	1eak
Launch site	172° 32 'E,	43 <sup>o</sup> 29 's	
Launch time 03/05	/66 1	841 UT	
Ascent rate			
0 - 5,000 m	1.5	m/sec	
5,000 - 10,000 m	m1.9	m/sec	
Float altitude	11,800	m	
Radar			
Computed xxxx			
Calibration data			
Sun angleCode	period (10	0 <sup>-1</sup> sec)	
10°	40.4		
30°	25.4		
80°	14.5		
80°	0cculti	ng angle	

Surface winds	(	calm	m/sec
Cloud cover	clear		
Climb-out winds_	2300		UT
0 - 5,000 m_	200°	4 m/s	ec
5,000 - 10,000	) m 19	0° 10	m/sec
10,000 m - alt	itude	240 <sup>0</sup>	10 m/sec
Altitude_	240°	10 m/	sec

Flight duration_		31		days
Flight duration_	33	bal	100n	days
Number of orbits_		2		
Position last hea	rd_63	3426	(03/0	06/66)
Balloon days trac		33		

### rks:

able cause of failure: balloon

Balloon #	30202 C		Surface winds	o calm m/se	<u>∍c</u>
Frequency	15.022	MHz	Cloud cover		
,			Climb-out winds		<u>JT</u>
Method of leak	test_air press	sure	$0 - 5,000 \text{ m} 300^{\circ}$		
Test results lo	st .5% per day.	Sma1	1 5,000 - 10,000 m_	270° 15 m/se	ec
hole discovered	& repaired 2 f	Et above	e 10,000 m - altitude	270° 17 m/s	sec
inflation fitti	ng. Retested -	- less	Altitude280°		_
than .1% per da	·y •				
Mfr. balloon #_	Raven 129	<u>,</u>	Flight duration	39 day	ys
Balloon mass	974	gm	Flight duration 42	balloon day	ys
Balloon volume_			Number of orbits	3	
Balloon diamete	er2.0	m	Position last heard_	** (16/06/66	<u>)</u>
Film thickness_	1.5	mils			<del></del>
Electronics mas	ss 115	gm			
Ballast	71	gm	Remarks: This balloor	was launche	d
Gross weight le		0 gm	3 min prior to 31206	D. The ball	oons
Free lift		gm	remained within 200 k	cm of each ot	her
			for the first 14 days	of flight.	
Launch site	172° 32'E, 4	3 <sup>0</sup> 29 ' S	** Last position	n with good d	ata
Launch time	08/05/66 19	33 UT	51487 on (14/06/66).		
Ascent rate			Probable cause o	of failure:	
0 - 5,000 m_	1.4	m/sec	balloon leak.		
5,000 - 10,00	00 m 1.8	m/sec			
Float altitude_	11,800	m			
Radar	_				
Computed_xxx	<u>«</u>				
Calibration dat	ta				
Sun angleCo	ode period (10 <sup>-1</sup>	l sec)			
10°	26.4				
30°	16 6				

80°

80°

9.2

Occulting angle

Balloon #	31206 D	7.4.	Surface winds	m/sec
Frequency	15.026	MHz		
			Climb-out winds	1700 UT
Method of leak te	st <u>air pr</u>	essure	0 - 5,000 m 300°	2 m/sec
Test results less	than .1%		5,000 - 10,000 m 27	$0^{\circ}$ 15 m/sec
	· · · · · · · · · · · · · · · · · · ·		10,000 m - altitude	270° 17 m/sec
			Altitude 280°	17 m/sec
Mfr. balloon #			Flight duration	17 days
Balloon mass	964	gm	Flight duration 18	balloon days
Balloon volume	4.19	m <sup>3</sup>	Number of orbits	1
Balloon diameter_	2.0	<u>m</u>	Position last heard 8	4734 (25/06/66)
Film thickness	1.5	mi1s	Balloon days tracked_	18
Electronics mass_	106	gm		
Ballast	90	gm	Remarks: See balloon	30202 C.
Gross weight less	helium 11	60 gm	Probable cause of fai	lure: balloon
Free lift	128	gm	leak.	
Launch site	172°32'E,	43°29'S		
Launch time 08/0	5/66	1936 UT		
Ascent rate				
0 - 5,000 m	1.4	m/sec		
5,000 - 10,000 r	n 1.8	m/sec		
Float altitude	11,800	m		
Radar				
Computed xxxx				
Calibration data				
Sun angleCode	period (10	) <sup>-1</sup> sec)		
10°	28.2			
30°	17.6			
80°	9.9	·		
80°	Occultir	g angle		

Occulting angle

Balloon #	32506	DWRK	
Frequency	15.026		MHz
Method of leak tes	st_heliu	n lift	
Test results less	than .0	5%	
			<del></del>
Mfr. balloon #		<u>dahl 2-</u>	<u>A</u>
Balloon mass			
Balloon volume	1.95		m <sup>3</sup>
Balloon diameter_	1.54		m
Film thickness	2.5	m	ils
Electronics mass_	132		gm
Ballast			gm
Gross weight less			gm
Free lift	363		gm
Launch site	172° 32'	E, 43°2	9'S
Launch time 12/0	5/66	2043	UT
Ascent rate			
0 - 5,000 m	2.5	m/	sec
5,000 - 10,000			
Float altitude			m
Radar <u>xxxx</u>			
Computed			
- L			
Calibration data			
Sun angleCode	period	(10 <sup>-1</sup> s	sec)
10°	43.0		

30°

86°

86°

25.5

13.7

Occulting angle

Surface winds	° calm	m/sec
Cloud cover		
Climb-out winds	1700	UT
0 - 5,000 m 250°	6 m/sec	
5,000 - 10,000 m		
10,000 m - altitud	e	
Altitude 250°	7 m/sec	

Flight duration 5 days

Flight duration 5 balloon days

Number of orbits 0

Position last heard 63539 (17/05/66)

Balloon days tracked

Remarks: This balloon was wax treated. Total mass of wax was 9 gm. This 4 coder measured sun angle, air temperature, film strain, and electronics temperature. The stress-strain data and creep information are discussed in the body of the text. Electronics temperature varied from  $+2^{\circ}$  C to  $+26^{\circ}$  C.

This balloon was heard on 17/07/66 in Djakarta.

Balloon #	33504 P	
Frequency		MHz
Method of leak te	sthelium te	st
Test results less	than .05%	· · · · · · · · · · · · · · · · · · ·
	****	
Mfr. balloon #		
Balloon mass		
Balloon volume		
Balloon diameter_		
Film thickness		mils
Electronics mass_	120	gm
Ballast	57	gm
Gross weight less	helium_ 10	67 gm
Free lift	320	gm
Launch site	172° 32'E,	43 <sup>0</sup> 29 <b>'</b> S
Launch time 16/0	5/66 20	025 UT
Ascent rate		
0 - 5,000 m	3	m/sec
5,000 - 10,000 r	n	m/sec
Float altitude	6200	m
Radar		
Computed xxxx		
Calibration data		
Sun angleCode	period (10	·1 sec)
10°	32.5	ŕ
30°	19.2	
83°	10.7	
83°	Occulting	anole

Surface winds	0	calm	m/sec
Cloud cover			
Climb-out winds		1700	UT
0 - 5,000 m 270	)°	9 m/se	ec
5,000 - 10,000 m			
10,000 m - altitu	ıde_		
Altitude 270	)°	14 m/s	sec

Flight duration  $\frac{3}{}$  days

Flight duration  $\frac{3}{}$  balloon days

Number of orbits  $\frac{0}{}$ Position last heard  $\frac{61862}{}$  (19/05/66)

Balloon days tracked  $\frac{3}{}$ 

Remarks: This balloon was wax treated and had 30% free lift. The balloon was girdled with 6 layers of glass filament tape around the equator to prevent burst.

Probable cause of failure: icing.

Balloon #	34206 J		Surface winds 210 ° 3 m/sec
Frequency	15.026	MHz	Cloud cover overcast above, clear to east
			Climb-out winds 0500 UT
Method of leak	test helium li	ift	$0 - 5,000 \text{ m}   180^{\circ}   2 \text{ m/sec}$
Test results_	less than .05%		$5,000 - 10,000 \text{ m} 290^{\circ} 5 \text{ m/sec}$
			10,000 m - altitude <u>270° 8 m/se</u> c
		M	Altitude $250^{\circ}$ 10 m/sec
Mfr. balloon #	Schjeldahl	18	Flight duration 234 days
<del></del> -	981		
Balloon volume	4.44	m <sup>3</sup>	Number of orbits 19
Balloon diamet	er2.04	m	Position last heard 74932 (13/01/67)
Film thickness	1.5	mils	Balloon days tracked 240
Electronics ma	ss <u>116</u>	gm	
Ballast	132	gm	Remarks: Last reported good trans-
Gross weight 1	ess helium 122	9 gm	mission on $13/01/67$ on $234$ th day.
Free lift	172	gm	Balloon was heard intermittently on
			24/01/67 by the Huancayo Observatory,
Launch site	172° 32'E, 43	3 <sup>o</sup> 29 ' S	Peru. Failure may have been electronic.
Launch time	25/05/66 04	<u>14 UT</u>	
Ascent rate			
0 - 5,000 m_	1.5	m/sec	
5,000 - 10,0	00 m 2.0	m/sec	
Float altitude	11,800	m	
Radar	<u></u>		
Computed xx	<u>x</u> x		
Calibration da	ta		
Sun angleC	ode period $(10^{-1})$	sec)	
10°	29.8		
30°	18.9		
80°	10.8	···	
	80° Occulting	anole	

Balloon #	35203 R	Surface winds $210^{\circ}$ 3 m/sec
Frequency	15.023 MHz	Cloud cover overcast above, clear to east
		Climb-out winds 0500 UT
Method of leak	test <u>helium lift</u>	0 - 5,000 m $180^{\circ}$ 2 m/sec
Test results les	ss than .04%	$5,000 - 10,000 \text{ m} 290^{\circ} 5 \text{ m/sec}$
		10,000 m - altitude $270^{\circ}$ 8 m/sec
		Altitude 250° 10 m/sec
Mfr. balloon #	Schjeldahl 19	Flight duration 25 days
Balloon mass	980 gm	Flight duration 27 balloon days
Balloon volume_	4.44 m <sup>3</sup>	Number of orbits 2
Balloon diameter	2.04 m	Position last heard 64650 (13/06/66)
Film thickness_	1.5 mils	Balloon days tracked9
Electronics mass	<u>g 116 gm</u>	
Ballast	133 gm	Remarks: This balloon remained at
Gross weight les		high latitudes. Balloon was heard
Free lift	172 gm	on 18/06/66 but no position obtained.
		Balloon life may have been one
	172° 32'E, 43° 29'S	month or more longer than recorded as
	25/05/66 0432 UT	it remained in the Antarctic night.
Ascent rate		
	1.5 m/sec	
5,000 - 10,000	m 2.0 m/sec	
Float altitude	11,800 m	
Radar		
Computed xxxx		
Calibration data		
	e period $(10^{-1} \text{ sec})$	
10°	36.5	
30°	20.8	
80 <sup>0</sup>	11 Д	

80°

Occulting angle

Balloon #	36204 K	
Frequency	15.024	MHz
Method of leak te	st <u>helium</u>	lift_
Test results less	than .06%	
	· · · · · · · · · · · · · · · · · · ·	·
Mfr. balloon #	Schjeldahl	1 20
Balloon mass	977	gm
Balloon volume	4.44	m <sup>3</sup>
Balloon diameter_	2.04	<u>m</u>
Film thickness	1.5	mils
Electronics mass_	123	gm
Ballast	129	gm
Gross weight less	helium 122	29 gm
Free lift	172	gm
Launch site	172° 32'E, 4	+3°29'S
Launch time 25/	05/66	0425 UT
Ascent rate		
0 - 5,000 m	1.5	m/sec
5,000 - 10,000	m 2.0	m/sec
Float altitude	11,800	m
Radar		
Computed xxxx		
	a	
Calibration data		
Sun angleCode	period (10	·1 sec)
10°	27.0	
30°	15.7	
80°	8.9	
80°	Occulting	g angle

Surface winds	210	0	3	m/se	c	
Cloud cover ove	rcast	abov	e,	clear	to	east
Climb-out winds		0.5	00	U	$_{ m IT}$	
0 - 5,000 m_	$180^{\circ}$	2	m/s	ec	_	
5,000 - 10,00	00 m	290 <sup>0</sup>	5	m/sec		
10,000 m - al					<u> </u>	
Altitude	250°				_	

Flight duration 39 days

Flight duration 7 balloon days

Number of orbits 7

Position last heard 75002 (09/06/66)

Balloon days tracked 8

Remarks: This balloon moved into the Antarctic night and was tracked intermittently. Last good data was on 09/06/66. Last data was on 02/07/66.

Balloon #	37202 W	_ Surface winds <u>040 0 5 m/sec</u>
Frequency	15.022 MH	z Cloud cover
		Climb-out winds 1700 UT
Method of leak	test <u>not tested</u>	0 - 5,000 m $270^{\circ}$ 6 m/sec
Test results		5,000 - 10,000 m 210° 17 m/sec
		10,000 m - altitude 210° 14 m/sec
		Altitude $210^{\circ}$ 11 m/sec
Mfr. balloon #_	Schjeldahl 17	Flight duration see remarks days
Balloon mass	978 g	m Flight duration <u>balloon days</u>
Balloon volume_	4.44 m	Number of orbits
Balloon diameter	r 2.04	n Position last heard
Film thickness_	1.5 mil	Balloon days tracked
Electronics mass	s <u> </u>	<u>n</u>
Ballast	145 g	n Remarks: Transmitter on this balloon
Gross weight lea	ss helium <u>1229</u> g	$\underline{ t n}$ put out less than $10\%$ normal power.
Free lift	172 g	n It was heard weakly for 3 days at
		Christchurch and then not picked
Launch site	172° 32'E, 43° 29'	s up again. The duration of flight
Launch time 26	/05/66 1900 U	$ar{arGamma}$ is not known.
Ascent rate		
0 - 5,000 m	1.5 m/se	<u>.</u> <u>2</u>
5,000 - 10,000	0 m 2.0 m/se	<u>2</u>
Float altitude_	11,800	<u>n</u>
Radar		
Computed xxxx		
Calibration data	a	
Sun angleCoo	de period $(10^{-1} \text{ sec})$	
see	remarks	_
		_
/		_
	Occulting angle	3

Balloon #	38206 U		Surface winds 040 ° 5 m/sec
Frequency	15.026	MHz	Cloud cover
	. * ·		Climb-out winds 1700 UT
Method of leak te	st not teste	ed	0 - 5,000 m 270° 6 m/sec
Test results			$5,000 - 10,000 \text{ m} 210^{\circ} 17 \text{ m/sec}$
			10,000 m - altitude 210° 14 m/sec
<del></del>			Altitude 210° 11 m/sec
Mfr. balloon #	Schjeldahl	16	Flight duration 5 days
Balloon mass	970	gm	Flight duration 5 balloon days
Balloon volume	4.44	m <sup>3</sup>	Number of orbits 0
Balloon diameter_			Position last heard 63110 (01/06/66)
Film thickness	1.5	mils	Balloon days tracked
Electronics mass_	116	gm	
Ballast	143	gm	Remarks:
Gross weight less	s helium <u> 1229</u>	gm	Probable cause of failure: balloon
Free lift	172	gm	leak (balloon was not tested).
Launch site	172° 32'E, 43	3 <sup>0</sup> 29 <b>'</b> S	
Launch time 20	<u>6/05/66                                 </u>	902 UT	
Ascent rate			
0 - 5,000 m_	1.5	m/sec	•
5,000 - 10,000	m 2.0	m/sec	
Float altitude	11,800	m	
Radar			
Computed $_{ m xxx}$			
Calibration data			
Sun angleCode	-	sec)	
10°	31.5	<del></del>	
30°	17.8		
80°	9.6		
80°	Occulting	angle	

Balloon #	39208 Н	Surface winds <sup>O</sup> calm m/sec
Frequency	15.028 MH	
		Climb-out winds 1700 UT
Method of leak	test air pressure	0 - 5,000 m $280^{\circ}$ 18 m/sec
Test results le	ss than .05%	5,000 - 10,000 m 310° 40 m/sec
		10,000 m - altitude320°46 m/sec
		Altitude 320° 45 m/sec
Mfr. balloon #_	Schjeldahl 13	Flight duration 85 days
Balloon mass	982 g	m Flight duration 91+ balloon days
Balloon volume_	4.44 m	Number of orbits 6+
Balloon diamete	er2.04	m Position last heard 65705 (21/08/66)
Film thickness_	1.5 mil	s Balloon days tracked 50
Electronics mas	ss 116 g	<u>m</u>
Ballast	131 g	m Remarks: This balloon remained in
Gross weight le	ess helium <u>1229</u> g	$_{ exttt{m}}$ the Antarctic night during much of
Free lift	172 g	$_{ m \underline{m}}$ July and August. Last good data on
		21/08/66. Last data on 26/08/66.
Launch site	172° 32'E, 43° 29'	<u>s</u>
Launch time	)2/06/66 2002 U	<u>T</u>
Ascent rate		
0 - 5,000 m_	1.5 m/se	<u>c</u>
5,000 - 10,00	00 m 2.0 m/se	<u>c</u>
Float altitude_	11,800	<u>m</u>
Radar	<u>-</u>	
Computed xxxx	•	
•		
Calibration dat	a.	
Sun angleCo	ode period $(10^{-1} \text{ sec})$	)
10 <sup>O</sup>	28.4	
30°	16.9	
80°	9.6	
8	0° Occulting angl	<b>e</b>

Balloon #	40204 B	
Frequency		MHz
Method of leak tes	st <u>air press</u>	sure
Test results less	than .05%	
· · · · · · · · · · · · · · · · · · ·		
Mfr. balloon #		
Balloon mass	976	gm
Balloon volume	4.44	m <sup>3</sup>
Balloon diameter_	2.04	m
Film thickness	1.5	mils
Electronics mass_	116	gm
Ballast	137	gm
Gross weight less	helium 122	9 gm
Free lift	172	gm
Launch site	172° 32 'E, 43	3 <sup>0</sup> 29 ' S
Launch time 06	/06/66 0010	<u>0 UT</u>
Ascent rate		
0 - 5,000 m	1.5	m/sec
5,000 - 10,000 r	n 2.0	m/sec
Float altitude	11,800	m
Radar		
Computed_xxxx		
Calibration data		•
Sun angleCode	period (10 <sup>-1</sup>	sec)
10°	25.2	,
30°	16.0	
80°	9.4	
80°	Occulting	angle
	Occurring	angre

C C	210	) /,	1
Surface winds	210	4	m/sec
Cloud cover			
Climb-out winds		2300	UT
0 - 5,000 m_	240 <sup>0</sup>	9 m/s	ec
5,000 - 10,00	0 m 2	50 <sup>0</sup> 10	m/sec
10,000 m - al	titude	250°	10 m/sec
Altitude	260°	10 m/s	ec

Flight duration 209 days

Flight duration 225 balloon days

Number of orbits 16

Position last heard 84765 (31/12/66)Balloon days tracked 216

Remarks: Last report with good data transmission on 31/12/66. Balloon heard briefly on 13/01/67 by Melbourne and on 20/01/67 by Lima. Failure may have been electronic.

Balloon #	41204 W		Surface winds	° calm m/s	sec
Frequency	15.024	MHz	Cloud cover		
			Climb-out winds	1700	UT
Method of leak te	st <u>air press</u>	ure	0 - 5,000 m 180	o 9 m/sec	
Test results less	s than .05%		5,000 - 10,000 m_	220 <sup>°</sup> 18 m/se	∋c
Analytic three to the second of the second o		· · · · · · · · · · · · · · · · · · ·	10,000 m - altitu		
			Altitude 210	° 22 m/sec	
Mfr. balloon #	Schjeldahl	14	Flight duration	89 da	ays
Balloon mass	982	gm	Flight duration 9	6 balloon da	ays
Balloon volume	4.44	m <sup>3</sup>	Number of orbits	7	
Balloon diameter_	2.04	m	Position last heard	52850 (12/09)	/66)
Film thickness	1.5	mils	Balloon days tracke	.d <u>80</u>	
Electronics mass_	110	gm			
Ballast			Remarks: Probable	cause of fail	ıre
Gross weight less	helium 1229	gm	balloon leak.		
Free lift	172	gm			
Launch site	172° 32'E, 43	° 29 ' S			
Launch time 15/0	6/66 2142	UT			
Ascent rate					
0 - 5,000 m	1.5	m/sec			
5,000 - 10,000 m	m 2.0	m/sec			
Float altitude	11,800	m			
Radar	· .				
Computed_xxxx					
Calibration data					
Sun angleCode	period $(10^{-1})$	sec)			
10°	19.6				
30°	12.5				
80°	7.4				
80°	Occulting	angle			

Occulting angle

Cloud coversee remarks  Climb-out windsUT  0 - 5,000 m  5,000 - 10,000 m  10,000 m - altitude  Altitude  Flight duration0 days  Flight duration0 balloon days  Number of orbits0
0 - 5,000 m
5,000 - 10,000 m
10,000 m - altitude
Altitude
Flight duration 0 days  Flight duration 0 balloon days  Number of orbits 0
Flight duration 0 balloon days  Number of orbits 0
Flight duration 0 balloon days  Number of orbits 0
Number of orbits 0
Position last heard
Balloon days tracked
Remarks: This balloon was waxed and
flown in a heavy overcast with tops
5000 m. The signals were never
received at the station from the
balloon.
•

Balloon #	43502 N		Surface winds	° calm m/sec
Frequency	15.023	MHz	Cloud cover see	remarks
			Climb-out winds	UT
Method of leak	test tent test	:	0 - 5,000 m	
Test results	no leaks found		5,000 - 10,000 m_	
			10,000 m - altitud	de
			Altitude	
			Flight duration	
•	877			
	1.86			
	er 1.52		·	
	2.5	mils	Balloon days tracked	d
Electronics ma		gm		
	87		Remarks: Broken alt	
_	ess helium 1104		scattered cirrus at	
Free lift	276	gm	Probable cause	of failure:
			balloon icing.	
Launch site	172° 32'E, 43°	<u> 29'S</u>		
Launch time	29/06/66 1923	3 UT		
Ascent rate				
0 - 5,000 m_	3 m	ı/sec		
5,000 - 10,0	00 mm	n/sec		
Float altitude	5600	<u>m</u>		
Radar				
Computed x	<u>xx</u> xx			
Calibration da	ta			
Sun angleC	ode period (10 <sup>-1</sup>	sec)		
10°	32.0	<del></del>		
30°	19.6			
83°	11.1			
	83 <sup>0</sup> Occulting a	ng1e		

Balloon #	44205 N	Surface winds 0 m/sec
Frequency	15.025 MHz	Cloud cover
		Climb-out winds UT
Method of leak	test_tent test_	0 - 5,000 m
Test results r	no leaks found	5,000 - 10,000 m
		10,000 m - altitude
		Altitude
Mfr. balloon #_	Raven 22	Flight duration 3 days
Balloon mass	956 gm	Flight duration 3 balloon days
Balloon volume_	4.19 m <sup>3</sup>	Number of orbits 0
Balloon diamete	er 2.0 m	Position last heard 63312 (17/07/66)
Film thickness_	1.5 mils	Balloon days tracked
Electronics mas	ss <u>114</u> gm	
Ballast	90 gm	Remarks: Techniques used at this
Gross weight le	ess helium <u>1160 gm</u>	time in the tent test were not
Free lift	162 gm	satisfactory for uncovering leaks.
Launch site	172° 32'E, 43° 29'S	
Launch time	14/07/66 2045 UT	
Ascent rate		
	1.5 m/sec	
5,000 - 10,00	00 m 2.0 m/sec	
Float altitude_	11,800 m	
Radar		
Computed xxxx	2	
•		
Calibration dat	_	
~	ode period $(10^{-1} \text{ sec})$	
10°	28.0	
<u>30°</u>	15.4	
80°	9.6	
80 <sup>c</sup>	Occulting angle	

Balloon #	45202 C	Surface winds o m/sec
Frequency	15.022 MHz	
		Climb-out winds UT
Method of leak te	st <u>tent test</u>	0 - 5,000 m
Test results	no leaks	5,000 - 10,000 m
	uncovered	10,000 m - altitude
		Altitude
Mfr. balloon #	Raven 16	Flight duration 4 days
Balloon mass	959 gm	Flight duration 4 balloon days
Balloon volume	4.19 m <sup>3</sup>	Number of orbits0
Balloon diameter_	2.0 m	Position last heard 63006 (29/07/66)
Film thickness	1.5 mils	Balloon days tracked
Electronics mass_	113gm	
Ballast	88 gm	Remarks: The tent test technique as
	helium <u>1160 gm</u>	used at this time was not satisfactory
Free lift	162 gm	for detecting leaks. It is apparent that
		this balloon was not leak free.
Launch site	172° 32'E, 43° 29'S	
Launch time 25	/07/66 2052 UT	
Ascent rate		
	1.5 m/sec	
5,000 - 10,000 r	m 2.0 m/sec	
:	11,800 m	
Radar		
Computed XXX	inger M	
Calibration data		
- (*)	period $(10^{-1} \text{ sec})$	
10°	20.0	
30°	12.7	
80°	7.6	
80°	Occulting angle	

Balloon #	46303 P		Surface winds m/sec
Frequency	15.025	MHz	Cloud cover
			Climb-out winds UT
Method of leak t	est <u>tent</u>	test	0 - 5,000 m
Test results	no leak	s	5,000 - 10,000 m
	detecte	d	10,000 m - altitude
	Wast .		Altitude
Mfr. balloon #	Schjeld	ah1 14	Flight duration 9 days
Balloon mass	879	gn	n Flight duration 9 balloon days
Balloon volume	1.86	m <sup>3</sup>	Number of orbits0
Balloon diameter	1.52	n	Position last heard 63450 (06/08/66)
Film thickness	2.5	mils	Balloon days tracked 5
Electronics mass	116	gn	<u>1</u>
Ballast	109	gn	Remarks: An error in computation
Gross weight les	s helium_	1104 gn	resulted in the free lift at launch
Free lift	276	gn	of 359 gm 35%. Balloon was wax
			treated and equipped with a special
Launch site	172° 32 'E	, 43 <sup>0</sup> 29 ' 8	harness to insure against damage to
Launch time 3	1/07/66	2335 ຫຼ	transmitter from turbulence.
Ascent rate			
0 - 5,000 m	3	m/sec	<u>.</u>
5,000 - 10,000	m	m/sec	<u> </u>
Float altitude	5550	n	<u>1</u>
Radar			
Computed xxxx			

- ,					
10,000 m - altitude					
Altit	ude	,	· · · · · · · · · · · · · · · · · · ·		
Flight	duration_		9	days	
Flight	duration_	9	balloon	days	
NT l	. E		. 0		

m/sec

### Calibration data

Sun angle--Code period (10<sup>-1</sup> sec)

	LO <sup>O</sup> 2	21.2	
3	30°	13.3	
8	3°	7.8	
	83°	Occulting	angle

Balloon #	47205 A	Surface winds O m/sec
Frequency	15.025 MHz	
		Climb-out winds UT
Method of leak te	est <u>tent</u> test	0 - 5,000 m
	two leaks	
detecte	ed and repaired	10,000 m - altitude
		Altitude
Mfr. balloon #	Raven 21	Flight duration 23 days
Balloon mass	963 gm	Flight duration 24 balloon days
Balloon volume	4.19 m <sup>3</sup>	Number of orbits 1
	2.0 m	
Film thickness_	1.5 mils	Balloon days tracked 23
Electronics mass_	167 gm	
Ballast	30 gm	Remarks: Probable cause of failure:
Gross weight less	helium 1160 gm	balloon leak
Free lift	162 gm	
Launch site	172° 32'E, 43° 29'S	
Launch time 09/	/08/66 2121 <u>UT</u>	
Ascent rate		
0 - 5,000 m	1.5 m/sec	
5,000 - 10,000	m 2.0 m/sec	
Float altitude	11,800 m	
Radar		
Computed xxxx		
Calibration data		
Sun angleCode	period $(10^{-1} \text{ sec})$	
10°	21.0	
30°	14.1	
80°	9.6	
80°	Occulting angle	

Balloon #	48207 M		Surface winds	m/sec
Frequency	15.027	MHz	Cloud cover	
			Climb-out winds	UT
Method of leak to	esttent_tes	st	0 - 5,000 m	
Test results	no leaks fo	ound	5,000 - 10,000 m	· · · · · · · · · · · · · · · · · · ·
			10,000  m - $altite$	ude
	· · · · · · · · · · · · · · · · · · ·		Altitude	
Mfr. balloon #	Raven 15		Flight duration	20+ days
Balloon mass	964	gm	Flight duration	21+ balloon days
Balloon volume	4.19	m <sup>3</sup>	Number of orbits	1
Balloon diameter_	2.0	<u>m</u>	Position last hear	d
Film thickness	1.5	mils	Balloon days track	ed5
Electronics mass		gm		
Ballast	86	gm	Remarks: Transmis	sion was inter-
Gross weight less	s helium 1160	gm	mittent and errati	c. Electronics
Free lift	162	gm	apparently failed	on the 20th day.
Launch site	172° 32'E, 4	3° 29 ' S		
Launch time 11	<u>/08/66 21</u>	00 UT		
Ascent rate				
0 - 5,000 m	•			
5,000 - 10,000	m 2.0	m/sec		
Float altitude	11,800	m		
Radar				
Computed xxxx	ti e			
Calibration data				
Sun angleCode		sec)		
10°	30.2			
30°	19.9			
80°	11.8			
80°_	Occulting	angle		

Balloon #	49208 R	· · · · · · · · · · · · · · · · · · ·	Surface winds
Frequency	15.028	MHz	Cloud cover_
			Climb-out win
Method of leak	test see rema	rks	0 - 5,000 m
Test results	15 holes foun	ıd and	5,000 - 10,
repa	ired		10,000 m -
			Altitude
Mfr. balloon #	Raven 23		Flight durati
Balloon mass_	960	gm	Flight durati
	4.19		
Balloon diamet	er2.0	m	Position last
	1.5		
	.ss <u>110</u>		
Ballast	90	gm	Remarks: Lea
Gross weight 1	ess helium <u>l</u>	.160 gm	face inspecti
Free lift	162	gm	This bal
			long on one g
Launch site	172° 32'E,	43 <sup>0</sup> 29'S	pinholes whic
Launch time	02/09/66 213	7 UT	the halogen d
Ascent rate			the extensive
	1.5		
5,000 - 10,0	00 m 2.0	m/sec	Transmit
Float altitude	11,800	<u>m</u>	first flight
Radar	_		
Computed xxx	<u>x</u>		
	+ +		
Calibration da	ta		
Sun angleC	ode period (10	sec)	
10 <sup>O</sup>	34.2		
30°	23.6		
80°	14.9		
	$80^{\circ}$ Occulting	- 02010	

Surface winds	0	m/sec
Cloud cover		
Climb-out winds		UT
0 - 5,000 m		
5,000 - 10,000 m_		
10,000 m - altitud	de	
Altitude		·

Flight duration 133 days

Flight duration 143 balloon days

Number of orbits 10

Position last heard 82555 (12/01/67)

Balloon days tracked 121

Remarks: Leak test by complete surface inspection with halogen detector.

This balloon had one crack 1/4"
long on one gore as well as 14 small
pinholes which were detected using
the halogen detector. Because of
the extensive surface testing, the
tent test was not used prior to flight.

Transmitter keyed improperly on first flight day.

Balloon #	50201 D		Surface winds	0	m/sec
Frequency	15.021	MHz	Cloud cover		
			Climb-out winds		UT
Method of leak	test tent tes	st	0 - 5,000 m		
Test results_3	leaks detected	d and	5,000 - 10,000 m_		
repai	red		10,000 m - altitu	de	· · · · · · · · · · · · · · · · · · ·
		<u></u>	Altitude		
Mfr. balloon #_	Raven 12	<del></del>	Flight duration_	148	days
Balloon mass	965	gm	Flight duration 15	<sup>7</sup> bal:	loon days
Balloon volume_	4.19	m <sup>3</sup>	Number of orbits	9	
Balloon diamete	er2.0	m	Position last heard	65945	(01/02/67
Film thickness_	1.5	mils	Balloon days tracke	d 150	
Electronics mas	ss118	gm			
Ballast	77	gm	Remarks:		
Gross weight le		0 gm	Probable cause of f	ailure:	balloon
Free lift	162	gm	leak.		
Launch site	172° 32'E, 43	3 <sup>0</sup> 29 ' S			
Launch time 07	7/09/66 2129	9 UT			
Ascent rate					
0 - 5,000 m_	1.5	m/sec			
5,000 - 10,00	00 m 2.0	m/sec			
Float altitude_	11,800	m			
Radar	_				
Computedxxx	<u>∢</u> x				
Calibration dat	ta .				
Sun angleCo	ode period $(10^{-1})$	sec)			
10°	29.1				
30°	18.9				
80°	11.1				
	80° Occulting	angle			

Balloon #	51206 P		Surface winds o m/sec
Frequency	15.026	MHz	Cloud cover
			Climb-out winds UT
Method of leak to	est <u>tent</u>	test	0 - 5,000 m
Test results 1	pinhole leal	ζ.	
detect	ed and repa	ired	10,000 m - altitude
			Altitude
Mfr. balloon #	Raven 18		Flight duration 67 days
Balloon mass	955	gm	Flight duration 72 balloon days
Balloon volume	4.19	m <sup>3</sup>	Number of orbits 5
Balloon diameter			Position last heard 52544 (29/11/66
Film thickness	1.5	mils	Balloon days tracked 70
Electronics mass	115	gm	
Ballast	90	gm	Remarks:
Gross weight less	s helium $1$	160 gm	Probable cause of failure: balloon
Free lift	162	gm	leak.
Launch site	172° 32'E,	43 <sup>°</sup> 29 'S	
Launch time 24	/09/66	2025 UT	
Ascent rate			
0 - 5,000 m	1.5	m/sec	
5,000 - 10,000	m 2.0	m/sec	
Float altitude	11,800	<u>m</u>	
Radar			
Computed xxxx			
Calibration data			
Sun angleCode	e period (10	) <sup>-1</sup> sec)	
10°	31.3		
30°	21.1		
80°	12.8	<del></del>	
80 <sup>0</sup>	0 1	-	

Balloon #	52207 W		Surface winds	m/sec
Frequency	15.027	MHz	Cloud cover	
			Climb-out winds	UT
Method of leak tes	st <u>tent test</u>		0 - 5,000 m	·
Test results	no leaks fo	und	5,000 - 10,000 m	
MARKET STATE OF THE STATE OF TH			10,000 m - altitude	
			Altitude	
Mfr. balloon #	Raven 19		Flight duration_	16 days
Balloon mass	961	gm	Flight duration 17	balloon days
Balloon volume	4.19	m <sup>3</sup>	Number of orbits	1
Balloon diameter_	2.0	<u>m</u>	Position last heard 67	330 (29/11/66)
Film thickness	1.5	mils	Balloon days tracked_	17
Electronics mass_	152	gm		
Ballast	47	gm	Remarks:	
Gross weight less	helium 1160	gm	Probable cause of fai	lure: balloon
Free lift	162	gm	leak.	
Launch site	172° 32'E, 43°	<sup>2</sup> 29 ' S		
Launch time 10/	10/66 2020	UT		
Ascent rate				
0 - 5,000 m	1.5	m/sec		
5,000 - 10,000 m	m 2.0	m/sec		
Float altitude	11,800	m		
Radar				
Computed xxxx				
Calibration data				
Sun angleCode	period $(10^{-1})$	sec)		
10°	22.5			
30°	14.3			
80°	7.8			
80°	Occulting	ano le		

Balloon #	53507 Z	
Frequency	15.027	MHz
Method of leak tes	t tent test	<u> </u>
Test results	no leaks fou	ınd
Mfr. balloon #	Schjeldahl	5
Balloon mass	874	gm
Balloon volume	1.853	m <sup>3</sup>
Balloon diameter_	1.524	m
Film thickness_	2.5	mils
Electronics mass	118	gm
Ballast	112	gm
Gross weight less	helium 1104	gm
Free lift	442	gm
Launch site	172° 32'E, 43°	29 <b>'</b> S
Launch time 11/10	0/66 2004	UT
Ascent rate		
0 - 5,000 m_	3.1 n	n/sec
5,000 - 10,000 m		
Float altitude	5585	m
Radar <u>xxxx</u>		
Computed		
	•	
Calibration data		
Sun angleCode	period $(10^{-1})$	sec)
10 <sup>°</sup>	22.6	
30°	14.3	
83 <sup>0</sup>	7.6	

83°

Occulting angle

Surface windso	m/sec
Cloud cover	<u> </u>
Climb-out winds	UT
0 - 5,000 m	
5,000 - 10,000 m	
10,000 m - altitude	
Altitude	

14	days
balloon	days
0	
(2	24/10/66)
5	
	balloon 0

Remarks: This balloon was wax treated and was reinforced with three horizontal bands of GT-12 tape across the equator section. Balloon reached the Andes but did not cross.

Probable cause of failure: either icing or contact with the Andes.

Balloon #	34303 L	<del></del>
Frequency		MHz
Method of leak tes	t tent tes	t
Test results 1 p		
and repa		<u> </u>
	,	
Mfr. balloon #	Schjeldah1	. 6
Balloon mass	201	gm
Balloon volume		
Balloon diameter_		m
Film thickness		mils
Electronics mass_		gm
Ballast	100	gm
Gross weight less		
Free lift		gm
Launch site	172°32 <b>'</b> E, 4	3 <sup>0</sup> 29 ' S
Launch time 11		
Ascent rate		
0 - 5,000 m	3.1	m/sec
5,000 - 10,000 m		
Float altitude		m
Radar		
Computed_xxxx		
-		
Calibration data		•
Sun angleCode	period (10	1 sec)
10°	27.6	,
30°	16.8	
83°	8.9	
83°	Occulting	anole

Surface windso	m/sec
Cloud cover	
Climb-out winds	UT
0 - 5,000 m	
5,000 - 10,000 m	
10,000 m - altitude	
Altitude	

Flight duration 11 days Flight duration 11 balloon days Number of orbits 0 Position last heard 53375 (21/10/66) Balloon days tracked

Remarks: This balloon was coated with wax and reinforced with GT-12 tape placed in planes along the equator and at  $45^{\circ}$ —offsets from the equator. The balloon reached South America.

Probable cause of failure: icing or contact with the Andes.

Balloon #	55201 M
Frequency	
Method of leak tes	t tent test
Test results 2 pin	
& repaired. Large	
balloon fabric dur:	ing pinhole repair
was also repaired.	
Mfr. balloon #	Raven 20
Balloon mass	962 gm
Balloon volume	4.19 m <sup>3</sup>
Balloon diameter	2.0 m
Film thickness	
Electronics mass	
Ballast	51 gm
Gross weight less	
Free lift	162 gm
Launch site	172°32'E, 43°29'S
Launch time 13/1	0/66 2040 UT
Ascent rate	
0 - 5,000 m	1.5 m/sec
5,000 - 10,000 m	2.0 m/sec
Float altitude	11,800 m
Radar	
Computed <u>xxxx</u>	
Calibration data	
Sun angleCode	period (10 <sup>-1</sup> sec)
10 <sup>o</sup>	30.5
30°	19.4
80°	12.3
80°	Occulting angle

Surface windso	m/sec
Cloud cover	
Climb-out winds	UT
0 - 5,000 m	
5,000 - 10,000 m	
10,000 m - altitude	
Altitude	

Flight duration 134 days

Flight duration 143 balloon days

Number of orbits 9?

Position last heard 63560 (23/02/67)

Balloon days tracked 68

Remarks: This balloon had a history of intermittent transmitter operation.

Probable cause of failure: electronics failure.

Balloon # 56034 L 56038 V	Surface winds O m/sec
Frequency 15.034 15.028 MHz	
	Climb-out winds UT
Method of leak test not tested	0 - 5,000 m
Test results	5,000 - 10,000 m
	10,000 m - altitude
	Altitude
Mfr. balloon # Schjeldahl 4	Flight duration 1 days
Balloon mass 6556 gm	Flight duration 1 balloon days
Balloon volume 158 m <sup>3</sup>	Number of orbits 0
Balloon diameter 6.70 m	Position last heard
Film thickness 1 mils	Balloon days tracked 1
Electronics mass 288 gm	
Ballast 96 gm	Remarks: A separate transmitter was
Gross weight less helium 6940 gm	flown to check on electronics temper-
Free lift 1249 gm	ature at 30 mb. The electronics
	operated at 17 <sup>0</sup> C with only minor
Launch site 172° 32'E, 43° 29'S	fluctuations during the day. The
Launch time 26/10/66 1730 UT	balloon failed on the first night.
Ascent rate	Probable cause of failure: large
0-10,000 m 3.8 m/sec	hole or rip introduced either in
10,000 - 24,000 m 3.4 m/sec	fabrication, handling, or during
Float altitude 24,000 m	the high speed ascent.
Radar	
Computed_xxxx	
Calibration data VVV	
Sun angleCode period $(10^{-1} \text{ sec})$	
10 <sup>o</sup> 44.7	
30° 30.1	
68° 18.4	
68° Occulting angle	

Balloon #	57200 O		Surface winds om/sec
Frequency	15.020	MHz	Cloud cover
			Climb-out winds UT
Method of leak	test <u>tent</u>	est	0 - 5,000 m
Test results no leaks found			5,000 - 10,000 m
-	<del></del>		10,000 m - altitude
			Altitude
Mfr. balloon #_			
Balloon mass		gm	
Balloon volume_		m <sup>3</sup>	
Balloon diamete		<u>m</u>	60
Film thickness_		mils	Balloon days tracked 69
Electronics mas		gm	
Ballast		gm	Remarks:
Gross weight le		60 gm	Probable cause of failure: balloon
Free lift	162	gm	leak.
Launch site	172° 32 'E,	43 <sup>0</sup> 29 ' S	
Launch time3	1/10/66 16	552 UT	
Ascent rate			
0 - 5,000 m_	1.5	m/sec	
5,000 - 10,00	0 m 2.0	m/sec	
Float altitude_	11,800	m	
Radar			
Computed xxxx			
Calibration dat	a		
Sun angleCo	de period (10	-1 sec)	
10°	30.2		
30°	20.2		
80°	11.6		
80	Occultin	o anole	

Balloon #	58207 G	Surface winds o m/sec
Frequency	15.027 MHz	Cloud cover
		Climb-out winds UT
Method of leak tes	sttent test	0 - 5,000 m
Test results	1 pinhole leak	5,000 - 10,000 m_
detected	d and repaired	10,000 m - altitude
		Altitude
		•
Mfr. balloon #	Raven 9	Flight duration 106 days
Balloon mass	978 gm	Flight duration 113 balloon days
Balloon volume	4.19 m <sup>3</sup>	Number of orbits 7
Balloon diameter_	2.0 m	Position last heard 54245 (23/02/67)
Film thickness	1.5 mils	· · · · · · · · · · · · · · · · · · ·
Electronics mass_	113 gm	
Ballast	69 gm	Remarks:
Gross weight less	helium 1160 gm	Probable cause of failure: balloon
Free lift	162 gm	leak.
Launch site	172° 32'E, 43° 29'S	
Launch time 0	9/11/66 1935 <u>UT</u>	
Ascent rate		
0 - 5,000 m	1.5 m/sec	
5,000 - 10,000 m	m 2.0 m/sec	
Float altitude	11,800 <u>m</u>	
Radar		
Computed xxxx		
Calibration data		
Sun angleCode	period $(10^{-1} \text{ sec})$	
10°	31.0	
30°	20.4	
80°	11.4	
80°	Occulting angle	

Balloon #	59207 ED	
Frequency		
Method of leak t	est <u>not</u> te	sted
Test results		
****		
134		
Mfr. balloon #	Schjelda	h1 18
Balloon mass		
Balloon volume	6.06	m <sup>3</sup>
Balloon diameter	2.26	<u>m</u>
Film thickness	2.0	mils
Electronics mass	200	gm
Ballast	58	gm
Gross weight les		
Free lift	300	gm
Launch site	166°7'E, 77°	°8'S
Launch time 13	/11/66	0734 UT
Ascent rate		
0 - 5,000 m		
5,000 - 10,000		
Float altitude		
Radar		
${\tt Computed}_{\underline{\tt XXXX}}$		
	•	
Calibration data		
Sun angleCode	e period (10	) <sup>-1</sup> sec)
0°	33.5	
30°	15.1	
80°	6.6	
80°	Occult <b>i</b> r	ng angle

Surface winds	0	5	m/sec
Cloud cover			
Climb-out winds			UT
0 - 5,000 m			
5,000 - 10,000 m_			
10,000 m - altitu	ıde		
Altitude			<del>,</del>

Flight duration_	12	days
Flight duration_	15 balloon	days
Number of orbits	3	
Position last hea	ard 57830 (24/11	L/66)
Balloon days trac		

Remarks: Balloon equipped with solar cell side panels for low sun angle transmission.

Probable cause of failure: balloon damage during cold inflation or windy launch.

Balloon #	60203 TA	
Frequency		MHz
Method of leak		
Test results		
***************************************		<del> </del>
Mfr. balloon #_	Schjeldahl 19	
Balloon mass	1397	gm
Balloon volume_	6.06	m <sup>3</sup>
Balloon diamete	r 2.26	m
Film thickness_		
Electronics mas	s200	gm
Ballast	83	gm
Gross weight le	ss helium 1680	gm
Free lift	300	gm
Launch site	166°7'E, 77°	8'S
Launch time 14	/11/66 22:	25 UT
Ascent rate		
0 - 5,000 m_	1.6	m/sec
5,000 - 10,00	0 m 2.0	m/sec
Float altitude_	11,800	m
Radar	-	
Computed xxxx	<u> </u>	
Calibration dat	a	
Sun angleCo	de period (10 <sup>-1</sup>	sec)
0°	41.0	
, <u>30</u> °	23.0	
80°	11.4	
80 <sup>0</sup>	Occulting	angle

Occulting angle

Surface winds	0	4	m/sec
Cloud cover			
Climb-out winds			UT
0 - 5,000 m	•		
5,000 - 10,000 m			
10,000 m - altitude	<u></u>		
Altitude			

Flight duration\_see remarks days Flight duration balloon days Number of orbits\_\_\_\_\_ Position last heard\_\_\_\_\_ Balloon days tracked\_\_\_\_

Remarks: Balloon equipped with solar cell side panels for low sun angle transmission.

It has remained at high latitudes during most of its life. On its  $206 \, \text{th}$  day (06/06/67) it was located at 56152. It then returned into the Antarctic night and reappeared momentarily on the 209th day (09/06/67).

Balloon #	61209 TR	Surface winds 3 m/sec
Frequency	15,030 MH:	z Cloud cover
		Climb-out winds UT
Method of leak	test not tested	0 - 5,000 m
Test results		5,000 - 10,000 m
444744		10,000 m - altitude
		Altitude
Mfr. balloon #_	Schjeldahl 2	Flight duration 89 days
Balloon mass	1410 gr	n Flight duration 93 balloon days
Balloon volume_	6.06 m <sup>3</sup>	Number of orbits4
Balloon diamete	er 2.26 r	Position last heard
Film thickness_	2.0 mils	Balloon days tracked82
Electronics mas	ss 200 gr	<u>a</u>
Ballast	70 gr	n Remarks: This balloon was not equipped
Gross weight le	ess helium <u>1680 gr</u>	$_{ t 0}$ with solar cell side panels.
Free lift	300 gr	Probable cause of failure: balloon
		leak introduced in fabrication,
Launch site	166°7'E, 77°8'S	handling, or cold temperature infla-
Launch time1	ט 17/11/66 0925 טי	tion.
Ascent rate		
0 - 5,000 m_	1.6 m/sec	2
5,000 - 10,00	00 m 2.0 m/sec	<u>:</u>
Float altitude_	11,800 n	<u>1</u>
Radar	<del>.</del>	
Computed xxx	ÇX.	
	•	
Calibration dat	a	
Sun angleCo	de period $(10^{-1} \text{ sec})$	
10°	32.4	<del>-</del> .
30°	18.5	- -
80°0	8.2	
80	00011+ina anala	

Balloon #	6220/ TN		Surface winds <u> </u>	<u>c</u>
Frequency	15.027	MHz	Cloud cover	
			Climb-out winds	T
Method of leak	test <u>not tes</u>	ted	0 - 5,000 m	
Test results	<u> </u>		5,000 - 10,000 m	
	·		10,000 m - altitude	
			Altitude	_
Mfr. balloon #_			Flight duration 21 day	
Balloon mass				'S
Balloon volume_			Number of orbits 3	_
Balloon diameter	r2.26	<u>m</u>	Position last heard 57660 (07/12/0	56) <u>–</u>
Film thickness_	2.0	mils	Balloon days tracked 24	<u>.</u>
Electronics mass	s223	gm		
Ballast	76	gm	Remarks: This balloon was equip	ed
Gross weight le	ss helium $\frac{1}{}$	680 gm	with solar cell side panels.	
Free lift	300	gm	Probable cause of failure:	
			balloon leak introduced either in	
Launch site	166°7'E, 77	°8'S	fabrication, handling, cold weath	er
Launch time 17/	11/66 102	.5 <u>UT</u>	inflation, or gusty launch.	
Ascent rate				
0 - 5,000 m	1.6	m/sec		
5,000 - 10,000	0 m 2.0	m/sec		
Float altitude_	11,800	m		
Radar				
Computed xxxx				
Calibration data	a			
Sun angleCo	de period (10	-1 sec)		
0°	38.0			
10°	25.5			
30°	14.5			
80°	6.1 Occultin	a anala		

Balloon #	63203 L	Surface winds m/sec
Frequency	15.023 MHz	Cloud cover
		Climb-out winds UT
Method of leak t	est tent test	0 - 5,000 m
	no leaks	
	detected	10,000 m - altitude
		Altitude
Mfr. balloon #	Raven 5	Flight duration 58 days
Balloon mass	963 gm	Flight duration 61 balloon days
Balloon volume	4.19 m <sup>3</sup>	Number of orbits 3
Balloon diameter	2.0 m	Position last heard 64532 (25/01/67)
Film thickness	1.5 mils	Balloon days tracked58
Electronics mass	<u>s 118</u> gm	
Ballast	79 gm	Remarks:
Gross weight les	s helium 1160 gm	Probable cause of failure: balloon
Free lift	162 gm	leak.
Launch site	172° 32'E, 43° 29'S	
Launch time 2	27/11/66 2030 UT	
Ascent rate		
0 - 5,000 m	1.5 m/sec	
5,000 - 10,000	m 2.0 m/sec	
Float altitude	11,800 m	
Radar		
Computed xxx	<b>S</b>	
Calibration data		
Sun angleCod	e period $(10^{-1} \text{ sec})$	
10°	22.3	
30°	14.6	
80°	8.1	
80°	Occulting angle	

Balloon #	64034 N		Surface winds <u>o calm m/sec</u>
Frequency	15.024	MHz	Cloud cover
			Climb-out winds UT
Method of leak tes	t <u>wadin</u>	g pool	0 - 5,000 m
Test results	no leak	s found	5,000 - 10,000 m
			10,000 m - altitude
			Altitude
Mfr. balloon #	Sch jeld	lah1 2	Flight duration 61 days
Balloon mass	6584	gm	Flight duration 59 balloon days
Balloon volume	158	m <sup>3</sup>	Number of orbits
Balloon diameter_			Position last heard 57160 (14/02/67)
Film thickness	1	mils	Balloon days tracked 49
Electronics mass_	119	gm	
Ballast	237	gm	Remarks: This balloon was leak tested
Gross weight less	helium_	6940 gm	in the Canterbury Court Building, the
Free lift	1249	gm	largest building in Christchurch.
			Although it tested leak free, it was
Launch site	172° 32 'E	<u>1, 43<sup>0</sup> 29 'S</u>	roughly handled during deflation.
Launch time 15/12	2/66	1645 UT	The balloon carried 600 gm dry ice
Ascent rate			to reduce rate of rise.
0 -10,000 m	2.0	m/sec	Probable cause of failure: balloon
10,000 - 24,000 m	2.5	m/sec	leak.
Float altitude	24,000	m	
Radar			
Computed_xxxx			
Calibration data			
Sun angleCode	period	(10 <sup>-1</sup> sec)	
10°	28.8		
30°	16.6		
66°	9.9		

66°

Occulting angle

Balloon #	65505 A	(
Frequency	15.025	MHz
		(
Method of leak tes		
Test results	no leaks	detected
Managine and Washington Standards and a second		<del></del>
***************************************		
Mfr. balloon #		1 7
		gm 1
Balloon volume		
Balloon diameter	1.524	<u>m</u> ]
Film thickness	2.5	mils 1
Electronics mass	116	gm
Ballast	101	gm I
Gross weight less		.04 gm
Free lift	442	gm
Launch site	172°32'E,	43 <sup>0</sup> 29'S
Launch time 15/12	2/66 172	.1 <u>ur</u>
Ascent rate		
0 - 5,000 m	3	m/sec
5,000 - 10,000 m		
Float altitude		m
Radar		
Computed xxxx		
-		
Calibration data		
Sun angleCode	period (10	-1 sec)
10°	30.0	
30°	18.6	
83°	10.2	
83 <sup>o</sup>	Occultin	g angle

Surface winds o	m/sec
Cloud cover	
Climb-out winds	UT
0 - 5,000 m	
5,000 - 10,000 m	
10,000 m - altitude	
Altitude	

Flight duration	4	days
Flight duration 4	ball	oon days
Number of orbits	0	
Position last heard_	54575	(19/12/66)
Balloon days tracked_	3	

Remarks: This balloon was reinforced and coated with a silicone wax.

Probable cause of failure: icing.

Balloon #	66502 Н	Surface winds 0 m/sec
Frequency	15.022 MHz	Cloud cover
		Climb-out winds UT
Method of leak te	st <u>tent test</u>	0 - 5,000 m
Test results	no leaks	5,000 - 10,000 m
	detected	10,000 m - altitude
		Altitude
Mfr. balloon #	Schjeldahl 9	Flight duration 1 days
Balloon mass	888 gm	Flight duration 1 balloon days
Balloon volume	1.853 m <sup>3</sup>	Number of orbits 0
Balloon diameter_	1.524 m	Position last heard 74778 (16/12/66)
Film thickness	2.5 mils	Balloon days tracked
Electronics mass_	120 gm	
Ballast	96 gm	Remarks: This balloon was prepared
Gross weight less	helium <u>1104 gm</u>	in identical fashion to 65505A, excep
Free lift	442 gm	that a different silicone wax was
		used as a water repellent.
Launch site	172° 32'E, 43° 29'S	Probable cause of failure: icing.
Launch time 15/12	2/66 1724 UT	
Ascent rate		
0 - 5,000 m	3 m/sec	
5,000 - 10,000	m m/sec	
Float altitude	<u>5550</u> m	
Radar		
Computed xxxx		
,		
Calibration data		
Sun angleCode	period $(10^{-1} \text{ sec})$	
10°	31.5	
30°	20.4	
83°	10.6	
83°	Occulting angle	

Balloon #	67306 U		Surface winds	<u> </u>
Frequency	15.026	MHz	Cloud cover	
•			Climb-out winds	UT
Method of leak	test <u>tent</u> te	est	0 - 5,000 m	· · · · · · · · · · · · · · · · · · ·
Test results	no leaks	detected	5,000 - 10,000 m	
			10,000 m - altitud	e
ev-date-water-water-water-water-water-water-water-water-water-water-water-water-water-water-water-water-water-		· · · · · · · · · · · · · · · · · · ·	Altitude	
Mfr. balloon #_	Schje1dal	n1 13	Flight duration	11 days
Balloon mass	1530	gm	Flight duration 11	balloon days
Balloon volume_	6.06	m <sup>3</sup>	Number of orbits	0
Balloon diameter	r2.26	m	Position last heard_	84765 (25/01/67)
Film thickness_	2.0	mils	Balloon days tracked	11
Electronics mass	s <u>117</u>	gm		
Ballast	733	gm	Remarks: This ballo	oon was a uvinol
Gross weight les	ss helium	2380 gm	coated balloon (for	ultraviolet
Free lift	300	gm	resistance) designed	d to fly at 200 mb
			It was ballasted for	300 mb flight.
Launch site	172° 32 'E,	43 <sup>°</sup> 29 'S		
Launch time 15/	01/67 00	50 <u>UT</u>	Probable cause of fa	ailure: icing.
Ascent rate				
0 - 5,000 m_	1.5	m/sec		
5,000 - 9,000	0 m 1.8	m/sec		
Float altitude_	9500	<u>m</u>		
Radar <u>xxxx</u>				
Computed				
Calibration data	a			
Sun angleCoo	ie period (10	) <sup>-1</sup> sec)		
10°	26.4	- Nagaragha Mayaraha ay		
30°	16.9			
80°	9.2			
80	Occultin	ng angle		

Balloon #	68300 W	Surface winds o m/sec
Frequency	15.020 M	z Cloud cover
		Climb-out winds UT
Method of leak	test tent test	0 - 5,000 m
Test results	no leaks	5,000 - 10,000 m
	detected	10,000 m - altitude
		Altitude
Mfr. balloon #_	Schjeldahl 21	Flight duration 5 days
Balloon mass_	1503	m Flight duration 5 balloon days
Balloon volume_	6.06 r	Number of orbits 0
Balloon diamete	er 2.26	m Position last heard 64648 (19/01/67)
Film thickness_	2.0 mi	ls Balloon days tracked 5
Electronics mas	s 124	<u>zm</u>
Ballast	753	m Remarks: This was a uvinol coated
Gross weight le	ess helium 2380	m balloon designed for flight at 200 m
Free lift	300	m which was ballasted for flight at
		300 mb.
Launch site	172° 32'E, 43° 29	'S Probable cause of failure: icing.
Launch time 15	5/01/67 0313 I	<u>JT</u>
Ascent rate		
0 - 5,000 m	1.5 m/se	<u>2C</u>
5,000 - 9,00	00 m <u>1.8 m/se</u>	<u>ec</u>
	9200	<u>m</u>
Radar	_	•
Computed_xxxx	2	
Calibration dat	ca	
Sun angleCo	ode period $(10^{-1} \text{ sec})$	2)
10°	23.4	
30°	14.4	<u>.</u>
80°	7.6	<u> </u>
80	Occulting ang	<u>le</u>

Balloon #	69206 Н		Surface winds o m/sec
	15.026		Cloud cover
			Climb-out winds UT
Method of leak	test not test	ed	
			5,000 - 10,000 m
· ·			10,000 m - altitude
			Altitude
Mfr. balloon #	Schjeldah1	14	Flight duration 6 days
	1474		Flight duration 6 balloon days
Balloon volume	6.06	m <sup>3</sup>	
Balloon diamet	er2.26	m	Position last heard 63301 (21/01/67)
Film thickness	2.0	mils	Balloon days tracked 6
Electronics ma	ss121	gm	
Ballast	85	gm	Remarks: This was a uvinol coated
Gross weight 1	ess helium <u>1680</u>	gm	balloon which was not tested. Sub-
Free lift	300	gm	sequent tests on similar balloons
			indicated that the uvinol coating
Launch site	172° 32'E, 43	° 29 ' S	
Launch time	15/01/67 03	350 UT	is assumed that this balloon which
Ascent rate			was carefully tested at the factory
0 - 5,000 m_	1.6	m/sec	developed an imperfection during
5,000 - 10,0	00 m 2.0	m/sec	
Float altitude	11,800	m	Probable cause of failure: balloon
Radar	<del>_</del>		leak.
Computed xx	<u>xx</u> x		
Calibration da	ıta		
Sun angle0	Code period $(10^{-1})$	sec)	
10°	24 2		
30°	16.4		
80°	9.5		
	80° 00011+ina	onala	

Balloon # 70201 K	Surface winds O m/sec
Frequency 15.021 MHz	Cloud cover
	Climb-out winds UT
Method of leak test not tested	0 - 5,000 m
Test results	5,000 - 10,000 m
	10,000 m - altitude
	Altitude
Mfr. balloon # Schjeldahl 20	Flight duration see remarks days
Balloon mass 1453 gm	Flight duration balloon days
Balloon volume 6.06 m <sup>3</sup>	Number of orbits
Balloon diameter 2.26 m	Position last heard
Film thickness 2.0 mils	Balloon days tracked
Electronics mass 157 gm	
Ballast	Remarks: Uvinol coated balloon.
Gross weight less helium 1680 gm	This balloon was still flying as of
Free lift 300 gm	08/06/67 on its 142nd day.
Launch site 172° 32'E, 43° 29'S	
Launch time 17/01/67 2057 UT	
Ascent rate	
0 - 5,000 m 1.6 m/sec	
5,000 - 10,000 m 2.0 m/sec	
Float altitude 11,800 m	
Radar	
Computed <u>xxx</u> x	
Calibration data	
Sun angleCode period (10 <sup>-1</sup> sec)	
10° 30.2	
30° 20.6	
80° 12.0	
$80^{\circ}$ Occulting angle	

Balloon #	71207 X	Surface winds om/sec
Frequency	15.027 MH:	cloud cover
		Climb-out winds UT
Method of leak te	st <u>not tested</u>	0 - 5,000 m
Test results		5,000 - 10,000 m
		10,000 m - altitude
	<del></del>	Altitude
Mfr. balloon #	Schjeldahl 17	Flight duration 17 days
Balloon mass	1420 gr	n Flight duration 18 balloon days
Balloon volume	6.06 m <sup>6</sup>	Number of orbits 1
Balloon diameter_	2.26 r	n Position last heard 85332 (03/02/67)
Film thickness	2.0 mils	Balloon days tracked 18
Electronics mass_	133 gr	<u>n</u>
Ballast	127gr	n Remarks:
Gross weight less	helium <u>1680</u> gr	n Probable cause of failure: balloon
Free lift	300 gr	n leak.
Launch site	172° 32'E, 43° 29's	<u> </u>
Launch time 18/	<u>/01/67 2043 U'</u>	<u>r</u>
Ascent rate		
0 - 5,000 m	1.6 m/sec	2
5,000 - 10,000	m 2.0 m/sec	2
Float altitude	11,800 r	<u>n</u>
Radar		
Computed xxxx		
Calibration data		
Sun angleCode	period (10 <sup>-1</sup> sec)	
10 <sup>o</sup>	26.0	<u>-</u>
30°	17.1	<del>-</del>
80°	9.7	_
80°	Occulting angle	

Balloon # 72207 C	Surface winds 0 m/sec
Frequency 15.027 MHz	Cloud cover
	Climb-out winds UT
Method of leak test <u>not tested</u>	0 - 5,000 m_
Test results	5,000 - 10,000 m
	10,000 m - altitude
	Altitude
Mfr. balloon # Schjeldahl 23	Flight duration 7 days
Balloon mass 1461 gm	Flight duration 7 balloon days
Balloon volume 6.06 m <sup>3</sup>	Number of orbits 0
Balloon diameter 2.26 m	Position last heard 54872 (24/01/67)
Film thickness 2.0 mils	Balloon days tracked 7
Electronics mass 157 gm	
Ballast 72 gm	Remarks: It is believed that this
Gross weight less helium $1680~{\rm gm}$	uvinol coated balloon was packed
Free lift 300 gm	before the surface treatment had
	hardened. The balloon may have been
Launch site 172° 32'E, 43° 29'S	damaged in unpacking.
Launch time 17/01/67 2108 UT	Probable cause of failure:
Ascent rate	balloon leak.
0 - 5,000 m 1.6 m/sec	
5,000 - 10,000 m 2.0 m/sec	
Float altitude 11,800 m	
Radar	
Computed_xxxx	
Calibration data	
Sun angleCode period $(10^{-1} \text{ sec})$	
10° 34.2	
30° 21.8	
80° 11.5	

80°

Occulting angle

been

Balloon #	73202 P	
Frequency		
Method of leak te	st not te	sted
Test results		
Mfr. balloon #	Schjeldal	h1 15
Balloon mass	1467	gm
Balloon volume	6.06	m <sup>3</sup>
Balloon diameter_	2.26	m
Film thickness	2 .	mils
Electronics mass_	149	gm
Ballast	64	gm
Gross weight less		
Free lift	300	gm
Launch site	172° 32'E,	43°29's
Launch time 17/	01/67 21:	28 UT
Ascent rate		
0 - 5,000 m	1.6	m/sec
5,000 - 10,000 r	n 2.0	m/sec
Float altitude	11,800	m
Radar		
Computed_xxxx		
g 1:1		

Surface windso	m/sec
Cloud cover	
Climb-out winds	UT
0 - 5,000 m	
5,000 - 10,000 m	
10,000 m - altitude	
Altitude	

Flight duration	4	days
Flight duration 4	balloon	days
Number of orbits	0	
Position last heard	(20/01/6	7)
Balloon days tracked_	4	

Remarks: It is believed that this uvinol coated balloon was packed before the surface treatment had hardened. The balloon may have been damaged in unpacking.

Probable cause of failure: balloon leak.

## Calibration data

Sun angle--Code period  $(10^{-1} \text{ sec})$ 

5.0
6.7
9.3
Occulting angle

Balloon #	74038 F	Surface winds o calm m/sec
Frequency	15.028 MHz	Cloud cover
		Climb-out winds UT
Method of leak	test <u>not tested</u>	0 - 5,000 m
Test results		5,000 - 10,000 m
- Annanasana		10,000 m - altitude
· · · · · · · · · · · · · · · · · · ·		Altitude
Mfr. balloon #_	Schjeldahl 1	Flight duration 1 days
Balloon mass	6640 gn	Flight duration <u>1</u> balloon days
Balloon volume_	158 m <sup>3</sup>	Number of orbits 0
Balloon diamete	r 6.7 m	Position last heard 74556 (19/01/67)
Film thickness_	1 mils	Balloon days tracked 1
Electronics mas	s 125 gm	
Ballast	175 gm	Remarks: This balloon was not tested
Gross weight le	ss helium <u>6940</u> gm	The balloon carried 600 gm dry ice to
Free lift	1249 gm	reduce its ascent rate.
		Probable cause of failure: large
Launch site	172° 32'E, 43° 29'S	hole or tear in balloon.
Launch time	18/01/67 0945 UI	
Ascent rate		
0- 10,000 m	2.0 m/sec	
10,000 - 24,00	00 m 2.5 m/sec	2
Float altitude_	24,000 n	1
Radar	_	
Computed xxxx	2	
Calibration dat	ca.	
Sun angleCo	ode period $(10^{-1} \text{ sec})$	
10°	26.0	_
30°	17.2	_
66°	10.5	-
66	$5^{\circ}$ Occulting angle	<u>.</u>

balloon

Balloon #	75030 V		Surface winds	° calm	m/sec
Frequency	15.030	MHz	Cloud cover		
			Climb-out winds		
Method of leak	test not test	ted	0 - 5,000 m		
Test results			5,000 - 10,000 m_		
			10,000 m - altitude		
•			Altitude		
Mfr. balloon #	Schjeldahl 3		Flight duration	67	days
	6297				
Balloon volume	1				
	er6.7				
Film thickness	_				
Electronics ma		gm	•		
Ballast	494	gm	Remarks: The balloon	n carri	ed 600 gm
	ess helium <u>694</u> 0		dry ice to reduce as	cent ra	te.
Free lift	1249	gm	Probable cause of	failure	: balloo
			leak.		
Launch site	172° 32'E, 43	3 <sup>o</sup> 29 ' s			
Launch time	19/01/67 09	935 UT			
Ascent rate					
0- 10,000 m_	2.0	m/sec			
10,000 - 24,00	00 m 2.5	m/sec			
Float altitude	24,000	m			
Radar	<u> </u>				
Computed xxx	<u>x</u>				
Calibration da	ta				
Sun angleCo	ode period (10 <sup>-1</sup> 19.6	sec)			
30°	12.8				
66°	7.9				

66°

Occulting angle

Balloon # 76034 Z	Surface winds o calm m/sec
Frequency 15.024 MHz	Cloud cover
I.	Climb-out winds UT
Method of leak test <u>not tested</u>	0 - 5,000 m
Test results	5,000 - 10,000 m
	10,000 m - altitude
	Altitude
Mfr. balloon # Schjeldahl 5	Flight duration 18 days
Balloon mass 6042 gm	Flight duration 18 balloon days
Balloon volume 158 m <sup>3</sup>	Number of orbits 0
Balloon diameter 6.7 m	Position last heard (06/02/67)
Film thickness 1 mils	Balloon days tracked 15
Electronics mass 178 gm	
Ballast 720 gm	Remarks: Balloon was launched with
Gross weight less helium 6940 gm	600 gm dry ice to reduce ascent rate.
Free lift 1249 gm	Probable cause of failure: balloon
	leak.
Launch site 172° 32'E, 43° 29'S	
Launch time 19/01/67 0930 UT	
Ascent rate	
0 -10,000 m 2.0 m/sec	
10,000 - 24,000 m 2.5 m/sec	
Float altitude 24,000 m	
Radar	
Computed <u>xxx</u> x	
Calibration data	
Sun angleCode period (10 <sup>-1</sup> sec)	
10° 24.2	
30° 15.0	
66° 8.6	
66° Occulting angle	

Balloon #	77035 A		Surface winds ocalm	m/sec
Frequency	15.025	MHz	Cloud cover	
			Climb-out winds	UT
Method of leak	test <u>not te</u> s	sted	0 - 5,000 m	1000
Test results_			5,000 - 10,000 m	The state of the s
-			10,000 m - altitude	Wing
			Altitude	
Mfr. balloon #	Schjeldahl	5	Flight duration 1	days
Balloon mass			Flight duration 1 balloo	
Balloon volume			Number of orbits 0	
Balloon diamet	er <u>6.7</u>	m <sub>·</sub>	Position last heard 74666 (21	<u>/01/6<b>7</b></u> )
Film thickness	11	mils	Balloon days tracked	
Electronics ma				
Ballast	463	gm	Remarks: The balloon carried	600 gm
Gross weight 1	ess helium <u>69</u>	40 gm	dry ice to reduce ascent rate	•
Free lift	1249	gm	Probable cause of failure:	balloon
			leak.	
Launch site	172° 32'E,	43°29'S		
Launch time 2	0/01/67 0	755 UT		
Ascent rate				
0- 10,000 m_	2.0	m/sec		
10,000 - 24,00	00 m 2.5	m/sec		
Float altitude	24,000	m		
Radar	_			
Computed xxx	×			
Calibration da				
Sun angleCo	ode period (10	sec)		
	**************************************	<del></del>		•
	Occulting	g angle		

Balloon #	78201 B	····	Surface winds	o m/sec
Frequency	15.021	MHz	Cloud cover	
			Climb-out winds	UT
Method of leak te	st <u>not teste</u>	ed	0 - 5,000 m_	
Test results			5,000 - 10,000 m	
·	·		10,000 m - altitude	
			Altitude	
Mfr. balloon #	Schjeldahl	24	Flight duration	2 days
Balloon mass	1472	gm	Flight duration 2	balloon days
Balloon volume	6.06	m <sup>3</sup>	Number of orbits	0
Balloon diameter_	2.26	m	Position last heard_	
Film thickness		mils	Balloon days tracked_	2
Electronics mass_	150	gm		
Ballast	58	gm	Remarks: It is belie	ved that this
Gross weight less	helium 1680	) gm	uvinol coated balloon	was packed
Free lift	300	gm	before the surface tr	eatment had
			hardened.	
Launch site	172° 32'E, 43	° 29 ' S	Probable cause o	f failure:
Launch time 05	<u>/02/67 2112</u>	<u>UT</u>	balloon leak.	
Ascent rate				
0 - 5,000 m	1.6	m/sec		
5,000 - 10,000 m	n 2.0	m/sec		
Float altitude	11,800	m		
Radar				
Computed xxxx				
Calibration data				
Sun angleCode	period $(10^{-1})$	sec)		
10°	27.0	·		
30°	18.5			
80°	11.2			
80°	Occulting	angle		

Balloon #	79202 R		Surface winds
Frequency	15.022	MHz	Cloud cover
			Climb-out wind
Method of leak tes	st <u>tent</u>	test	0 - 5,000 m
Test results no	Leaks det	ected	5,000 - 10,0
			10,000 m - a
			Altitude
Mfr. balloon #	Schjeld.	ah1 16	Flight duration
Balloon mass	1440	gm	Flight duration
Balloon volume	6.06	m <sup>3</sup>	Number of orb
Balloon diameter_	2.26	<u>m</u>	Position last
Film thickness	2	mi1s	Balloon days
Electronics mass_	127	gm	
Ballast	113	gm	Remarks: Bal
Gross weight less	helium	1680 gm	26/05/67 on i
Free lift	300	gm	to be present
			night and sti
Launch site	172° 32 'E	43° 29'S	
Launch time 15	/02/67	2205 UT	
Ascent rate			
0 - 5,000 m	1.6	m/sec	
5,000 - 10,000 m	n 2.0	m/sec	
Float altitude	11,800	m	
Radar			
Computed xxxx			
Calibration data			
Sun angleCode	period (	10 <sup>-1</sup> sec)	
10°	26.2		
30°	17.3		
80°	9.5		
80°	Occult;	ing angle	

Occulting angle

Surface windso	m/sec
Cloud cover	
Climb-out winds	UT
0 - 5,000 m	
5,000 - 10,000 m	
10,000 m - altitude	
Altitude	

Flight duration see	remarks	days
Flight duration	balloon	days
Number of orbits		
Position last heard		
Balloon days tracked	1	

loon last heard on ts 100th day. Believed ly in the Antarctic 11 flying.

Balloon #	80303 DMHU	J	Surface winds		m/sec
Frequency	15.023	MHz	Cloud cover	broken	altocumulus
			Climb-out winds	S	UT
Method of leak	test tent te	est	0 - 5,000 m_		
Test results no	leaks discove	ered	5,000 - 10,00	00 m	·
	<u></u>		Altitude	270° 2	25 m/sec
Mfr. balloon #_	Schjeldahl	1 4	Flight duration	1	15 days
Balloon mass	2108	gm	Flight duration	1 15	balloon days
Balloon volume_	6.06	m <sup>3</sup>	Number of orbit	:s	0
Balloon diamete	er 2.26	m	Position last h	neard <u>838</u>	818 (07/03/67)
Film thickness_	3.0	mils	Balloon days tr	acked	15
Electronics mas	ss <u>169</u>	gm			
Ballast	103	gm	Remarks: Strain	n gauge	improperly
Gross weight le		380 gm	installed and		
Free lift	300	gm	ful stress data	a. Ball	oon flew well
			with no indica	tion of	icing problems
Launch site	172° 32 'E, 4	43° 29'S	through 07/03/	67. It	was not heard
Launch time 20	0/02/67 2:	210 UT	on 08/03/67.		
Ascent rate			U stra	in; D	air tempera-
0 - 5,000 m_	1.4	m/sec	ture; H sun	angle;	M reference
5,000 - 9,00	00 m 1.6	m/sec	Probable	cause of	failure:
Float altitude	9160	<u>m</u>	balloon leak o	r icing.	
Radar	_				
Computed xxx	x				
Calibration da	ta HHH				
•	ode period (10	-1 sec)			
10°	22.6				
30°	14.9	<del></del>			
65°	7.1	<del></del>			
6	5° Occulting	g angle			

Balloon #	81306 VKI	łD
Frequency	15.026	MHz
Method of leak tes	st <u>tent</u>	est
Test results	no leaks	found
Mfr balloon #	Sch ioldal	.1 5
Mfr. balloon # Balloon mass		
Balloon volume		
Balloon diameter_		
Film thickness		
Electronics mass_		
Ballast		
Gross weight less		
Free lift		
		·
Launch site	172°32'E,	43 <sup>0</sup> 29 ' S
Launch time 23/02		
Ascent rate		
0 - 5,000 m	2.0	m/sec
5,000 - 9,000 m		
Float altitude		
Radar		
Computed_xxxx		
Calibration data	ННН	
Sun angleCode	period (10	-1 sec)
10 <sup>°</sup>	28.0	
30°	14.5	
65°	6.0	
65 <sup>°</sup>	Occultin	g angle

Surface windso	m/sec
Cloud cover	···
Climb-out winds	UT
0 - 5,000 m	
5,000 - 10,000 m	
10,000 m - altitude	
Altitude	

Flight duration 3 days

Flight duration 3 balloon days

Number of orbits 0

Position last heard 72768 (26/02/67)

Balloon days tracked 3

Remarks: Balloon flew well for 3 days with no evidence of gas loss. On the first day, clouds as indicated by the sun sensor data produced an overpressure drop from 56 mb to 29 mb. On the second and third days with clear skies above, overpressure increased from 30 mb to 50 mb as the sun angle increased from 10° to 80°.

It appears that the helium temperature was 10 to  $12^{\circ}$  colder than ambient at night at 300 mb. Daytime solar heating was measured at 12 to  $14^{\circ}$  C.

H -- sun angle; V -- air temperature; D -- strain; K -- reference.

Probable cause of failure: icing.

Frequency         15.027         MHz         Cloud cover cirrus           Climb-out winds         UT           Method of leak test tent test         0 - 5,000 m           Test results         1 leak detected         5,000 - 10,000 m           and repaired         10,000 m - altitude	Surface winds <sup>O</sup> m/sec	3alloon #82307 UMSN
Method of leak test         tent test         0 - 5,000 m           Test results         1 leak detected         5,000 - 10,000 m	MHz Cloud cover cirrus	Frequency 15.027 MHz
Test results	Climb-out winds UT	
	0 - 5,000 m	Method of leak test tent test
and repaired 10 000 m - altitude	ed 5,000 - 10,000 m	Test results 1 leak detected
	10,000 m - altitude	and repaired
Altitude	Altitude	
Mfr. balloon # Raven 3 Flight duration 1 days	Flight duration 1 days	Mfr. balloon #Raven 3
Balloon mass 2175 gm Flight duration 1 balloon days	gm Flight duration 1 balloon days	Balloon mass 2175 gm
Balloon volume 6.06 m <sup>3</sup> Number of orbits 0	m <sup>3</sup> Number of orbits 0	Balloon volume 6.06 m <sup>3</sup>
Balloon diameter 2.26 m Position last heard 74379 (12/03/67)	m Position last heard 74379 (12/03/67)	Balloon diameter 2.26 m
Film thickness 3.0 mils Balloon days tracked 1	ils Balloon days tracked 1	Film thickness 3.0 mils
Electronics mass 180 gm	gm	Electronics mass 180 gm
Ballast 33 gm Remarks: Balloon went to altitude	gm Remarks: Balloon went to altitude	Ballast <u>33</u> gm
Gross weight less helium $2388$ gm and superpressured properly. Sun	gm and superpressured properly. Sun	Gross weight less helium 2388 gm
Free lift 425 gm sensor data from weak signals indicated	gm sensor data from weak signals indicated	Free lift 425 gm
heavy clouds. Data obtained for on	heavy clouds. Data obtained for only	
Launch site 172° 32'E, 43° 29'S 2 hr.	9'S 2 hr.	Launch site 172° 32'E, 43° 29'S
Launch time $11/03/67$ $1955$ UT U air temperature; M ref	UT U air temperature; M refer-	Launch time 11/03/67 1955 UT
Ascent rate ence; S sun angle; N strain	ence; S sun angle; N strain	Ascent rate
0 - 5,000 m 2.0 m/sec gauge.	sec gauge.	0 - 5,000 m 2.0 m/sec
5,000 - 9,000 m 2.5 m/sec Probable cause of failure: ici	sec Probable cause of failure: icing.	5,000 - 9,000 m 2.5 m/sec
Float altitude 9100 m	<u>m</u>	Float altitude 9100 m
Radar		Radar
Computed_xxx_		
Calibration data SSS		Calibration data SSS
Sun angleCode period $(10^{-1} \text{ sec})$	ec)	Sun angleCode period (10 <sup>-1</sup> sec)
10° 29.5		10° 29.5
30° 20.0		30° 20.0
61° 9.6		61° 9.6
61° Occulting angle	gle	61° Occulting angle

Balloon #	83305 VWHR	Surface winds O m/sec
Frequency	15.025 MHz	
		Climb-out winds UT
Method of leak te	sttent_test	0 - 5,000 m
Test results	l pinhole leak	5,000 - 10,000 m
	detected and	10,000 m - altitude
	repaired	Altitude
Mfr. balloon #	Raven 2	Flight duration 1 days
Balloon mass	2194 gm	Flight duration $1$ balloon days
Balloon volume	6.06 m <sup>3</sup>	Number of orbits0
Balloon diameter_	2.26 m	Position last heard 74379 (12/03/67)
Film thickness	3.0 mils	Balloon days tracked $1$
Electronics mass_	177 gm	
Ballast	33 gm	Remarks: V air temperature; W
Gross weight less	helium 2404 gm	reference; H sun angle; R strain
Free lift	432 gm	gauge.
		Balloon flown together with
Launch site	172° 32'E, 43° 29'S	82 UMSN, 84 W, and 85 WKRD.
Launch time 11	/03/67 2015 UT	Balloon went to altitude and over-
Ascent rate		pressured properly. Sun sensor data
0 - 5,000 m	2.0 m/sec	from weak signals indicated heavy
5,000 - 9,000	m 2.5 m/sec	clouds. Data obtained for only 15
Float altitude	9080 m	hr.
Radar		Probable cause of failure: icing.
Computed xxx		
Calibration data	ННН	
Sun angleCode	period $(10^{-1} \text{ sec})$	
10°	26.5	
30°	15.8	
61°	8.7	
61°	Occulting angle	

Balloon #	84308 W		Surface winds	m/sec
Frequency	15.028	MHz	Cloud cover	
			Climb-out winds	UT
Method of leak	test tent tes	s t	0 - 5,000 m	
Test results	1 pinhole leak		5,000 - 10,000 m_	
dete	cted and repaire	ed	10,000 m - altitude	
			Altitude	
Mfr. balloon #	Raven 1	<del></del>	Flight duration 1	days
Balloon mass	2182	gm	Flight duration 1 balloo	on days
Balloon volume	6.06	m <sup>3</sup>	Number of orbits 0	
Balloon diamet	er2.26	m	Position last heard	
Film thickness	3	mils	Balloon days tracked 1	······································
Electronics ma	lss162	gm		
Ballast	34	gm	Remarks: Balloon was tracked	for
Gross weight 1	ess helium 2378	8 gm	only 35 min and disappeared	in
Free lift	425	gm	clouds.	
			Probable cause of failure:	icing
Launch site	172° 32 'E, 43	3 <sup>0</sup> 29 ' S	on ascent.	
Launch time]	11/03/67 2220	UT		
Ascent rate				
0 - 5,000 m	2.0	m/sec		
5,000 - 9,0	000 m 2.5	m/sec		
Float altitude	9140	m		
Radar				
Computed xxx	<u>αχ</u>			
Calibration da	ıta			
Sun angle0	Code period $(10^{-1})$	sec)		
10°	29.0			
30°	19.9			
80°				
•	80° Occulting	angle		

Balloon #	85307 WKRD
Frequency	15.027 MHz
Method of leak tes	ttent_test
Test results	l pinhole leak
•	detected and
	repaired.
Mfr. balloon #	Raven 5
Balloon mass	2211 gm
Balloon volume	6.06 m <sup>3</sup>
Balloon diameter	2.26 m
Film thickness	3.0 mils
Electronics mass	178 gm
Ballast	34 gm
Gross weight less	helium 2423 gm
Free lift	432 gm
Launch site	172° 32'E, 43° 29'S
Launch time 11/	03/67 2245 UT
Ascent rate	
0 - 5,000 m	2.0 m/sec
5,000 - 9,000 m	2.5 m/sec
Float altitude	9060 m
Radar	
Computed xxxx	
Calibration data	RRR
	period $(10^{-1} \text{ sec})$
10°	27.1
30°	17.9
85°	8.6
85°	Occulting angle

Surface winds	0	m/sec
Cloud cover	cirrus	
Climb-out winds		UT
0 - 5,000 m_		
5,000 - 10,00	00 m	
10,000 m - al	titude	
Altitude		

Flight duration 51+ days

Flight duration 53 balloon days

Number of orbits 2

Position last heard  $\frac{65672}{2}$  (30/04/67)

Balloon days tracked 25

Remarks: R -- sun angle; W -- air temperature; D -- strain gauge; K -- reference.

This balloon was flown together with 82 UMSN, 83 VWHR, and 84 W. All of these apparently failed within one day of launch. 85 WKRD flew for 51 days and moved into the Antarctic night on 30/04/67. It still indicated adequate overpressure and may still be flying. The only difference on this flight with respect to the others was a different antenna design permitting a suspension of the electronics 13 m below the balloon.

Balloon #	86025 C		Surface winds o calm m/sec
Frequency	15.025	MHz	Cloud cover high cirrus
			Climb-out winds UT
Method of leak te	st factory H <sub>2</sub>	0 test	0 - 5,000 m calm
Test results no 1	eaks detected		5,000 - 10,000 m calm
National Control of the Control of t			10,000 m - altitude calm
			Altitude calm
Mfr. balloon #	Raven 104		Flight duration see remarks days
Balloon mass	6690	gm	Flight duration balloon days
Balloon volume	216	m <sup>3</sup>	Number of orbits
Balloon diameter_	7.4	m	Position last heard
Film thickness	1	mils	Balloon days tracked
Electronics mass_	169	gm	
Ballast	54	gm	Remarks: Balloon still flying on
Gross weight less	helium <u>6913</u>	gm	09/06/67 on 89th day. This balloon
Free lift	1244	gm	carried 600 gm dry ice to reduce
			ascent rate.
Launch site	172° 32 'E, 43	°29 <b>'</b> S	
Launch time 13/	<u>'03/67 194</u>	5 UT	
Ascent rate			
0 - 10,000 m	2.0	m/sec	
10,000 - 25,000	m 2.5	m/sec	
Float altitude	25,500	<u>m</u>	
Radar			
Computed xxxx			
Calibration data			
Sun angleCode	period $(10^{-1})$	sec)	
10°	33.0		
30°	20.4		
64°	11.4		
64 <sup>0</sup>	Occulting	angle	

Balloon # 8/023 J 8/025 P	Surface winds calm m/sec
Frequency 15.023 15.025 MHz	Cloud cover
	Climb-out winds UT
Method of leak test factory H <sub>2</sub> O test	0 - 5,000 m
Test results no leaks detected.	5,000 - 10,000 m
H4 10	10,000 m - altitude
	Altitude
Mfr. balloon # Raven 103	Flight duration see remarks days
Balloon mass 5897 gm	Flight duration balloon days
Balloon volume 216 m <sup>3</sup>	Number of orbits
Balloon diameter 7.4 m	Position last heard 76089 (28/04/67)
	Balloon days tracked
Electronics mass 325 gm	
Ballast276 gm	Remarks: Since this balloon is equipped
Gross weight less helium $\underline{6500}$ gm	with a strain gauge, it is possible to
Free lift 1200 gm	monitor gas loss and estimate flight
	duration. Flight duration should be
Launch site 172° 32'E, 43° 29'S	between 4 and 6 months. It is assumed
Launch time 16/03/67 1955 UT	as of $10/06/67$ that this balloon re-
Ascent rate	mains in the Antarctic night.
0 -10,000 m 2.0 m/sec	J transmits sun angle information,
10,000 - 25,000 m 2.5 m/sec	P transmits strain data.
Float altitude 25,800 m	
Radar	
Computed <u>xxx</u> x	
Calibration data JJJ	
Sun angleCode period (10 <sup>-1</sup> sec)	
10° 26.0	
30° 17.6	
80° 10.5	
80° Occulting angle	

Balloon #	88308 M	
Frequency	15.028	MHz
Method of leak tes		
Test results	no leaks	
	detected	
Mfr. balloon #	Raven 4	
Balloon mass	2145	gm
Balloon volume	6.06	m <sup>3</sup>
Balloon diameter_	2.26	<u>m</u>
Film thickness		mils
Electronics mass_	160	gm
Ballast		gm
Gross weight less		0 gm
Free lift		gm
Launch site	172° 32'E, 4	3° 29 ' S
Launch time 16	/03/67 21	00 UT
Ascent rate		
0 - 5,000 m_	2.0	m/sec
5,000 - 9,000 m	m2,5	m/sec
Float altitude	9500	m
Radar		
Computed xxxx		
Calibration data		
Sun angleCode	period (10	1 sec)
10°	29.5	
30°	21.4	
80°	13.7	
80°	Occulting	angle
		<del>-</del>

Surface windso	m/sec
Cloud cover	
Climb-out winds	UT
0 - 5,000 m	near an annual annua
5,000 - 10,000 m	
10,000 m - altitude_	
Altitude	

Flight duration 4 days
Flight duration 4 balloon days
Number of orbits 0
Position last heard 64345 (19/03/67)
Balloon days tracked 4

Remarks: This balloon was highly stressed for 2 days prior to launch to introduce a permanent creep which provided a volume increase of 4%.

Probable cause of failure: icing.

Balloon #	89305 W	Surface winds m/sec
Frequency	15.025 M	Hz Cloud cover
		Climb-out winds 1700 UT
Method of leak	test tent test	
Test results	no leaks	5,000 - 10,000 m 360° 46 m/sec
***************************************	detected	10,000 m - altitude
		Altitude $360^{\circ}$ 52 m/sec
Mfr. balloon #_	Viron 1-B	Flight duration 12 days
Balloon mass	1008	gm Flight duration 12 balloon days
Balloon volume_	5.04	
Balloon diamete	r 2.13	$\underline{m}$ Position last heard 64913 (05/04/67)
Film thickness_	1.5 mi	<u>ls</u> Balloon days tracked 11
Electronics mas	s158	<u>gm</u>
Ballast	564	gm Remarks: This balloon was designed t
Gross weight le	ss helium <u>1730</u>	gm fly at 200 mb but was heavily ballast
Free lift	182	gm for flight at 250 mb.
		Probable cause of failure: defect
Launch site	172° 32'E, 43° 29	'S introduced by over-stressed design.
Launch time 2	5/03/67 1945	<u>UT</u>
Ascent rate		
0 - 5,000 m	1.5 m/s	<u>ec</u>
5,000 - 10,00	0  m   1.8  m/s	ec
Float altitude_	10,500	<u>m</u>
Radar		
Computed xxxx		
Calibration dat	a	
Sun angleCo	de period (10 <sup>-1</sup> se	c)
10°	42.9	
30°	23.9	·
80°	9.8	
80	Occulting ang	<u>le</u>

Balloon # 90027 O 90026 A	Surface winds o calm m/sec
Frequency 15.027 15.026 MHz	Cloud cover
	Climb-out winds UT
Method of leak test factory H <sub>2</sub> O test	0 - 5,000 m
Test results no leaks	5,000 - 10,000 m
detected	10,000 m - altitude
	Altitude
Mfr. balloon # Raven 106	Flight duration see remarks days
Balloon mass 5886 gm	Flight duration balloon days
Balloon volume 216 m <sup>3</sup>	Number of orbits
Balloon diameter 7.4 m	Position last heard 66220 (23/04/67)
Film thickness 1 mils	Balloon days tracked
Electronics mass 350 gm	
Ballast 264 gm	Remarks: This balloon was last heard
Gross weight less helium 6500 gm	on 23/04/67. Since it was equipped
Free lift 1200 gm	with a strain gauge, it was possible
	to estimate life at between $2$ and $3$
Launch site 172° 32'E, 43° 29'S	months. As of 10/06/67 the balloon
Launch time <u>25/03/67</u> <u>1950</u> <u>UT</u>	remains in the Antarctic night.
Ascent rate	Since dry ice was not available,
0 -10,000 m 2.0 m/sec	methyl alcohol was used as a dribble
10,000 - 20,000 m 2.5 m/sec	ballast to reduce ascent rate.
Float altitude 25,800 m	O transmits sun angle information,
Radar	A transmits strain data.
Computed xxxx	
Calibration data 000	
Sun angleCode period $(10^{-1} \text{ sec})$	
10° 27.9	
30° 18.6	
80° 10.8	
80° Occulting angle	

Balloon #	91022 D		Surface winds o calm m/se
Frequency	15.022	MHz	Cloud cover
			Climb-out windsU
Method of leak to	est_factory wa	ater te	st 0 -10,000 m 270° 3 m/sec
Test results			
Table Townson of the State of t	detected		10,000 m - altitude
• 194			Altitude
Mfr. balloon #	Raven 102		Flight duration see remarks day
Balloon mass	5897	gm	Flight duration balloon day
Balloon volume	216	m <sup>3</sup>	Number of orbits
Balloon diameter	7.4	· m	Position last heard 55610 (05/05/6
Film thickness_	1	mils	Balloon days tracked
Electronics mass	160	gm	
Ballast	443	gm	Remarks: Last reported position on
Gross weight less	s helium <u>6500</u>	gm	this balloon on its 40th day at $56^\circ$
Free lift	1200	gm	latitude with a maximum sun angle
			$18^{\circ}$ . We cannot determine as yet
Launch site	172° 32'E, 43	°29'S	whether the balloon failed at this
Launch time 26,	<u>/03/67 1950</u>	UT	time or whether it moved into the
Ascent rate			Antarctic night.
0 -10,000 m	4.0	m/sec	
10,000 - 20,000	m3.5	m/sec	
Float altitude	25,800	m	
Radar			
Computed xxxx			
Calibration data			
Sun angleCode	period $(10^{-1})$	sec)	
10°	42.4		
30°	21.1		
64°	8.6		
64°	Occulting	angle	

#### REFERENCES

- 1. Grass, L. A., 1962: <u>Superpressure Balloon for Constant Level Flight</u>, AFCRL Res. Rept. 62-824 (Aug.), pp. 9, 11, 12.
- Nerkin, A., 1956: "Experiments on flows of gases through leaks," in 1956 National Symposium on Vacuum Technology Transactions, 4 pp.
- 3. Lichfield, E. W. and R. W. Frykman, 1966: "Ghost balloons riding the skies will report the world's weather," <u>Electronics</u> (<u>Nov. 28</u>), 98-106.
- 4. National Academy of Sciences, 1966: The Feasibility of a Global
  Observation and Analysis Experiment, Report of the Panel on International Meteorological Cooperation to the Committee on Atmospheric Sciences, NAS-NRC Publ. No. 1290, 172 pp.

• .